

National Aeronautics and Space Administration

**Technology Evaluation for Environmental Risk
Mitigation Principal Center (TEERM)**

**Hexavalent Chrome Free Coatings for Electronics
Applications**

DRAFT Joint Test Report

August 2012

TABLE OF CONTENTS

LIST OF TABLES	iv
LIST OF FIGURES	iv
1 Introduction.....	1
1.1 Background.....	1
1.2 Objective.....	1
2 Materials	2
2.1 Alloys.....	2
2.2 Panel Preparation	2
2.3 Pretreatments	3
3 Pretreatment Testing	4
3.1 Salt Spray Resistance.....	5
3.1.1 Test Procedure	5
3.1.2 Evaluation Procedure	5
3.1.3 Test Results – ASTM B 117, 168 hours	5
3.1.4 Test Panel Pictures	11
3.1.4.1 Alodine 1600	11
3.1.4.2 Alodine T 5900 RTU.....	13
3.1.4.3 Iridite NCP.....	15
3.1.4.4 Metalast HF	17
3.1.4.5 Metalast HF-EPA	19
3.1.4.6 SurTec 650.....	21
3.1.4.7 SurTec 650C	23
3.1.5 Test Results – ASTM B 117, to Failure.....	25
3.1.6 Test Panel Pictures	30
3.1.6.1 Alodine 1600	30
3.1.6.2 Alodine T 5900 RTU.....	32
3.1.6.3 Iridite NCP.....	34
3.1.6.4 Metalast HF	36
3.1.6.5 Metalast HF-EPA	38
3.1.6.6 SurTec 650.....	40
3.1.6.7 SurTec 650C	42
3.2 Cyclic Corrosion	44
3.2.1 Test Procedure	44
3.2.2 Evaluation Procedure	44
3.2.3 Test Results – ASTM G 85 Annex 5, 168 hours	44
3.2.4 Test Panel Pictures	49
3.2.4.1 Alodine 1600	49
3.2.4.2 Alodine T 5900 RTU.....	51
3.2.4.3 Iridite NCP.....	53
3.2.4.4 Metalast HF	55
3.2.4.5 Metalast HF-EPA	57
3.2.4.6 SurTec 650.....	59
3.2.4.7 SurTec 650C	61

3.3	Marine Environment	63
3.3.1	Test Procedure	63
3.3.2	Evaluation Procedure	63
3.3.3	Test Results – Beachside Corrosion, 5 Weeks.....	63
3.3.4	Test Panel Pictures – Beachside Corrosion Laboratory; Day 1	64
3.3.5	Test Panel Pictures – 5 Weeks of Beach Front Exposure	69
3.3.5.1	Alodine 1600	69
3.3.5.2	Alodine T 5900 RTU	71
3.3.5.3	Iridite NCP.....	73
3.3.5.4	Metalast HF	75
3.3.5.5	Metalast HF-EPA	77
3.3.5.6	SurTec 650.....	79
3.3.5.7	SurTec 650C	81
3.4	PATTI JR Pull Test.....	83
3.4.1	Test Procedure	83
3.4.2	Evaluation Procedure	83
3.4.3	Test Results – PATTI JR Pull Test.....	83
3.4.4	Test Panel Pictures with Burst Pressure Readings (psi)	86
3.4.4.1	Alodine T 5900 RTU – PPG CA7233	86
3.4.4.2	Iridite NCP - PPG CA7233	87
3.4.4.3	Metalast HF - PPG CA7233	88
3.4.4.4	Metalast HF-EPA - PPG CA7233	89
3.4.4.5	SurTec 650 - PPG CA7233	90
3.4.4.6	SurTec 650C - PPG CA7233.....	91
3.4.5	Test Panel Pictures with Burst Pressure Readings (psi)	92
3.4.5.1	Alodine T 5900 RTU - Deft 44-GN-07A	92
3.4.5.2	Iridite NCP - Deft 44-GN-07A.....	93
3.4.5.3	Metalast HF - Deft 44-GN-07A.....	94
3.4.5.4	Metalast HF-EPA - Deft 44-GN-07A.....	95
3.4.5.5	SurTec 650 - Deft 44-GN-07A.....	96
3.4.5.6	SurTec 650C - Deft 44-GN-07A	97
3.5	Cross-Cut Tape Test	98
3.5.1	Test Procedure	98
3.5.2	Evaluation Procedure	98
3.5.3	Test Results – Cross-Cut Tape Test.....	100
3.5.4	Test Panel Pictures with ASTM D 3359, Test Method B Ratings.....	102
3.5.4.1	Alodine T 5900 RTU - PPG CA7233 - PPG CA9311	102
3.5.4.2	Iridite NCP - PPG CA7233 - PPG CA9311	103
3.5.4.3	Metalast HF - PPG CA7233 - PPG CA9311	104
3.5.4.4	Metalast HF-EPA - PPG CA7233 - PPG CA9311	105
3.5.4.5	SurTec 650 - PPG CA7233 - PPG CA9311	106
3.5.4.6	SurTec 650C - PPG CA7233 - PPG CA9311.....	107
3.5.5	Test Panel Pictures with ASTM D 3359, Test Method B Ratings.....	108
3.5.5.1	Alodine T 5900 RTU – Deft-44-GN-07A - PPG CA9311	108

3.5.5.2	Iridite NCP - Deft-44-GN-07A - PPG CA9311	109
3.5.5.3	Metalast HF – Deft-44-GN-07A - PPG CA9311	110
3.5.5.4	Metalast HF-EPA – Deft-44-GN-07A - PPG CA9311	111
3.5.5.5	SurTec 650 – Deft-44-GN-07A - PPG CA9311	112
3.5.5.6	SurTec 650C – Deft-44-GN-07A - PPG CA9311	113
3.6	Wet Tape Paint Adhesion	114
3.6.1	Test Procedure	114
3.6.2	Evaluation Procedure	115
3.6.3	Test Results – Wet Tape Adhesion, 24 Hour Immersion	115
3.6.4	Test Panel Pictures - Wet Tape Adhesion, 24 Hour Immersion	118
3.6.4.1	Alodine T 5900 RTU - PPG CA7233.....	118
3.6.4.2	Iridite NCP - PPG CA7233	118
3.6.4.3	Metalast HF - PPG CA7233	119
3.6.4.4	Metalast HF-EPA - PPG CA7233	119
3.6.4.5	SurTec 650 - PPG CA7233	120
3.6.4.6	SurTec 650C - PPG CA7233.....	120
3.6.5	Test Panel Pictures - Wet Tape Adhesion, 24 Hour Immersion	121
3.6.5.1	Alodine T 5900 RTU – Deft 44-GN-07A	121
3.6.5.2	Iridite NCP - Deft 44-GN-07A.....	121
3.6.5.3	Metalast HF - Deft 44-GN-07A.....	122
3.6.5.4	Metalast HF-EPA - Deft 44-GN-07A.....	122
3.6.5.5	SurTec 650 - Deft 44-GN-07A.....	123
3.6.5.6	SurTec 650C - Deft 44-GN-07A	123
3.6.6	Test Results – Wet Tape Adhesion, 96 Hour Immersion at 120°F.....	124
3.6.7	Test Panel Pictures - Wet Tape Adhesion, 96 Hour Immersion @ 120°F.....	126
3.6.7.1	Alodine T 5900 RTU – PPG CA7233	126
3.6.7.2	Iridite NCP - PPG CA7233	127
3.6.7.3	Metalast HF - PPG CA7233	128
3.6.7.4	Metalast HF-EPA - PPG CA7233	129
3.6.7.5	SurTec 650 - PPG CA7233	130
3.6.7.6	SurTec 650C - PPG CA7233.....	131
3.6.8	Test Panel Pictures - Wet Tape Adhesion, 96 Hour Immersion @ 120°F.....	132
3.6.8.1	Alodine T 5900 RTU – Deft 44-GN-07A	132
3.6.8.2	Iridite NCP - Deft 44-GN-07A.....	133
3.6.8.3	Metalast HF - Deft 44-GN-07A.....	134
3.6.8.4	Metalast HF-EPA - Deft 44-GN-07A.....	135
3.6.8.5	SurTec 650 - Deft 44-GN-07A.....	136
3.6.8.6	SurTec 650C - Deft 44-GN-07A	137
3.7	Surface Resistance Test	138
3.7.1	Test Procedure	138
3.7.2	Evaluation Procedure	138
3.7.3	Test Results - Surface Resistance Test	138
3.8	Contact Electrical Resistance.....	141
3.8.1	Test Procedure	141

3.8.2	Evaluation Procedure	142
3.8.3	Test Results - Contact Electrical Resistance	142
3.9	Screening Level Testing	144
4	Results Summary	145
5	Recommendations.....	150
5.1	Proposed Panel Preparation Procedure	150
5.2	Proposed Testing.....	151

LIST OF TABLES

Table 1 - Alloys Procured.....	2
Table 2 - Pretreatment Procurement	3
Table 3 – Pretreatment Testing	4

LIST OF FIGURES

Figure 1 – ASTM B 117 Results @ 168 Hours; Alodine 1600.....	6
Figure 2 - ASTM B 117 Results @ 168 Hours; Alodine T 5900 RTU	7
Figure 3 - ASTM B 117 Results @ 168 Hours; Iridite NCP	7
Figure 4 - ASTM B 117 Results @ 168 Hours; Metalast HF.....	8
Figure 5 - ASTM B 117 Results @ 168 Hours; Metalast HF-EPA.....	8
Figure 6 - ASTM B 117 Results @ 168 Hours; SurTec 650	9
Figure 7 - ASTM B 117 Results @ 168 Hours; SurTec 650	9
Figure 8 – Alodine 1600, 1006 - 1010.....	11
Figure 9 – Alodine 1600, 1051 – 1054	11
Figure 10 - Alodine 1600, 1090 – 1093.....	12
Figure 11 - Alodine 1600, 1128 – 1132.....	12
Figure 12 – Alodine T 5900 RTU, 2006 – 2009.....	13
Figure 13 - Alodine T 5900 RTU, 2051 – 2055	13
Figure 14 - Alodine T 5900 RTU, 2089 – 2093	14
Figure 15 - Alodine T 5900 RTU, 2128 – 2132	14
Figure 16 – Iridite NCP, 3006 – 3009.....	15
Figure 17 – Iridite NCP, 3051 – 3055.....	15
Figure 18 – Iridite NCP, 3089 – 3093.....	16
Figure 19 – Iridite NCP, 3129 – 3132.....	16
Figure 20 – Metalast HF, 4006 – 4010	17
Figure 21 – Metalast HF, 4052 – 4055	17
Figure 22 – Metalast HF, 4089 – 4093	18
Figure 23 – Metalast HF, 4129 – 4132	18
Figure 24 – Metalast HF-EPA, 5006 – 5009	19
Figure 25 – Metalast HF-EPA, 5051 – 5055	19
Figure 26 – Metalast HF-EPA, 5089 – 5092	20
Figure 27 – Metalast HF-EPA, 5129 - 5132.....	20
Figure 28 – SurTec 650, 6006 – 6009.....	21
Figure 29 – SurTec 650, 6052 – 6055.....	21
Figure 30 – SurTec 650, 6089 - 6092	22

Figure 31 – SurTec 650, 6128 - 6131	22
Figure 32 – SurTec 650C, 7006 – 7010.....	23
Figure 33 – SurTec 650C, 7051 – 7055.....	23
Figure 34 – SurTec 650C, 7089 – 7093.....	24
Figure 35 – SurTec 650C, 7128 - 7132.....	24
Figure 36 - ASTM B 117 Results, To Failure; Alodine 1600	26
Figure 37 - ASTM B 117 Results, To Failure; Alodine T 5900 RTU	26
Figure 38 - ASTM B 117 Results, To Failure; Iridite NCP.....	27
Figure 39 - ASTM B 117 Results, To Failure; Metalast HF	27
Figure 40 - ASTM B 117 Results, To Failure; Metalast HF-EPA.....	28
Figure 41 - ASTM B 117 Results, To Failure; SurTec 650.....	28
Figure 42 - ASTM B 117 Results, To Failure; SurTec 650C	29
Figure 43 – Alodine 1600, 1011 - 1015	30
Figure 44 – Alodine 1600, 1056 – 1059	30
Figure 45 – Alodine 1600, 1094 – 1097	31
Figure 46 – Alodine 1600, 1133 - 1136.....	31
Figure 47 – Alodine T 5900 RTU, 2011 – 2015.....	32
Figure 48 – Alodine T 5900 RTU, 2056 – 2058.....	32
Figure 49 - Alodine T 5900 RTU, 2094 – 2097	33
Figure 50 – Alodine T 5900 RTU, 2133 – 2136.....	33
Figure 51 – Iridite NCP, 3011 – 3015.....	34
Figure 52 – Iridite NCP, 3056 – 3059.....	34
Figure 53 – Iridite NCP, 3094 – 3097.....	35
Figure 54 – Iridite NCP, 3133 – 3136.....	35
Figure 55 – Metalast HF, 4011 – 4015	36
Figure 56 – Metalast HF, 4059 – 4057	36
Figure 57 – Metalast HF, 4094 – 4097	37
Figure 58 – Metalast HF, 4133 – 4136	37
Figure 59 – Metalast HF-EPA, 5011 – 5015	38
Figure 60 – Metalast HF-EPA, 5056 – 5059	38
Figure 61 – Metalast HF-EPA, 5094 – 5097	39
Figure 62 – Metalast HF-EPA, 5133 – 5136	39
Figure 63 – SurTec 650, 6011 – 6015.....	40
Figure 64 – SurTec 650, 6056 – 6058.....	40
Figure 65 – SurTec 650, 6094 – 6097.....	41
Figure 66 – SurTec 650, 6136 - 6133	41
Figure 67 – SurTec 650C, 7011 – 7015.....	42
Figure 68 – SurTec 650C, 7056 – 6059.....	42
Figure 69 – SurTec 650C, 7094 – 7097.....	43
Figure 70 – SurTec 650C, 7136 - 7133.....	43
Figure 71 - ASTM G 85, Annex 5 Results, 168 Hours; Alodine 1600.....	45
Figure 72 - ASTM G 85, Annex 5 Results, 168 Hours; Alodine T 5900 RTU	45
Figure 73 - ASTM G 85, Annex 5 Results, 168 Hours; Iridite NCP.....	46
Figure 74 - ASTM G 85, Annex 5 Results, 168 Hours; Metalast HF.....	46

Figure 75 - ASTM G 85, Annex 5 Results, 168 Hours; Metalast HF-EPA.....	47
Figure 76 - ASTM G 85, Annex 5 Results, 168 Hours; SurTec 650.....	47
Figure 77 - ASTM G 85, Annex 5 Results, 168 Hours; SurTec 650C	48
Figure 78 – Alodine 1600, 1017 – 1019	49
Figure 79 – Alodine 1600, 1062 – 1064	49
Figure 80 – Alodine 1600, 1100 – 1102	50
Figure 81 – Alodine 1600, 1139 – 1141	50
Figure 82 – Alodine T 5900 RTU, 2017 – 2019.....	51
Figure 83 – Alodine T 5900 RTU, 2062 - 2064	51
Figure 84 – Alodine T 5900 RTU, 2100 – 2102.....	52
Figure 85 – Alodine T 5900 RTU, 2139 – 2142.....	52
Figure 86 – Iridite NCP, 3017 – 3019.....	53
Figure 87 – Iridite NCP, 3062 – 3064.....	53
Figure 88 – Iridite NCP, 3100 – 3102.....	54
Figure 89 – Iridite NCP, 3139 – 3142.....	54
Figure 90 – Metalast HF, 4017 – 4019	55
Figure 91 – Metalast HF, 4062 – 4064	55
Figure 92 – Metalast HF, 4100 – 4102	56
Figure 93 – Metalast HF, 4139 – 4141	56
Figure 94 – Metalast HF-EPA, 5016, 5018 – 5019	57
Figure 95 – Metalast HF-EPA, 5062 – 5064	57
Figure 96 – Metalast HF-EPA, 5100 - 5102	58
Figure 97 – Metalast HF-EPA, 5139 – 5141	58
Figure 98 – SurTec 650, 6017 – 6019.....	59
Figure 99 – SurTec 650, 6062 – 6064.....	59
Figure 100 – SurTec 650, 6100 – 6102.....	60
Figure 101 – SurTec 650, 6139 – 6141.....	60
Figure 102 – SurTec 650C, 7017 – 7019.....	61
Figure 103 – SurTec 650C, 7062 – 7064.....	61
Figure 104 – SurTec 650C, 7100 – 7102.....	62
Figure 105 – SurTec 650C, 7139 – 7141	62
Figure 106 - Beachside Corrosion; Rack 1	64
Figure 107 - Beachside Corrosion; Rack 2	65
Figure 108 - Beachside Corrosion; Rack 3	66
Figure 109 - Beachside Corrosion; Rack 4.....	67
Figure 110 - Beachside Corrosion; Rack 5	68
Figure 111 – Alodine 1600, 6061-T6	69
Figure 112 – Alodine 1600, 7075-T73	69
Figure 113 – Alodine 1600, 2024-T3	70
Figure 114 – Alodine 1600, 5052-H32	70
Figure 115 – Alodine T 5900 RTU, 6061-T6.....	71
Figure 116 – Alodine T 5900 RTU, 7075-T73	71
Figure 117 – Alodine T 5900 RTU, 2024-T3	72
Figure 118 – Alodine T 5900 RTU, 5052-H32.....	72

Figure 119 – Iridite NCP, 6061-T6.....	73
Figure 120 – Iridite NCP, 7075-T73.....	73
Figure 121 – Iridite NCP, 2024-T3.....	74
Figure 122 – Iridite NCP, 5052-H32.....	74
Figure 123 – Metalast HF, 6061-T6.....	75
Figure 124 – Metalast HF, 7075-T73.....	75
Figure 125 – Metalast HF, 2024-T3.....	76
Figure 126 – Metalast HF, 5052-H32.....	76
Figure 127 – Metalast HF-EPA, 6061-T6.....	77
Figure 128 – Metalast HF-EPA, 7075-T73.....	77
Figure 129 – Metalast HF-EPA, 2024-T3.....	78
Figure 130 – Metalast HF-EPA, 5052-H32.....	78
Figure 131 – SurTec 650, 6061-T6.....	79
Figure 132 – SurTec 650, 7075-T73.....	79
Figure 133 – SurTec 650, 2024-T3.....	80
Figure 134 – SurTec 650, 5052-H32.....	80
Figure 135 – SurTec 650C, 6061-T6.....	81
Figure 136 – SurTec 650C, 7075-T73.....	81
Figure 137 – SurTec 650C, 2024-T3.....	82
Figure 138 – SurTec 650C, 5052-H32.....	82
Figure 139 - PATTI JR Pull Test Results; Primer (MIL-PRF-23377) - PPG CA7233.....	84
Figure 140 - PATTI JR Pull Test Results; Primer (MIL-PRF-85582) - Deft 44-GN-07A.....	85
Figure 141 – Alodine T 5900 RTU; 6061-T6 (Left), 5052-H32 (Right).....	86
Figure 142 – Iridite NCP; 6061-T6 (Left), 5052-H32 (Right).....	87
Figure 143 – Metalast HF; 6061-T6 (Left), 5052-H32 (Right).....	88
Figure 144 – Metalast HF-EPA; 6061-T6 (Left), 5052-H32 (Right).....	89
Figure 145 – SurTec 650; 6061-T6 (Left), 5052-H32 (Right).....	90
Figure 146 – SurTec 650C; 6061-T6 (Left), 5052-H32 (Right).....	91
Figure 147 – Alodine T 5900 RTU; 6061-T6 (Left), 5052-H32 (Right).....	92
Figure 148 – Iridite NCP; 6061-T6 (Left), 5052-H32 (Right).....	93
Figure 149 – Metalast HF; 6061-T6 (Left), 5052-H32 (Right).....	94
Figure 150 – Metalast HF-EPA; 6061-T6 (Left), 5052-H32 (Right).....	95
Figure 151 – SurTec 650; 6061-T6 (Left), 5052-H32 (Right).....	96
Figure 152 – SurTec 650C; 6061-T6 (Left), 5052-H32 (Right).....	97
Figure 153 - ASTM D 3359, Test Method B, Figure 1 Classification of Adhesion Test Results	99
Figure 154 – Cross-Cut Tape Test Results; Primer (MIL-PRF-23377) - PPG CA7233.....	100
Figure 155 – Cross-Cut Tape Test Results; Primer (MIL-PRF-85582) - Deft 44-GN-07A.....	101
Figure 156 – Alodine T 5900 RTU; 6061-T6 (Top), 5052-H32 (Bottom).....	102
Figure 157 – Iridite NCP; 6061-T6 (Top), 5052-H32 (Bottom).....	103
Figure 158 – Metalast HF; 6061-T6 (Top), 5052-H32 (Bottom).....	104
Figure 159 – Metalast HF-EPA; 6061-T6 (Top), 5052-H32 (Bottom).....	105
Figure 160 – SurTec 650; 6061-T6 (Top), 5052-H32 (Bottom).....	106
Figure 161 – SurTec 650C; 6061-T6 (Top), 5052-H32 (Bottom).....	107
Figure 162 – Alodine T 5900 RTU; 6061-T6 (Top), 5052-H32 (Bottom).....	108

Figure 163 – Iridite NCP; 6061-T6 (Top), 5052-H32 (Bottom).....	109
Figure 164 – Metalast HF; 6061-T6 (Top), 5052-H32 (Bottom)	110
Figure 165 – Metalast HF-EPA; 6061-T6 (Top), 5052-H32 (Bottom)	111
Figure 166 – SurTec 650; 6061-T6 (Top), 5052-H32 (Bottom).....	112
Figure 167 – SurTec 650C; 6061-T6 (Top), 5052-H32 (Bottom).....	113
Figure 168 – Wet Tape Adhesion Test Panel	115
Figure 169 - Wet Tape Adhesion Test Results, 24 Hour; Primer (MIL-PRF-23377) - PPG CA7233.....	116
Figure 170 - Wet Tape Adhesion Test Results, 24 Hour; Test Results; Primer (MIL-PRF-85582) - Deft 44-GN-07A.....	117
Figure 171 – Alodine T 5900 RTU; 6061-T6 (Left), 5052-H32 (Right).....	118
Figure 172 – Iridite NCP - ; 6061-T6 (Left), 5052-H32 (Right)	118
Figure 173 – Metalast HF; 6061-T6 (Left), 5052-H32 (Right)	119
Figure 174 – Metalast HF-EPA; 6061-T6 (Left), 5052-H32 (Right)	119
Figure 175 – SurTec 650; 6061-T6 (Left), 5052-H32 (Right).....	120
Figure 176 – SurTec 650C; 6061-T6 (Left), 5052-H32 (Right).....	120
Figure 177 – Alodine T 5900 RTU; 6061-T6 (Left), 5052-H32 (Right).....	121
Figure 178 – Iridite NCP; 6061-T6 (Left), 5052-H32 (Right).....	121
Figure 179 – Metalast HF; 6061-T6 (Left), 5052-H32 (Right)	122
Figure 180 – Metalast HF-EPA; 6061-T6 (Left), 5052-H32 (Right)	122
Figure 181 - SurTec 650; 6061-T6 (Left), 5052-H32 (Right)	123
Figure 182 - SurTec 650C; 6061-T6 (Left), 5052-H32 (Right).....	123
Figure 183 - Wet Tape Adhesion Test Results, 96 Hour @ 120°F; Primer (MIL-PRF-23377) - PPG CA7233.....	124
Figure 184 - Wet Tape Adhesion Test Results, 96 Hour @ 120°F; Primer (MIL-PRF-85582) - Deft 44-GN-07A	125
Figure 185 – Alodine T 5900 RTU; 6061-T6 (Left), 5052-H32 (Right).....	126
Figure 186 – Iridite NCP; 6061-T6 (Left), 5052-H32 (Right).....	127
Figure 187 – Metalast HF; 6061-T6 (Left), 5052-H32 (Right)	128
Figure 188 – Metalast HF-EPA; 6061-T6 (Left), 5052-H32 (Right)	129
Figure 189 – SurTec 650; 6061-T6 (Left), 5052-H32 (Right).....	130
Figure 190 – SurTec 650C; 6061-T6 (Left), 5052-H32 (Right).....	131
Figure 191 – Alodine T 5900 RTU; 6061-T6 (Left), 5052-H32 (Right).....	132
Figure 192 – Iridite NCP; 6061-T6 (Left), 5052-H32 (Right).....	133
Figure 193 – Metalast HF; 6061-T6 (Left), 5052-H32 (Right)	134
Figure 194 – Metalast HF-EPA; 6061-T6 (Left), 5052-H32 (Right)	135
Figure 195 – SurTec 650; 6061-T6 (Left), 5052-H32 (Right).....	136
Figure 196 – SurTec 650C; 6061-T6 (Left), 5052-H32 (Right).....	137
Figure 197 - Electro-Tech Systems, Model 803B Probe	138
Figure 198 – Surface Resistance Data, Pre ASTM B 117 Testing	139
Figure 199 - Surface Resistance Data, Pre ASTM B 117 Testing.....	140
Figure 200 - Areas for measurements of electrical resistance on treated panels, MIL-DTL-81706B.....	142
Figure 201 – Contact Electrical Resistance Readings, Pre ASTM B 117	143

Figure 202 – Combined Corrosion Test Results..... 146
Figure 203 – Combined Adhesion Test Results; Pretreatments with PPG CA7233 primer..... 148
Figure 204 - Combined Adhesion Test Results; Pretreatments with Deft 44-GN-07A primer.. 149

1 Introduction

1.1 Background

Regardless of the corrosivity of the environment, all metals require periodic maintenance activity to guard against the insidious effects of corrosion and thus ensure that alloys meet or exceed design or performance life. The standard practice for protecting metallic substrates is the application of a coating system. Applied coating systems work via a variety of methods (barrier, galvanic, and/or inhibitor) and adhere to the substrate through a combination of chemical and physical bonds. For years hexavalent chromium has been a widely used element within applied coating systems because of its self healing and corrosion resistant properties. Occupational Safety and Health Administration (OSHA) studies have concluded that hexavalent chromium (hex chrome) is carcinogenic and poses significant risk to human health. On May 5, 2011 amendments to the Defense Federal Acquisition Regulation Supplement (DFARS) were issued in the Federal Register. Subpart 223.73 prohibits contracts from requiring hexavalent chromium in deliverables unless certain exceptions apply. These exceptions include authorization from a general or flag officer and members of the Senior Executive Service from a Program Executive Office, and unmodified legacy systems. Otherwise, Subpart 252.223-7008 provides the contract clause prohibiting contractors from using or delivering hexavalent chromium in a concentration greater than 0.1 percent by weight for all new contracts and to be included down to subcontractors for supplies, maintenance and repair services, and construction materials. National Aeronautics and Space Administration (NASA), Department of Defense (DoD), and industry stakeholders continue to search for alternatives to hex chrome in coatings applications that meet their performance requirements in corrosion protection, cost, operability, and health and safety, while typically specifying that performance must be equal to or greater than existing systems.

1.2 Objective

The overall objective of the Hexavalent Chrome Free Coatings for Electronics Applications project is to evaluate and test pretreatments not containing hexavalent chrome in avionics and electronics housing applications. This objective will be accomplished by testing strong performing coating systems from prior NASA and DoD testing or new coating systems as determined by the stakeholders.

2 Materials

2.1 Alloys

The following alloys have been selected because of their relatively common use in avionics and electronics housing systems and/or their ability to exhibit similar performance to other materials of interest. Table 1 lists the alloys on which coatings were applied and the entities given credit for procurement. All panels were procured mill finished without mill markings. Mill finish is as supplied from the mill (raw material manufacturer); is not polished and will most likely have a dull matte appearance.

Table 1 - Alloys Procured

Alloy	Size	Procuring Entity
6061-T6 Aluminum	3" X 10" X .032"	Rockwell Collins
7075-T73 Aluminum	3" X 10" X .032"	Lockheed Martin & Raytheon
2024-T3 Aluminum	3" X 10" X .032"	Lockheed Martin
5052-H32 Aluminum	3" X 10" X .032"	Harris Corp

2.2 Panel Preparation

The panel preparation procedure was developed as part of the NASA TEERM Hexavalent Chrome Alternatives for Aerospace Project. Stakeholders participating in the Hexavalent Chrome Free Coatings for Electronics Applications Project agreed to use the following procedure:

1. Solvent Hand Cleaning
 - a. Ethanol {200 proof}.
2. Mild Alkaline Aqueous Degreaser (Non-Silicate)
 - a. Chemetall-Oakite NST – (5% by volume @ 49° - 54°C for 4 minutes.)
3. DI water rinse to water break-free. Preceding degreasing steps will be repeated until water break-free is achieved.
4. Deoxidize Bath (Oakite LNC)
 - a. Oakite LNC (10% by volume @ ambient temperature for 3 - 4 minutes.)
5. Rinse thoroughly using clean (5 megaohm or better) DI ambient temperature water.
6. Take panels directly to pretreatment bath

2.3 Pretreatments

Table 2 lists the pretreatments that were tested under the Hexavalent Chrome Free Coatings for Electronics Applications project.

Table 2 - Pretreatment Procurement

Pretreatment	Approved per MIL DTL 81706	Manufacturer
Alodine 1600	Type I Class 1A,3 Form I Method C	Henkel
Metalast HFEP A	Type II Class 1A Form I Method A,B,C	Metalast
Metalast HF	Type II Class 1A,3 Form I Method A,B,C	Metalast
SurTec 650 – chromitAL TCP	Type II Class 1A,3 Form I Method A,B,C	SurTec
SurTec 650 C	Type II Class 1A,3 Form I Method A,B,C	SurTec
Alodine T 5900 RTU	Type II Class 1A,3 Form III Method A,B,C	Henkel
Iridite NCP	Type II Class 3 Form I Method A,B,C	MacDermid

3 Pretreatment Testing

MIL-DTL-81706 is the specification to which pretreatments are qualified. Class 1A refers to the classification of pretreatments used for maximum corrosion protection while Class 3 refers to the classification of pretreatments with low electrical resistivity. The technical stakeholders agreed that this project be focused specifically on Class 3 coatings. The performance requirements and related tests are listed in Table 3. These tests were agreed upon by the stakeholders that participated in Hexavalent Chrome Free Coatings for Electronics Applications Project.

All testing was conducted at the NASA Kennedy Space Center (KSC) Corrosion Technology Laboratory and Beachside Corrosion Laboratory.

Table 3 – Pretreatment Testing

Test	Test Method	Evaluation Criteria	Performing Entity
Salt Spray Resistance	ASTM B 117	No evidence of corrosion when compared to unexposed control panels using the naked eye	NASA KSC
Cyclic Corrosion	ASTM G 85, Annex 5	No evidence of corrosion when compared to unexposed control panels using the naked eye	NASA KSC
18-Month Marine Environment	ASTM D 1014	No evidence of corrosion when compared to unexposed control panels using the naked eye	NASA KSC
PATTI JR Pull Test	ASTM D 4541		NASA KSC
Cross-Cut Tape Test	ASTM D 3359	ASTM D 3359, Method B, Figure 1, Classification of Adhesion Test Results	NASA KSC
Wet Tape Paint Adhesion	FED STD 141, Method 6301.3	ASTM D 3359, Method A	NASA KSC
Surface Resistance	ASTM D 257	N/A	NASA KSC
Contact Electrical Resistance	MIL-DTL-81706	Not greater than 5,000 microhms psi as applied and 10,000 microhms psi after salt spray exposure	NASA KSC

3.1 Salt Spray Resistance

This test is used to rapidly evaluate the performance of a coating or coating system and how well it prevents corrosion. Salt Spray Resistance is a requirement of MIL-DTL-81706B.

3.1.1 Test Procedure

Test panels were subjected to a 5 percent NaCl salt spray, pH-adjusted to a range of 6.5 – 7.2, in accordance with ASTM B 117 (Standard Practice for Operating a Salt Spray (Fog) Apparatus).

There were sixteen (16) replicates per substrate / per coating system. One specimen from each substrate and coating system pairing was stored and used as an unexposed control. Five specimens from each substrate and coating system pairing were used for contact electrical resistance (MIL-DTL-81706B) and serve as the “before exposure” reading. Another five specimens underwent salt spray resistance then contact electrical resistance (MIL-DTL- 81706B) and serve as the “after exposure” reading. The last five were used for surface resistance testing (ASTM D 257), then underwent salt spray resistance, and then reevaluated for surface resistance (ASTM D 257).

3.1.2 Evaluation Procedure

For this effort, the following criteria were used when evaluating the test panels; MIL-DTL-81706B, section 3.5.1;”the specimens shall show no evidence of corrosion when compared to unexposed control panels using the naked eye. Areas within 0.25 inch (6.35 millimeters [mm]) from the edges of the panel, the identification markings, and the panel holding points during processing or salt spray exposure shall not be evaluated. Differences in color between the test panels and the control panels shall not be cause for rejection.” Should panels survive 168 hours and pass the surface resistance test, and test chambers are available, testing will continue until failure, and be evaluated at additional 168 hour intervals. Panels will be evaluated using the following standards.

3.1.3 Test Results – ASTM B 117, 168 hours

Test results following 168 hours of salt spray exposure are provided in Figure 1 through Figure 7 below.

During test panel inspection, it was observed that the control, Alodine 1600, did not perform as expected. Following 168 hours of salt spray exposure, all of the test panels with Alodine 1600 were deemed failed. This unexpected result brings into question the compatibility of Alodine 1600 and the panel preparation procedure selected for this project.

Inspection of the hexavalent chrome free pretreatments revealed a clear trend with respect to pretreatment performance by alloy. Pretreatments on alloys known for their resistance to corrosion (6061-T6 and 5052-H32) showed no evidence of corrosion when compared to unexposed control panels after 168 hours of salt spray exposure. Pretreatments on alloys that are known to have less inherent resistance to corrosion, mostly due to having a higher copper content (2024-T3 and 7075-T73) were determined failed after 168 hours of salt spray exposure. Such a strong delineation of the data across alloy type, regardless of hexavalent chrome free

pretreatment, was not expected. This unexpected result once again brings into question the panel preparation procedure selected for this project.

Pretreatment	Alloy	Unique Panel #	Batch #	Family	@ 168 Hours
Alodine 1600	6061-T6	1006	B7	b	Fail
		1007	B6	b	Fail
		1008	B6	b	Fail
		1009	B6	b	Fail
		1010	B1	b	Fail
	7075-T73	1051	B7	b	Fail
		1052	B7	b	Fail
		1053	B4	b	Fail
		1054	B4	b	Fail
		1055	B2	b	Fail
	2024-T3	1089	B1	b	Fail
		1090	B3	b	Fail
		1091	B5	b	Fail
		1092	B3	b	Fail
		1093	B3	b	Fail
	5052-H32	1128	B7	b	Fail
		1129	B6	b	Fail
		1130	B2	b	Fail
1131		B5	b	Fail	
1132		B2	b	Fail	

Figure 1 – ASTM B 117 Results @ 168 Hours; Alodine 1600

Pretreatment	Alloy	Unique Panel #	Batch #	Family	@ 168 Hours
Alodine T 5900 RTU	6061-T6	2006	B7	b	Pass
		2007	B6	b	Pass
		2008	B6	b	Pass
		2009	B6	b	Pass
		2010	B1	b	Pass
	7075-T73	2051	B7	b	Fail
		2052	B7	b	Fail
		2053	B4	b	Fail
		2054	B4	b	Fail
		2055	B2	b	Fail
	2024-T3	2089	B1	b	Fail
		2090	B3	b	Fail
		2091	B5	b	Fail
		2092	B3	b	Fail
		2093	B3	b	Fail
	5052-H32	2128	B7	b	Pass
		2129	B6	b	Pass
		2130	B2	b	Pass
		2131	B5	b	Pass
		2132	B2	b	Pass

Figure 2 - ASTM B 117 Results @ 168 Hours; Alodine T 5900 RTU

Pretreatment	Alloy	Unique Panel #	Batch #	Family	@ 168 Hours
Iridite NCP	6061-T6	3006	B7	b	Pass
		3007	B6	b	Pass
		3008	B6	b	Pass
		3009	B6	b	Pass
		3010	B1	b	Pass
	7075-T73	3051	B7	b	Fail
		3052	B7	b	Fail
		3053	B4	b	Fail
		3054	B4	b	Fail
		3055	B2	b	Fail
	2024-T3	3089	B1	b	Fail
		3090	B3	b	Fail
		3091	B5	b	Fail
		3092	B3	b	Fail
		3093	B3	b	Fail
	5052-H32	3128	B7	b	Pass
		3129	B6	b	Pass
		3130	B2	b	Pass
		3131	B5	b	Pass
		3132	B2	b	Pass

Figure 3 - ASTM B 117 Results @ 168 Hours; Iridite NCP

Pretreatment	Alloy	Unique Panel #	Batch #	Family	@ 168 Hours
Metalast HF	6061-T6	4006	B7	b	Pass
		4007	B6	b	Pass
		4008	B6	b	Pass
		4009	B6	b	Pass
		4010	B1	b	Pass
	7075-T73	4051	B7	b	Fail
		4052	B7	b	Fail
		4053	B4	b	Fail
		4054	B4	b	Fail
		4055	B2	b	Fail
	2024-T3	4089	B1	b	Fail
		4090	B3	b	Fail
		4091	B5	b	Fail
		4092	B3	b	Fail
	5052-H32	4093	B3	b	Fail
		4128	B7	b	Pass
		4129	B6	b	Pass
		4130	B2	b	Pass
		4131	B5	b	Pass
			4132	B2	b

Figure 4 - ASTM B 117 Results @ 168 Hours; Metalast HF

Pretreatment	Alloy	Unique Panel #	Batch #	Family	@ 168 Hours
Metalast HF-EPA	6061-T6	5006	B7	b	Pass
		5007	B6	b	Pass
		5008	B6	b	Pass
		5009	B6	b	Pass
		5010	B1	b	Pass
	7075-T73	5051	B7	b	Fail
		5052	B7	b	Fail
		5053	B4	b	Fail
		5054	B4	b	Fail
		5055	B2	b	Fail
	2024-T3	5089	B1	b	Fail
		5090	B3	b	Fail
		5091	B5	b	Fail
		5092	B3	b	Fail
	5052-H32	5093	B3	b	Fail
		5128	B7	b	Pass
		5129	B6	b	Pass
		5130	B2	b	Pass
		5131	B5	b	Pass
			5132	B2	b

Figure 5 - ASTM B 117 Results @ 168 Hours; Metalast HF-EPA

Pretreatment	Alloy	Unique Panel #	Batch #	Family	@ 168 Hours
SurTec 650	6061-T6	6006	B7	b	Pass
		6007	B6	b	Pass
		6008	B6	b	Pass
		6009	B6	b	Pass
		6010	B1	b	Pass
	7075-T73	6051	B7	b	Fail
		6052	B7	b	Fail
		6053	B4	b	Fail
		6054	B4	b	Fail
		6055	B2	b	Fail
	2024-T3	6089	B1	b	Fail
		6090	B3	b	Fail
		6091	B5	b	Fail
		6092	B3	b	Fail
	5052-H32	6093	B3	b	Fail
		6128	B7	b	Pass
		6129	B6	b	Pass
		6130	B2	b	Pass
		6131	B5	b	Pass
			6132	B2	b

Figure 6 - ASTM B 117 Results @ 168 Hours; SurTec 650

Pretreatment	Alloy	Unique Panel #	Batch #	Family	@ 168 Hours
SurTec 650C	6061-T6	7006	B7	b	Pass
		7007	B6	b	Pass
		7008	B6	b	Pass
		7009	B6	b	Pass
		7010	B1	b	Pass
	7075-T73	7051	B7	b	Fail
		7052	B7	b	Fail
		7053	B4	b	Fail
		7054	B4	b	Fail
		7055	B2	b	Fail
	2024-T3	7089	B1	b	Fail
		7090	B3	b	Fail
		7091	B5	b	Fail
		7092	B3	b	Fail
	5052-H32	7093	B3	b	Fail
		7128	B7	b	Pass
		7129	B6	b	Pass
		7130	B2	b	Pass
		7131	B5	b	Pass
			7132	B2	b

Figure 7 - ASTM B 117 Results @ 168 Hours; SurTec 650C

3.1.4 Test Panel Pictures

3.1.4.1 Alodine 1600



Figure 8 – Alodine 1600, 1006 - 1010

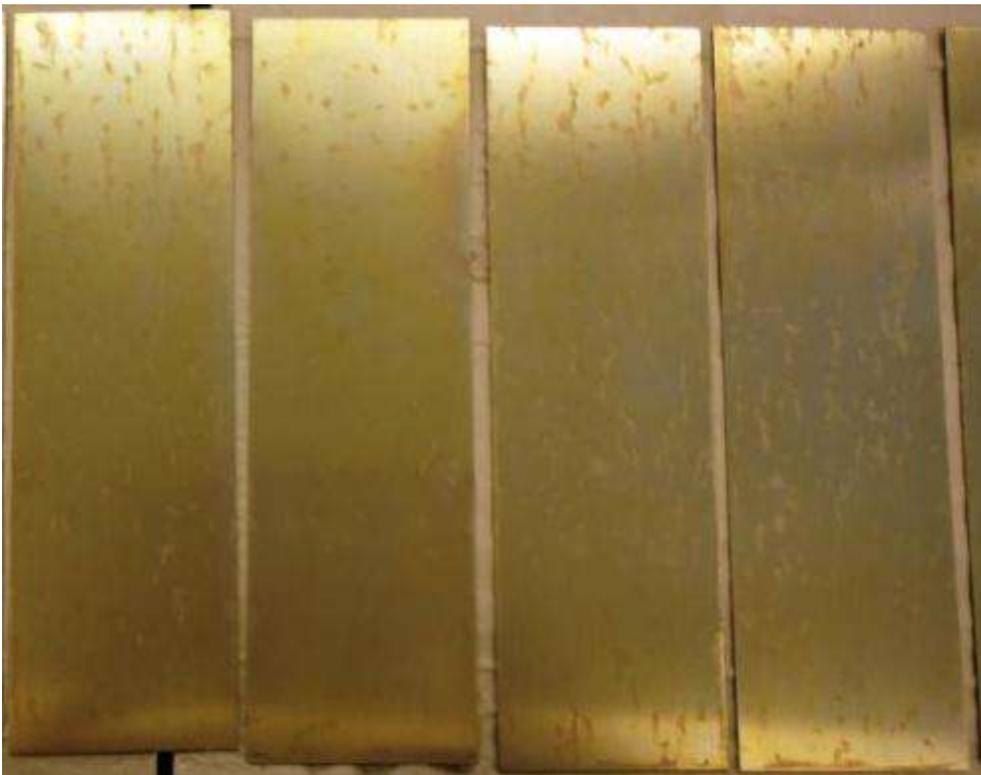


Figure 9 – Alodine 1600, 1051 – 1054



Figure 10 - Alodine 1600, 1090 – 1093

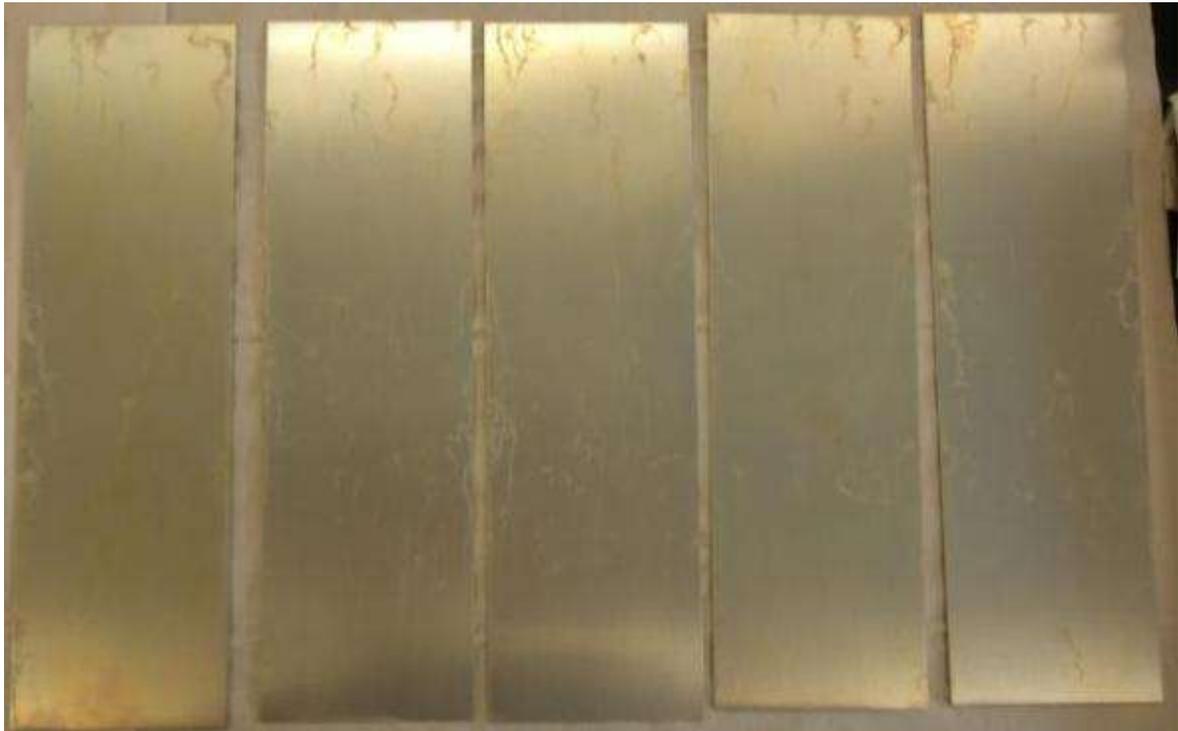


Figure 11 - Alodine 1600, 1128 – 1132

3.1.4.2 Alodine T 5900 RTU



Figure 12 – Alodine T 5900 RTU, 2006 – 2009



Figure 13 - Alodine T 5900 RTU, 2051 – 2055



Figure 14 - Alodine T 5900 RTU, 2089 – 2093



Figure 15 - Alodine T 5900 RTU, 2128 – 2132

3.1.4.3 Iridite NCP



Figure 16 – Iridite NCP, 3006 – 3009



Figure 17 – Iridite NCP, 3051 – 3055



Figure 18 – Iridite NCP, 3089 – 3093



Figure 19 – Iridite NCP, 3129 – 3132

3.1.4.4 Metalast HF



Figure 20 – Metalast HF, 4006 – 4010

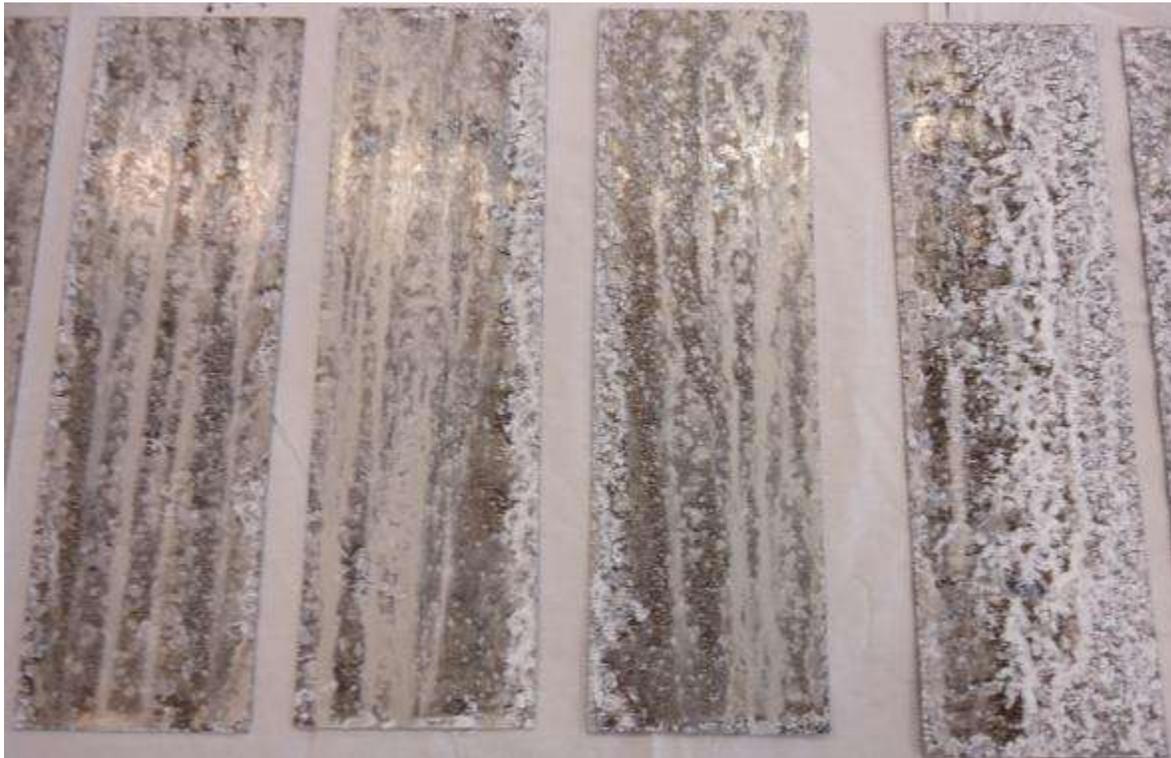


Figure 21 – Metalast HF, 4052 – 4055



Figure 22 – Metalast HF, 4089 – 4093



Figure 23 – Metalast HF, 4129 – 4132

3.1.4.5 Metalast HF-EPA



Figure 24 – Metalast HF-EPA, 5006 – 5009

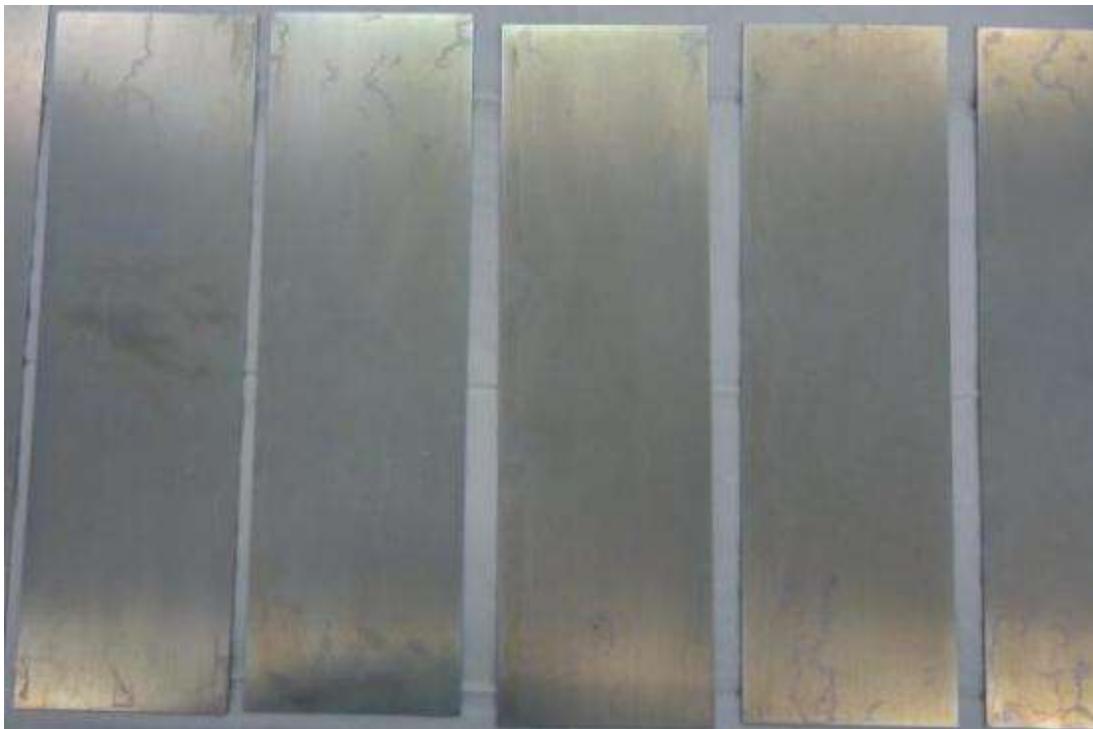


Figure 25 – Metalast HF-EPA, 5051 – 5055



Figure 26 – Metalast HF-EPA, 5089 – 5092



Figure 27 – Metalast HF-EPA, 5129 - 5132

3.1.4.6 SurTec 650



Figure 28 – SurTec 650, 6006 – 6009



Figure 29 – SurTec 650, 6052 – 6055



Figure 30 – SurTec 650, 6089 - 6092



Figure 31 – SurTec 650, 6128 - 6131

3.1.4.7 SurTec 650C



Figure 32 – SurTec 650C, 7006 – 7010

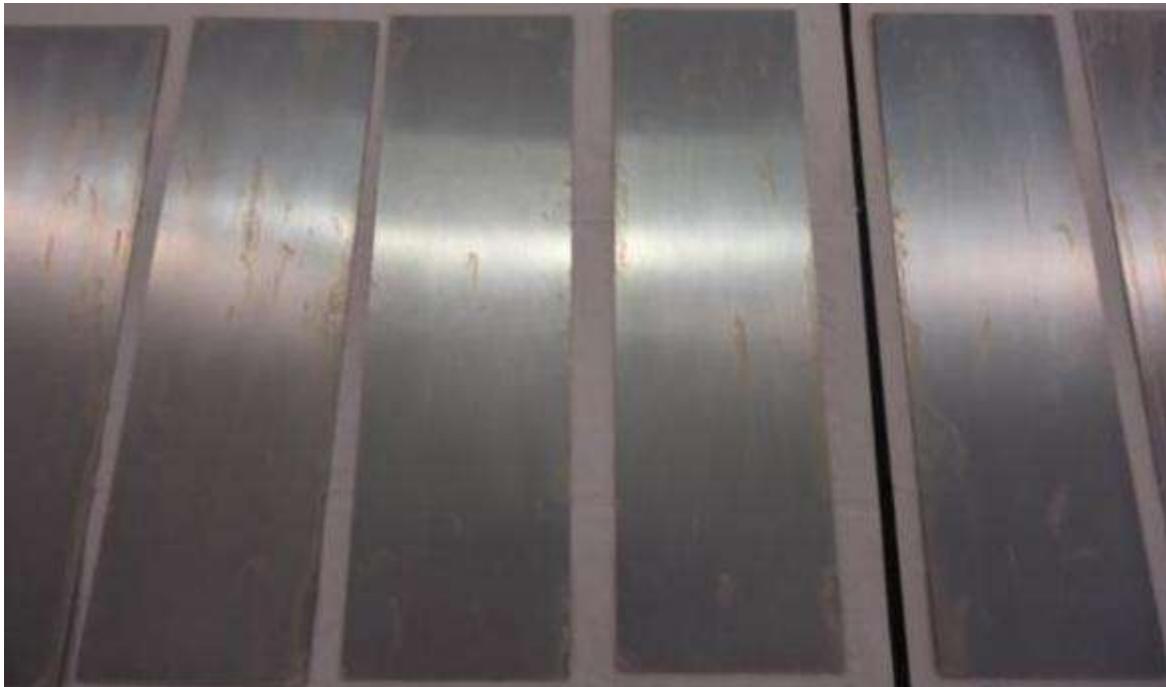


Figure 33 – SurTec 650C, 7051 – 7055



Figure 34 – SurTec 650C, 7089 – 7093

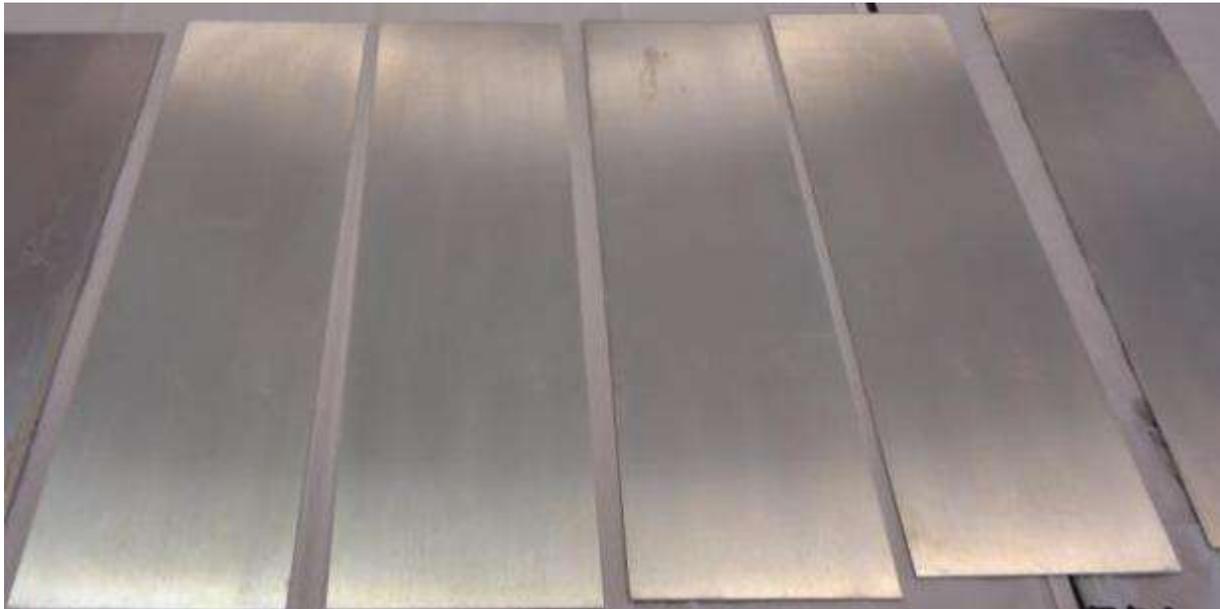


Figure 35 – SurTec 650C, 7128 - 7132

3.1.5 Test Results – ASTM B 117, to Failure

Test results following 168 hours of salt spray exposure are provided in Figure 36 through Figure 42 below. All five 6061-T6 test panels as well as 1 of 5 test panels for 7075-T73, 2024-T3, and 5052-H32 for all pretreatments were used for surface resistance readings. These panels were prepared at the same time as the other test panels, but were not tested at the same time. Test panels not used for surface resistance measurements were inspected at 168 hour intervals. Test panels that were considered failed were removed from the test chamber prior to continuing the test.

Alodine 1600 did not perform as expected on 7075-T73, 2024-T3 and 5052-H32 test panels. Curiously, Alodine 1600 did perform well on 6061-T6 test panels, a polar result to the ASTM B 117 salt spray results reported in section 3.1.3. Following 168 hours of salt spray exposure, all of the 7075-T73, 2024-T3 test panels with Alodine 1600 were considered failed. For 5052-H32 test panels, nearly all of the test panels failed, 4 of 5, the one exception was the test panel that was used for surface resistance measurements. These results bring into question the compatibility of Alodine 1600 and the panel preparation procedure selected for this project.

The hexavalent chrome free pretreatments on 6061-T6 test panels performed well, with not more than one test panel deemed failed after 168 hours of ASTM B 117 salt spray exposure, for a majority of the pretreatments. Two pretreatments had more than one test panel deemed failed following 168 hours of ASTM B 117 salt spray exposure; Alodine T 5900 RTU and Metalast HF. Pretreatments on 5052-H32 test panels showed no evidence of corrosion when compared to unexposed control panels after 1008 hours of salt spray exposure for a majority of test panels. Noted exception, Metalast HF only had two test panels make the 1008 hour mark. It should also be noted that for Metalast HF the only test panel that did not pass 336 hours of exposure was the test panel used for resistance measurements. Iridite NCP and SurTec 650C has similar anomalies, with the only test panels to fail at 168 hours of exposure was the test panels used for ASTM D 257 measurements. Hexavalent chrome free pretreatments on alloys that are known to have less inherent resistance to corrosion, mostly due to having a higher copper content (2024-T3 and 7075-T73) were determined failed after 168 hours of salt spray exposure.

For Figure 51, Figure 55, Figure 59, and Figure 67 there are markings associated with the 803B probe used to obtain surface resistance measurements. This is important to note because the purpose of running this test was to determine if it could be utilized as a non-destructive test method for surface resistivity of test panels to allow for readings throughout testing lifecycles. The presence of visible markings due to the 803B probe show that some level of damage is occurring to the coated surface.

Pretreatment	Alloy	Panel #	Batch #	Family	168 Hrs	336 Hrs	504 Hrs	672 Hrs	840 Hrs	1008 Hrs
Alodine 1600	6061-T6	1011*	B1	c	Fail	N/A	N/A	N/A	N/A	N/A
		1012*	B7	c	Pass	N/A	N/A	N/A	N/A	N/A
		1013*	B6	c	Pass	N/A	N/A	N/A	N/A	N/A
		1014*	B4	c	Pass	N/A	N/A	N/A	N/A	N/A
		1015*	B1	c	Pass	N/A	N/A	N/A	N/A	N/A
	7075-T73	1056	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		1057	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
		1058	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
		1059	B1	c	Fail	N/A	N/A	N/A	N/A	N/A
		1060*	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
	2024-T3	1094	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		1095	B4	c	Fail	N/A	N/A	N/A	N/A	N/A
		1096	B7	c	Fail	N/A	N/A	N/A	N/A	N/A
		1097	B2	c	Fail	N/A	N/A	N/A	N/A	N/A
		1098*	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
	5052-H32	1133	B2	c	Fail	N/A	N/A	N/A	N/A	N/A
		1134	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
1135		B5	c	Fail	N/A	N/A	N/A	N/A	N/A	
1136		B7	c	Fail	N/A	N/A	N/A	N/A	N/A	
1137*		B2	c	Pass	N/A	N/A	N/A	N/A	N/A	

*Note - Test panels were used for ASTM D 257 analysis before and after ASTM B 117 exposure. Test panels were not tested at the same time as the others listed in the table. Testing was stopped after 168 hours.

Figure 36 - ASTM B 117 Results, To Failure; Alodine 1600

Pretreatment	Alloy	Panel #	Batch #	Family	168 Hrs	336 Hrs	504 Hrs	672 Hrs	840 Hrs	1008 Hrs
Alodine T 5900 TRU	6061-T6	2011*	B1	c	Fail	N/A	N/A	N/A	N/A	N/A
		2012*	B7	c	Pass	N/A	N/A	N/A	N/A	N/A
		2013*	B6	c	Pass	N/A	N/A	N/A	N/A	N/A
		2014*	B4	c	Fail	N/A	N/A	N/A	N/A	N/A
		2015*	B1	c	Pass	N/A	N/A	N/A	N/A	N/A
	7075-T73	2056	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		2057	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
		2058	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
		2059	B1	c	Fail	N/A	N/A	N/A	N/A	N/A
		2060*	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
	2024-T3	2094	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		2095	B4	c	Fail	N/A	N/A	N/A	N/A	N/A
		2096	B7	c	Fail	N/A	N/A	N/A	N/A	N/A
		2097	B2	c	Fail	N/A	N/A	N/A	N/A	N/A
		2098*	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
	5052-H32	2133	B2	c	Pass	Pass	Pass	Pass	Pass	Pass
		2134	B5	c	Pass	Pass	Pass	Pass	Pass	Pass
2135		B5	c	Pass	Pass	Pass	Pass	Pass	Pass	
2136		B7	c	Pass	Pass	Pass	Pass	Pass	Pass	
2137*		B2	c	Pass	N/A	N/A	N/A	N/A	N/A	

*Note - Test panels were used for ASTM D 257 analysis before and after ASTM B 117 exposure. Test panels were not tested at the same time as the others listed in the table. Testing was stopped after 168 hours.

Figure 37 - ASTM B 117 Results, To Failure; Alodine T 5900 RTU

Pretreatment	Alloy	Panel #	Batch #	Family	168 Hrs	336 Hrs	504 Hrs	672 Hrs	840 Hrs	1008 Hrs
Iridite NCP	6061-T6	3011*	B1	c	Pass	N/A	N/A	N/A	N/A	N/A
		3012*	B7	c	Pass	N/A	N/A	N/A	N/A	N/A
		3013*	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		3014*	B4	c	Pass	N/A	N/A	N/A	N/A	N/A
		3015*	B1	c	Pass	N/A	N/A	N/A	N/A	N/A
	7075-T73	3056	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		3057	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
		3058	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
		3059	B1	c	Fail	N/A	N/A	N/A	N/A	N/A
		3060*	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
	2024-T3	3094	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		3095	B4	c	Fail	N/A	N/A	N/A	N/A	N/A
		3096	B7	c	Fail	N/A	N/A	N/A	N/A	N/A
		3097	B2	c	Fail	N/A	N/A	N/A	N/A	N/A
	5052-H32	3098*	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
		3133	B2	c	Pass	Pass	Pass	Pass	Pass	Pass
		3134	B5	c	Pass	Pass	Pass	Pass	Pass	Pass
		3135	B5	c	Pass	Pass	Pass	Pass	Pass	Pass
		3136	B7	c	Pass	Pass	Pass	Pass	Pass	Pass
	3137*	B2	c	Fail	N/A	N/A	N/A	N/A	N/A	

*Note - Test panels were used for ASTM D 257 analysis before and after ASTM B 117 exposure. Test panels were not tested at the same time as the others listed in the table. Testing was stopped after 168 hours.

Figure 38 - ASTM B 117 Results, To Failure; Iridite NCP

Pretreatment	Alloy	Panel #	Batch #	Family	168 Hrs	336 Hrs	504 Hrs	672 Hrs	840 Hrs	1008 Hrs
Metalast HF	6061-T6	4011*	B1	c	Fail	N/A	N/A	N/A	N/A	N/A
		4012*	B7	c	Fail	N/A	N/A	N/A	N/A	N/A
		4013*	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		4014*	B4	c	Fail	N/A	N/A	N/A	N/A	N/A
		4015*	B1	c	Pass	N/A	N/A	N/A	N/A	N/A
	7075-T73	4056	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		4057	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
		4058	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
		4059	B1	c	Fail	N/A	N/A	N/A	N/A	N/A
		4060*	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
	2024-T3	4094	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		4095	B4	c	Fail	N/A	N/A	N/A	N/A	N/A
		4096	B7	c	Fail	N/A	N/A	N/A	N/A	N/A
		4097	B2	c	Fail	N/A	N/A	N/A	N/A	N/A
	5052-H32	4098*	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
		4133	B2	c	Pass	Pass	Fail	N/A	N/A	N/A
		4134	B5	c	Pass	Pass	Pass	Fail	N/A	N/A
		4135	B5	c	Pass	Pass	Pass	Pass	Pass	Pass
		4136	B7	c	Pass	Pass	Pass	Pass	Pass	Pass
	4137*	B2	c	Fail	N/A	N/A	N/A	N/A	N/A	

*Note - Test panels were used for ASTM D 257 analysis before and after ASTM B 117 exposure. Test panels were not tested at the same time as the others listed in the table. Testing was stopped after 168 hours.

Figure 39 - ASTM B 117 Results, To Failure; Metalast HF

Pretreatment	Alloy	Panel #	Batch #	Family	168 Hrs	336 Hrs	504 Hrs	672 Hrs	840 Hrs	1008 Hrs
Metalast HF-EPA	6061-T6	5011*	B1	c	Pass	N/A	N/A	N/A	N/A	N/A
		5012*	B7	c	Fail	N/A	N/A	N/A	N/A	N/A
		5013*	B6	c	Pass	N/A	N/A	N/A	N/A	N/A
		5014*	B4	c	Pass	N/A	N/A	N/A	N/A	N/A
		5015*	B1	c	Pass	N/A	N/A	N/A	N/A	N/A
	7075-T73	5056	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		5057	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
		5058	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
		5059	B1	c	Fail	N/A	N/A	N/A	N/A	N/A
		5060*	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
	2024-T3	5094	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		5095	B4	c	Fail	N/A	N/A	N/A	N/A	N/A
		5096	B7	c	Fail	N/A	N/A	N/A	N/A	N/A
		5097	B2	c	Fail	N/A	N/A	N/A	N/A	N/A
		5098*	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
	5052-H32	5133	B2	c	Pass	Pass	Pass	Pass	Pass	Pass
		5134	B5	c	Pass	Pass	Pass	Pass	Pass	Pass
5135		B5	c	Pass	Pass	Pass	Pass	Pass	Pass	
5136		B7	c	Pass	Pass	Pass	Pass	Pass	Pass	
5137*		B2	c	Pass	N/A	N/A	N/A	N/A	N/A	

*Note - Test panels were used for ASTM D 257 analysis before and after ASTM B 117 exposure. Test panels were not tested at the same time as the others listed in the table. Testing was stopped after 168 hours.

Figure 40 - ASTM B 117 Results, To Failure; Metalast HF-EPA

Pretreatment	Alloy	Panel #	Batch #	Family	168 Hrs	336 Hrs	504 Hrs	672 Hrs	840 Hrs	1008 Hrs
SurTec 650	6061-T6	6011*	B1	c	Pass	N/A	N/A	N/A	N/A	N/A
		6012*	B7	c	Fail	N/A	N/A	N/A	N/A	N/A
		6013*	B6	c	Pass	N/A	N/A	N/A	N/A	N/A
		6014*	B4	c	Pass	N/A	N/A	N/A	N/A	N/A
		6015*	B1	c	Pass	N/A	N/A	N/A	N/A	N/A
	7075-T73	6056	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		6057	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
		6058	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
		6059	B1	c	Fail	N/A	N/A	N/A	N/A	N/A
		6060*	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
	2024-T3	6094	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		6095	B4	c	Fail	N/A	N/A	N/A	N/A	N/A
		6096	B7	c	Fail	N/A	N/A	N/A	N/A	N/A
		6097	B2	c	Fail	N/A	N/A	N/A	N/A	N/A
		6098*	B3	c	Pass	N/A	N/A	N/A	N/A	N/A
	5052-H32	6133	B2	c	Pass	Pass	Pass	Pass	Pass	Pass
		6134	B5	c	Pass	Pass	Pass	Pass	Pass	Pass
6135		B5	c	Pass	Pass	Pass	Pass	Pass	Pass	
6136		B7	c	Pass	Pass	Pass	Pass	Pass	Pass	
6137*		B2	c	Pass	N/A	N/A	N/A	N/A	N/A	

*Note - Test panels were used for ASTM D 257 analysis before and after ASTM B 117 exposure. Test panels were not tested at the same time as the others listed in the table. Testing was stopped after 168 hours.

Figure 41 - ASTM B 117 Results, To Failure; SurTec 650

Pretreatment	Alloy	Panel #	Batch #	Family	168 Hrs	336 Hrs	504 Hrs	672 Hrs	840 Hrs	1008 Hrs
SurTec 650C	6061-T6	7011*	B1	c	Pass	N/A	N/A	N/A	N/A	N/A
		7012*	B7	c	Pass	N/A	N/A	N/A	N/A	N/A
		7013*	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		7014*	B4	c	Pass	N/A	N/A	N/A	N/A	N/A
		7015*	B1	c	Pass	N/A	N/A	N/A	N/A	N/A
	7075-T73	7056	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		7057	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
		7058	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
		7059	B1	c	Fail	N/A	N/A	N/A	N/A	N/A
		7060*	B5	c	Fail	N/A	N/A	N/A	N/A	N/A
	2024-T3	7094	B6	c	Fail	N/A	N/A	N/A	N/A	N/A
		7095	B4	c	Fail	N/A	N/A	N/A	N/A	N/A
		7096	B7	c	Fail	N/A	N/A	N/A	N/A	N/A
		7097	B2	c	Fail	N/A	N/A	N/A	N/A	N/A
		7098*	B3	c	Fail	N/A	N/A	N/A	N/A	N/A
	5052-H32	7133	B2	c	Pass	Pass	Pass	Pass	Pass	Pass
		7134	B5	c	Pass	Pass	Pass	Pass	Pass	Pass
		7135	B5	c	Pass	Pass	Pass	Pass	Pass	Pass
		7136	B7	c	Pass	Pass	Pass	Pass	Pass	Pass
		7137*	B2	c	Fail	N/A	N/A	N/A	N/A	N/A

*Note - Test panels were used for ASTM D 257 analysis before and after ASTM B 117 exposure. Test panels were not tested at the same time as the others listed in the table. Testing was stopped after 168 hours.

Figure 42 - ASTM B 117 Results, To Failure; SurTec 650C

3.1.6 Test Panel Pictures

3.1.6.1 Alodine 1600



Figure 43 – Alodine 1600, 1011 - 1015

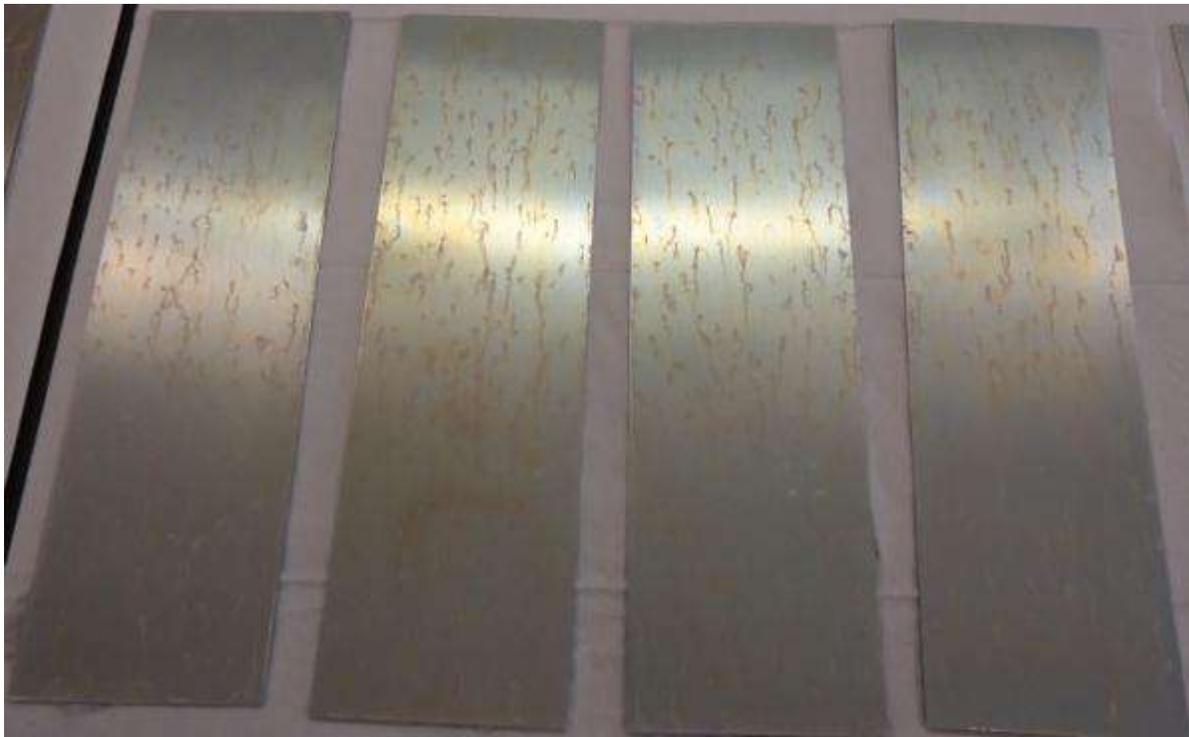


Figure 44 – Alodine 1600, 1056 – 1059



Figure 45 – Alodine 1600, 1094 – 1097



Figure 46 – Alodine 1600, 1133 - 1136

3.1.6.2 Alodine T 5900 RTU

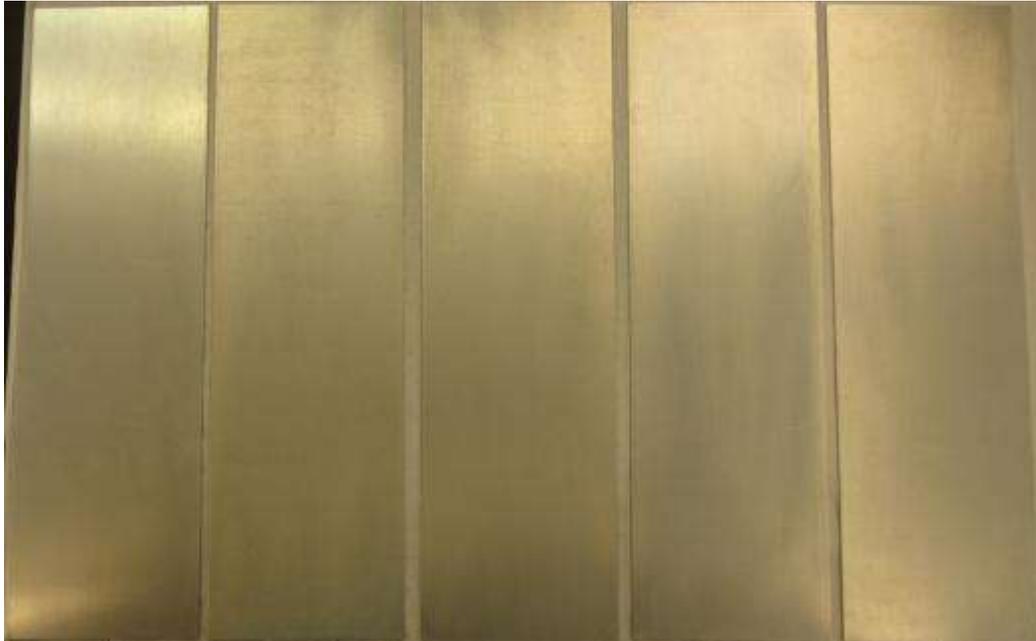


Figure 47 – Alodine T 5900 RTU, 2011 – 2015

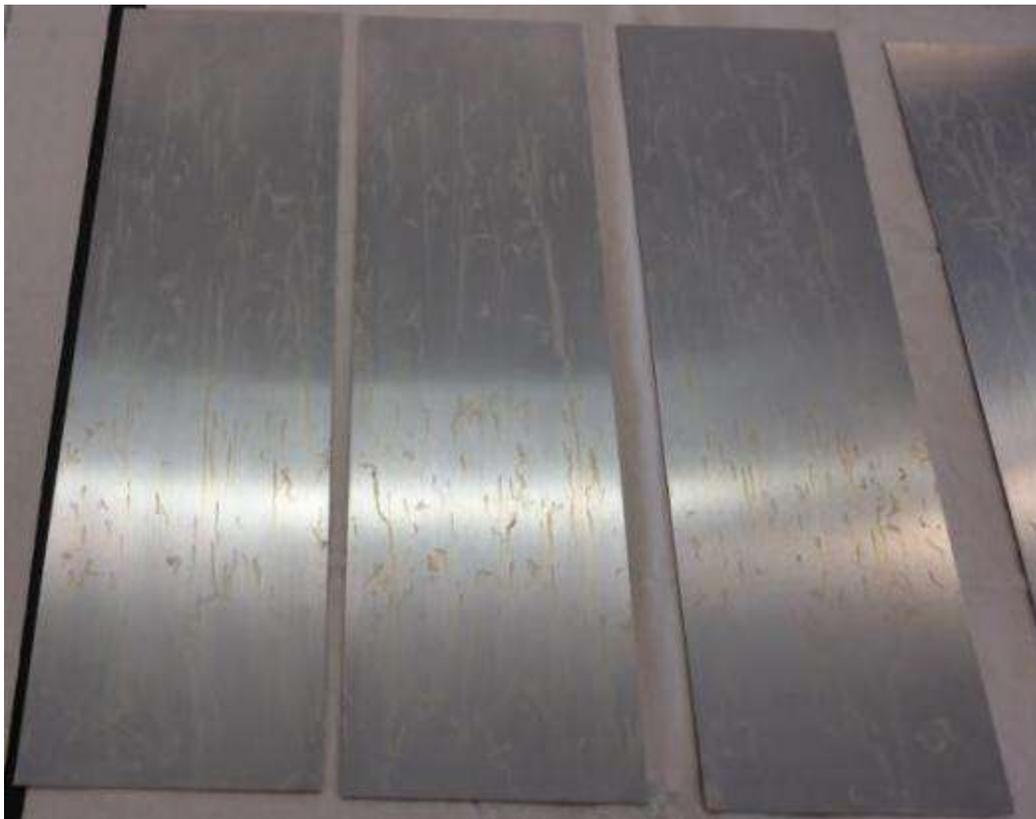


Figure 48 – Alodine T 5900 RTU, 2056 – 2058



Figure 49 - Alodine T 5900 RTU, 2094 – 2097



Figure 50 – Alodine T 5900 RTU, 2133 – 2136

3.1.6.3 Iridite NCP

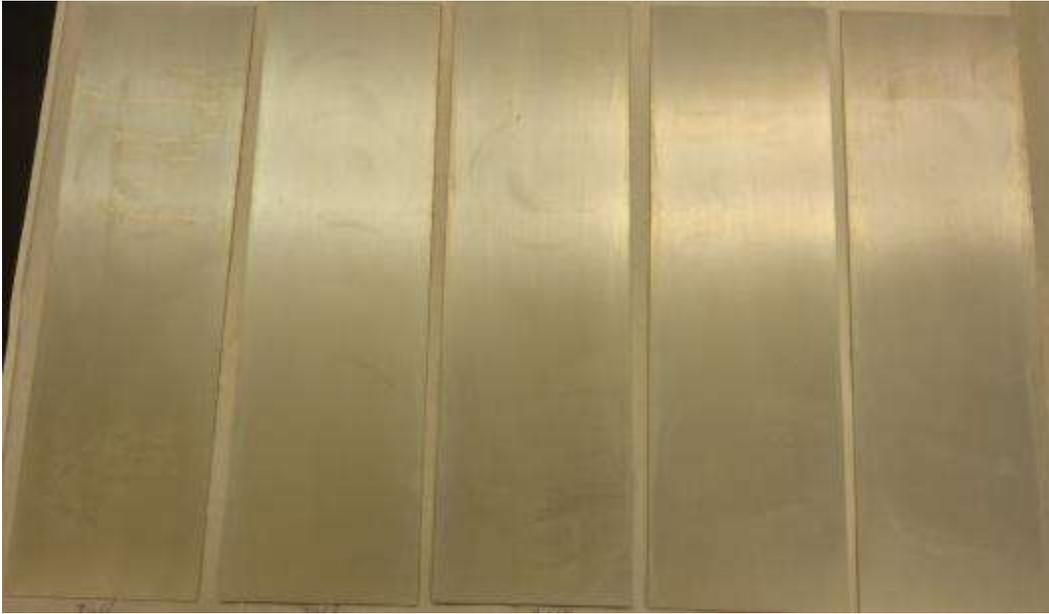


Figure 51 – Iridite NCP, 3011 – 3015



Figure 52 – Iridite NCP, 3056 – 3059



Figure 53 – Iridite NCP, 3094 – 3097



Figure 54 – Iridite NCP, 3133 – 3136

3.1.6.4 Metalast HF



Figure 55 – Metalast HF, 4011 – 4015



Figure 56 – Metalast HF, 4059 – 4057



Figure 57 – Metalast HF, 4094 – 4097



Figure 58 – Metalast HF, 4133 – 4136

3.1.6.5 Metalast HF-EPA



Figure 59 – Metalast HF-EPA, 5011 – 5015



Figure 60 – Metalast HF-EPA, 5056 – 5059



Figure 61 – Metalast HF-EPA, 5094 – 5097

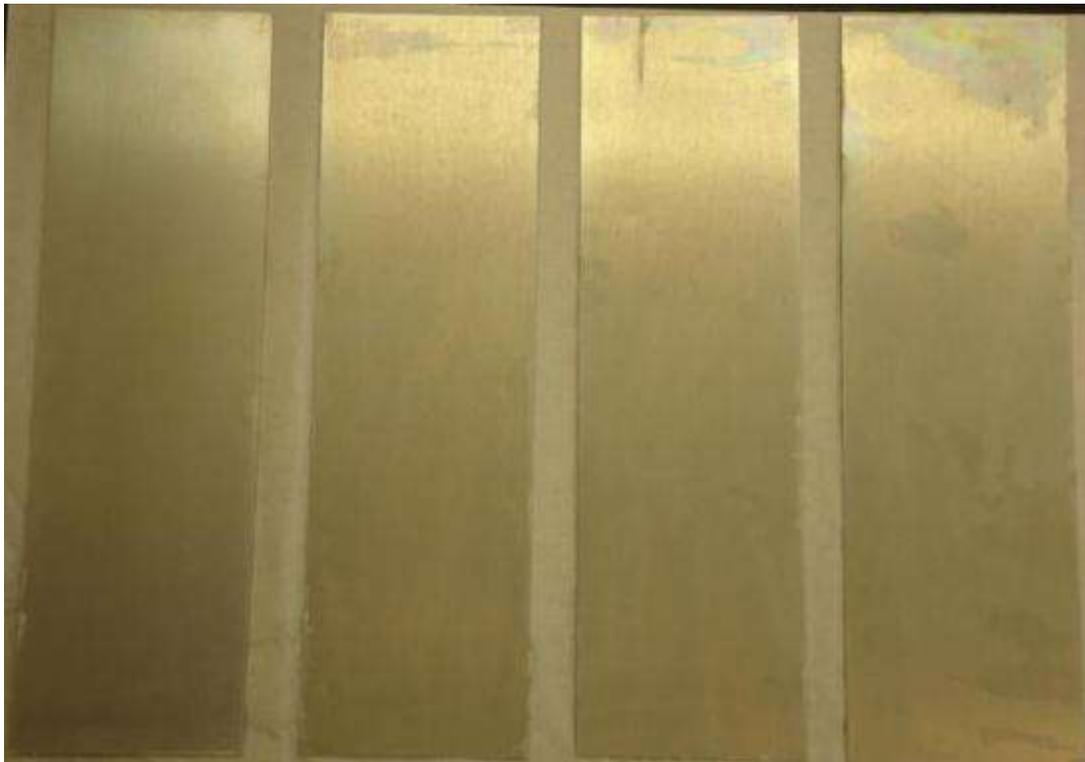


Figure 62 – Metalast HF-EPA, 5133 – 5136

3.1.6.6 SurTec 650

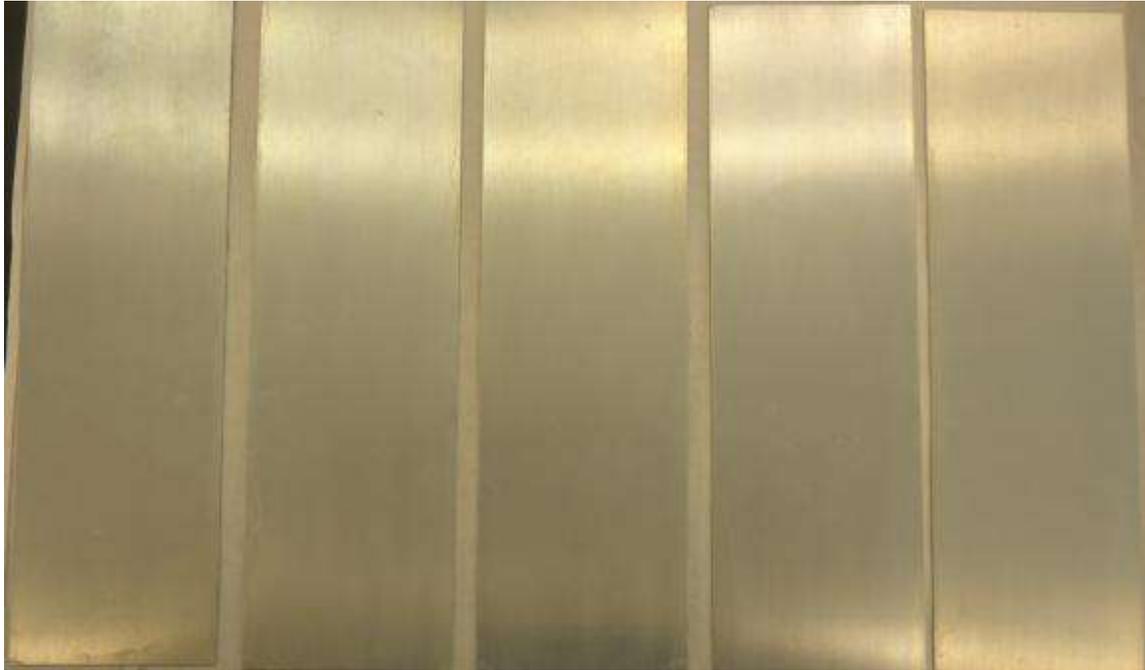


Figure 63 – SurTec 650, 6011 – 6015

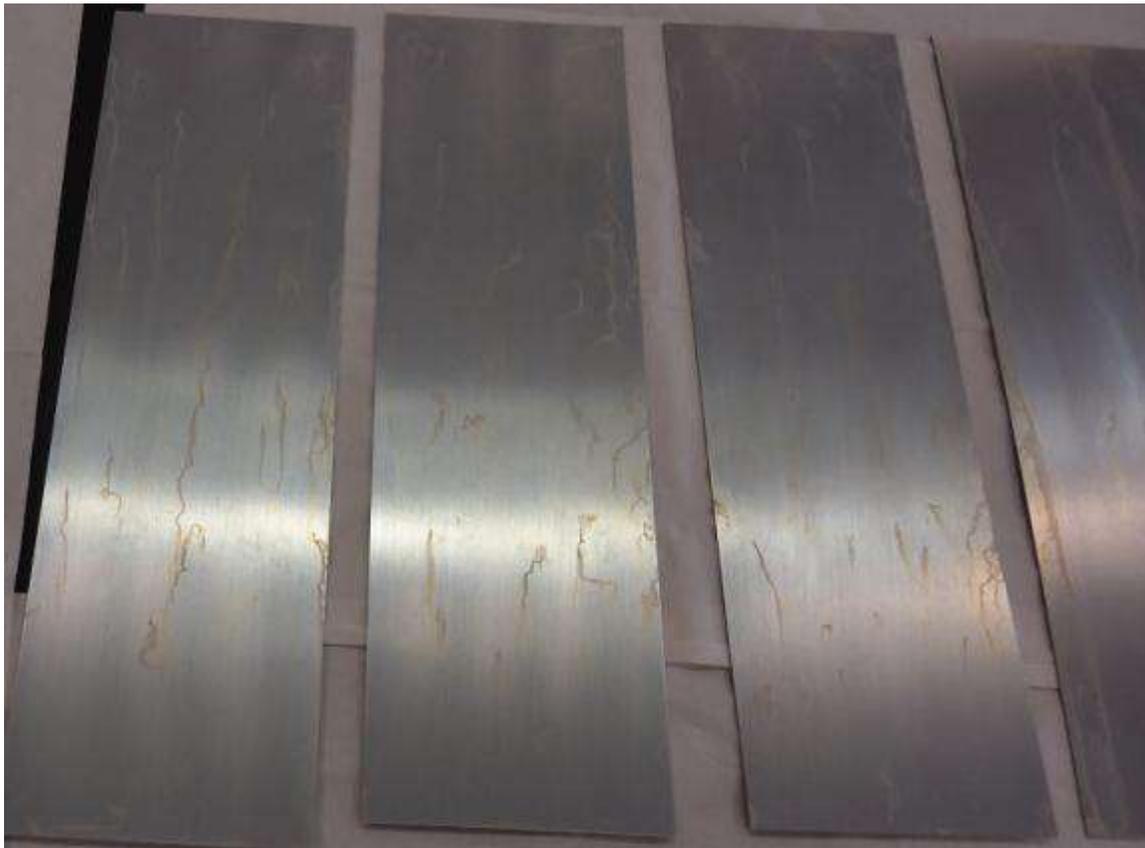


Figure 64 – SurTec 650, 6056 – 6058



Figure 65 – SurTec 650, 6094 – 6097

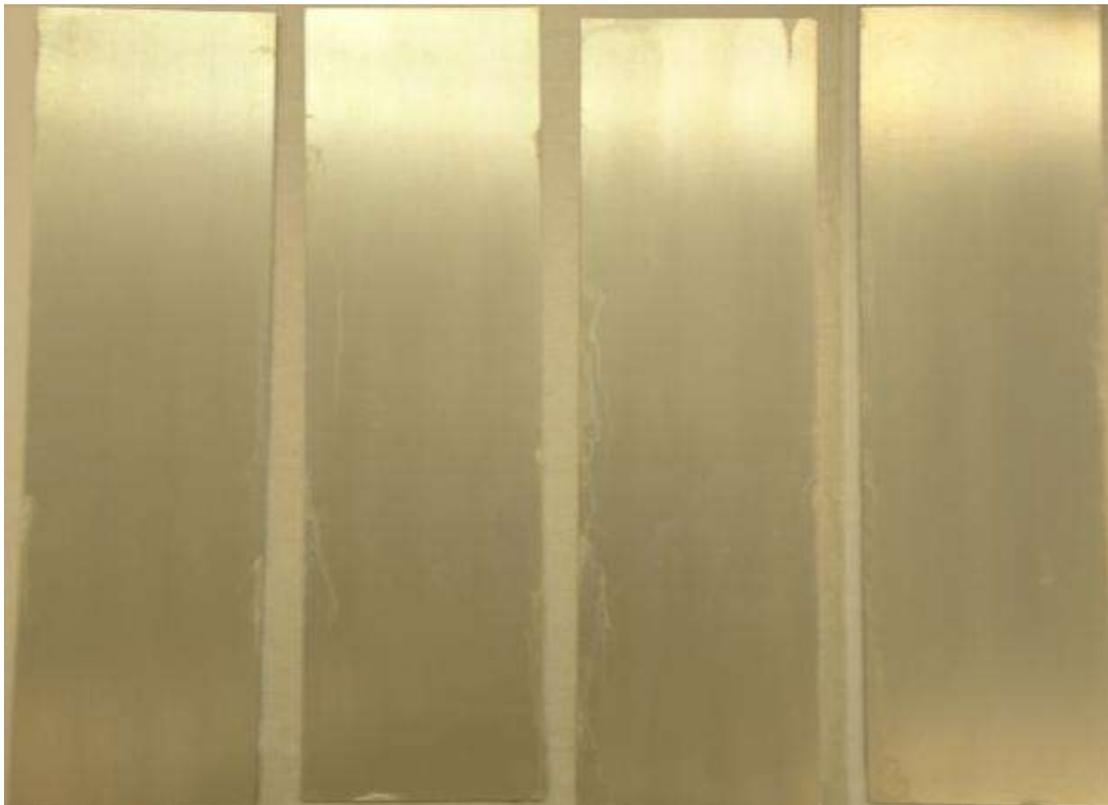


Figure 66 – SurTec 650, 6136 - 6133

3.1.6.7 SurTec 650C



Figure 67 – SurTec 650C, 7011 – 7015



Figure 68 – SurTec 650C, 7056 – 6059



Figure 69 – SurTec 650C, 7094 – 7097

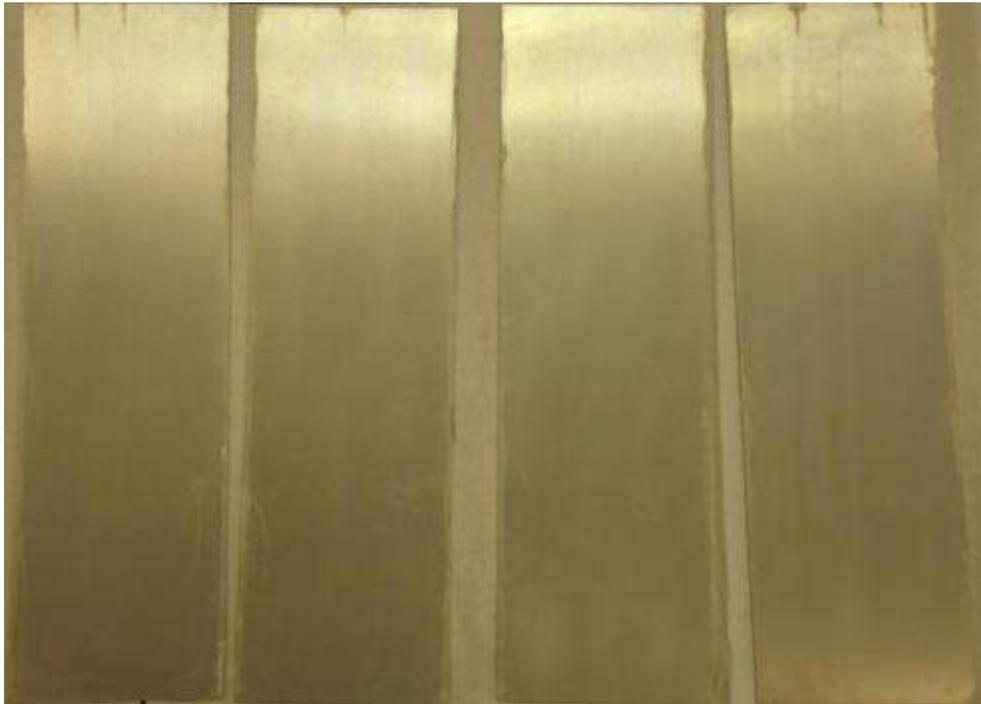


Figure 70 – SurTec 650C, 7136 - 7133

3.2 Cyclic Corrosion

This test evaluates the corrosion protection that coatings provide on metal samples in an accelerated corrosive environment. Cyclic corrosion testing is necessary to determine the effects of a marine environment on the coating system.

3.2.1 Test Procedure

Three (3) replicates per substrate / per coating underwent cyclic corrosion testing in accordance with ASTM G 85 (Modified Salt Spray (Fog) Testing), Annex 5 (dilute electrolyte cyclic fog dry test) for duration of 7 days (1 week {168 hours}). All of the samples were exposed to a salt fog solution consisting of 0.05% sodium chloride (NaCl) and 0.35% ammonium sulfate by weight for approximately one hour at ambient temperature (approximately 75°F), followed by approximately one hour of drying at approximately 95°F.

3.2.2 Evaluation Procedure

For this effort, the following criteria were used when evaluating the test panels; MIL-DTL-81706B, section 3.5.1;”the specimens shall show no evidence of corrosion when compared to unexposed control panels using the naked eye. Areas within 0.25 inch (6.35 millimeters [mm]) from the edges of the panel, the identification markings, and the panel holding points during processing or salt spray exposure shall not be evaluated. Differences in color between the test panels and the control panels shall not be cause for rejection.”

3.2.3 Test Results – ASTM G 85 Annex 5, 168 hours

Test results following 168 hours of cyclic corrosion testing are provided in Figure 71 through Figure 77 below.

Following 168 hours of cyclic corrosion testing, test panels with Alodine 1600 revealed a clear trend with respect to pretreatment performance by alloy. As mentioned in the ASTM B 117 test result sections, Alodine 1600 on alloys known for their resistance to corrosion (6061-T6 and 5052-H32) showed no evidence of corrosion when compared to unexposed control panels after 168 hours of cyclic corrosion testing. Alodine 1600 on alloys that are known to have less inherent resistance to corrosion, mostly due to having a higher copper content (2024-T3 and 7075-T73) were determined failed after 168 hours of salt spray exposure.

Inspection of the hexavalent chrome free pretreatments once again revealed a clear trend with respect to pretreatment performance by alloy. As mentioned in the ASTM B 117 test results sections, pretreatments on alloys known for their resistance to corrosion (6061-T6 and 5052-H32) showed no evidence of corrosion when compared to unexposed control panels after 168 hours of cyclic corrosion testing. There was one exception to the trend; Metalast HF did show signs of corrosion 6061-T6 and 5052-H32 alloys. Pretreatments on alloys that are known to have less inherent resistance to corrosion, mostly due to having a higher copper content (2024-T3 and 7075-T73) were determined failed after 168 hours of salt spray exposure.

Pretreatment	Alloy	Unique Panel #	Batch #	Family	Result @ 168 Hours
Alodine 1600	6061-T6	1017	B1	d	Pass
		1018	B3	d	Pass
		1019	B7	d	Pass
	7075-T73	1062	B3	d	Fail
		1063	B6	d	Fail
		1064	B4	d	Fail
	2024-T3	1100	B1	d	Fail
		1101	B6	d	Fail
		1102	B3	d	Fail
	5052-H32	1139	B2	d	Pass
		1140	B6	d	Pass
		1141	B7	d	Pass

Figure 71 - ASTM G 85, Annex 5 Results, 168 Hours; Alodine 1600

Pretreatment	Alloy	Unique Panel #	Batch #	Family	Result @ 168 Hours
Alodine T 5900 RTU	6061-T6	2017	B1	d	Pass
		2018	B3	d	Pass
		2019	B7	d	Pass
	7075-T73	2062	B3	d	Fail
		2063	B6	d	Fail
		2064	B4	d	Fail
	2024-T3	2100	B1	d	Fail
		2101	B6	d	Fail
		2102	B3	d	Fail
	5052-H32	2139	B2	d	Pass
		2140	B6	d	Pass
		2141	B7	d	Pass

Figure 72 - ASTM G 85, Annex 5 Results, 168 Hours; Alodine T 5900 RTU

Pretreatment	Alloy	Unique Panel #	Batch #	Family	Result @ 168 Hours
Iridite NCP	6061-T6	3017	B1	d	Pass
		3018	B3	d	Pass
		3019	B7	d	Pass
	7075-T73	3062	B3	d	Fail
		3063	B6	d	Fail
		3064	B4	d	Fail
	2024-T3	3100	B1	d	Fail
		3101	B6	d	Fail
		3102	B3	d	Fail
	5052-H32	3139	B2	d	Pass
		3140	B6	d	Pass
3141		B7	d	Pass	

Figure 73 - ASTM G 85, Annex 5 Results, 168 Hours; Iridite NCP

Pretreatment	Alloy	Unique Panel #	Batch #	Family	Result @ 168 Hours
Metalast HF	6061-T6	4017	B1	d	Fail
		4018	B3	d	Fail
		4019	B7	d	Fail
	7075-T73	4062	B3	d	Fail
		4063	B6	d	Fail
		4064	B4	d	Fail
	2024-T3	4100	B1	d	Fail
		4101	B6	d	Fail
		4102	B3	d	Fail
	5052-H32	4139	B2	d	Fail
		4140	B6	d	Fail
4141		B7	d	Fail	

Figure 74 - ASTM G 85, Annex 5 Results, 168 Hours; Metalast HF

Pretreatment	Alloy	Unique Panel #	Batch #	Family	Result @ 168 Hours
Metalast HF-EPA	6061-T6	5016	B1	d	Pass
		5018	B3	d	Pass
		5019	B7	d	Pass
	7075-T73	5062	B3	d	Fail
		5063	B6	d	Fail
		5064	B4	d	Fail
	2024-T3	5100	B1	d	Fail
		5101	B6	d	Fail
		5102	B3	d	Fail
	5052-H32	5139	B2	d	Pass
		5140	B6	d	Pass
5141		B7	d	Pass	

Figure 75 - ASTM G 85, Annex 5 Results, 168 Hours; Metalast HF-EPA

Pretreatment	Alloy	Unique Panel #	Batch #	Family	Result @ 168 Hours
SurTec 650	6061-T6	6017	B1	d	Pass
		6018	B3	d	Pass
		6019	B7	d	Pass
	7075-T73	6062	B3	d	Fail
		6063	B6	d	Fail
		6064	B4	d	Fail
	2024-T3	6100	B1	d	Fail
		6101	B6	d	Fail
		6102	B3	d	Fail
	5052-H32	6139	B2	d	Pass
		6140	B6	d	Pass
6141		B7	d	Pass	

Figure 76 - ASTM G 85, Annex 5 Results, 168 Hours; SurTec 650

Pretreatment	Alloy	Unique Panel #	Batch #	Family	Result @ 168 Hours
SurTec 650C	6061-T6	7017	B1	d	Pass
		7018	B3	d	Pass
		7019	B7	d	Pass
	7075-T73	7062	B3	d	Fail
		7063	B6	d	Fail
		7064	B4	d	Fail
	2024-T3	7100	B1	d	Fail
		7101	B6	d	Fail
		7102	B3	d	Fail
	5052-H32	7139	B2	d	Pass
		7140	B6	d	Pass
		7141	B7	d	Pass

Figure 77 - ASTM G 85, Annex 5 Results, 168 Hours; SurTec 650C

3.2.4 Test Panel Pictures

3.2.4.1 Alodine 1600



Figure 78 – Alodine 1600, 1017 – 1019



Figure 79 – Alodine 1600, 1062 – 1064



Figure 80 – Alodine 1600, 1100 – 1102

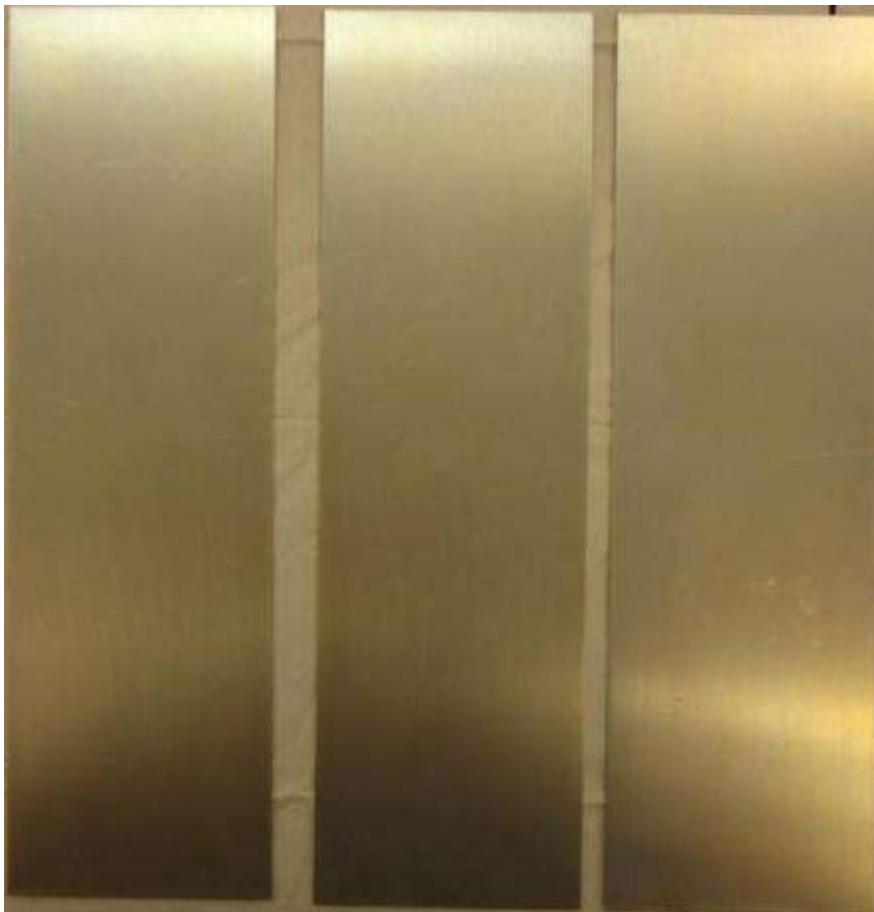


Figure 81 – Alodine 1600, 1139 – 1141

3.2.4.2 Alodine T 5900 RTU



Figure 82 – Alodine T 5900 RTU, 2017 – 2019

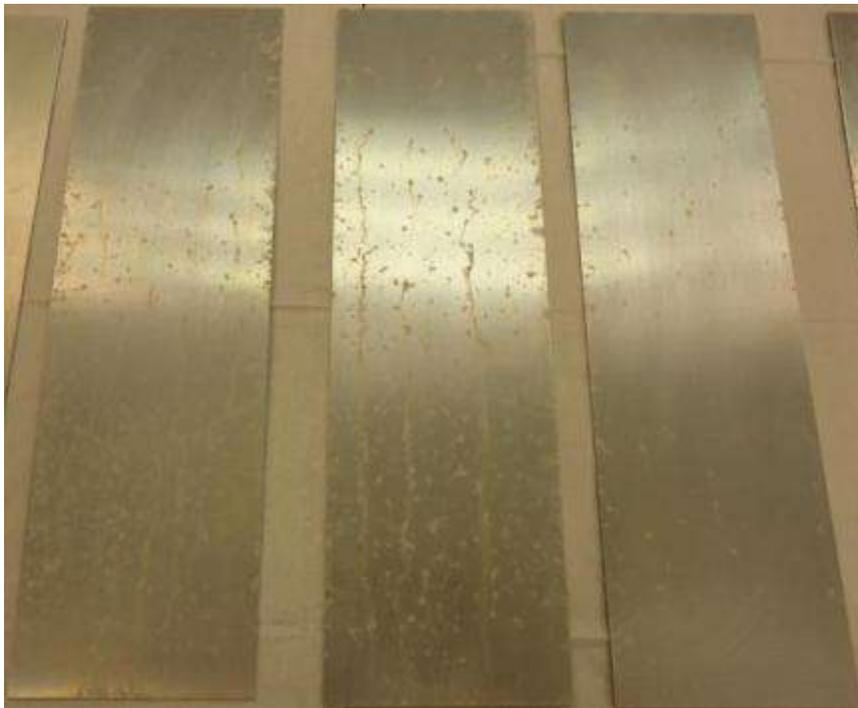


Figure 83 – Alodine T 5900 RTU, 2062 - 2064



Figure 84 – Alodine T 5900 RTU, 2100 – 2102

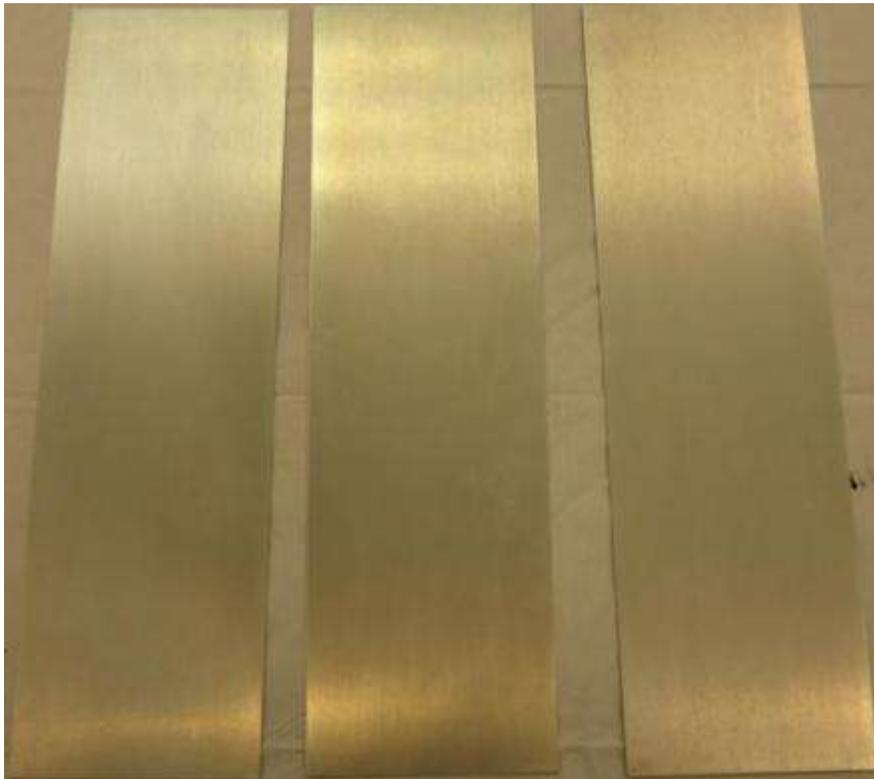


Figure 85 – Alodine T 5900 RTU, 2139 – 2142

3.2.4.3 Iridite NCP



Figure 86 – Iridite NCP, 3017 – 3019



Figure 87 – Iridite NCP, 3062 – 3064

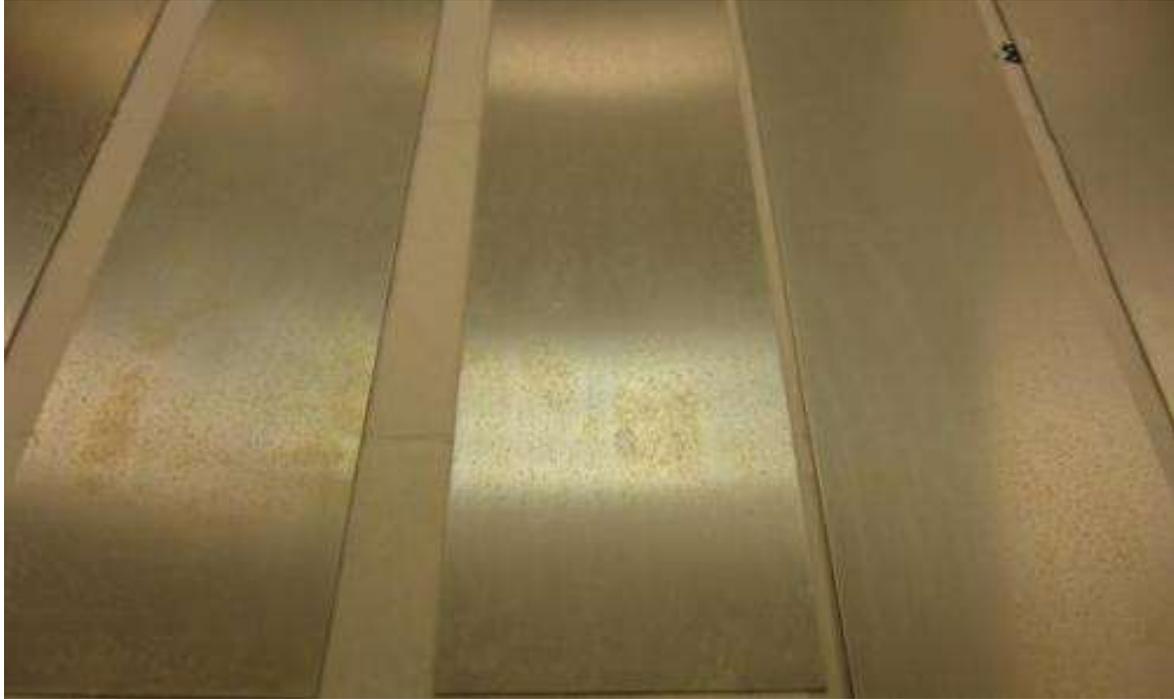


Figure 88 – Iridite NCP, 3100 – 3102



Figure 89 – Iridite NCP, 3139 – 3142

3.2.4.4 Metalast HF



Figure 90 – Metalast HF, 4017 – 4019



Figure 91 – Metalast HF, 4062 – 4064

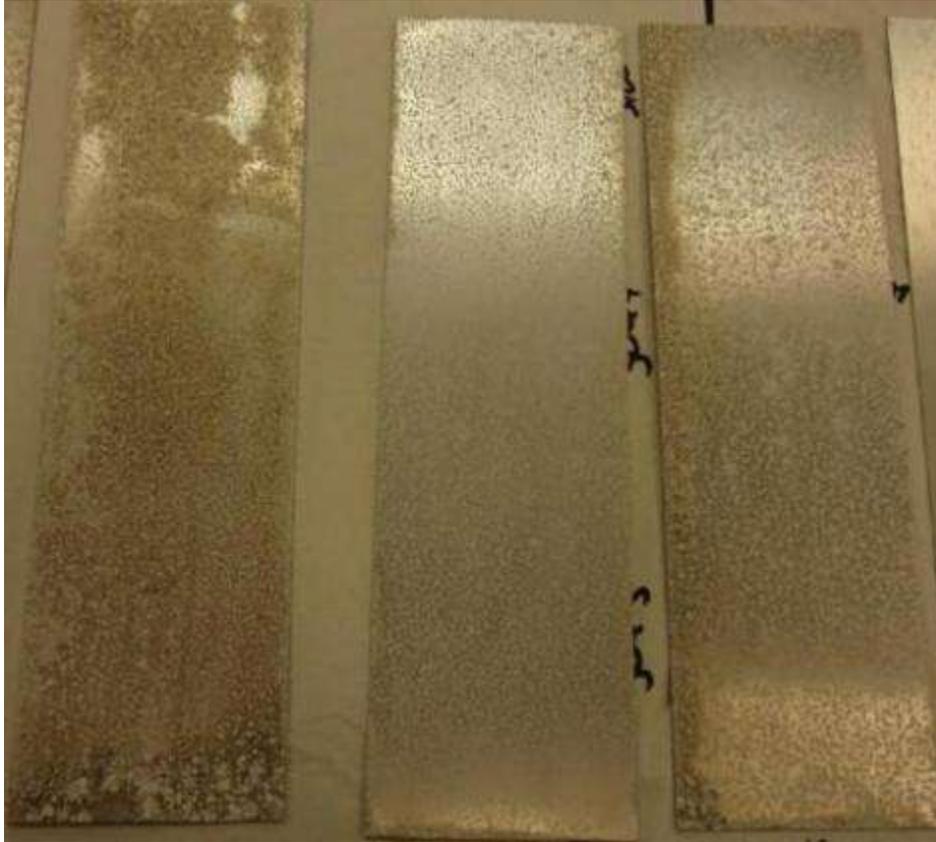


Figure 92 – Metalast HF, 4100 – 4102



Figure 93 – Metalast HF, 4139 – 4141

3.2.4.5 Metalast HF-EPA

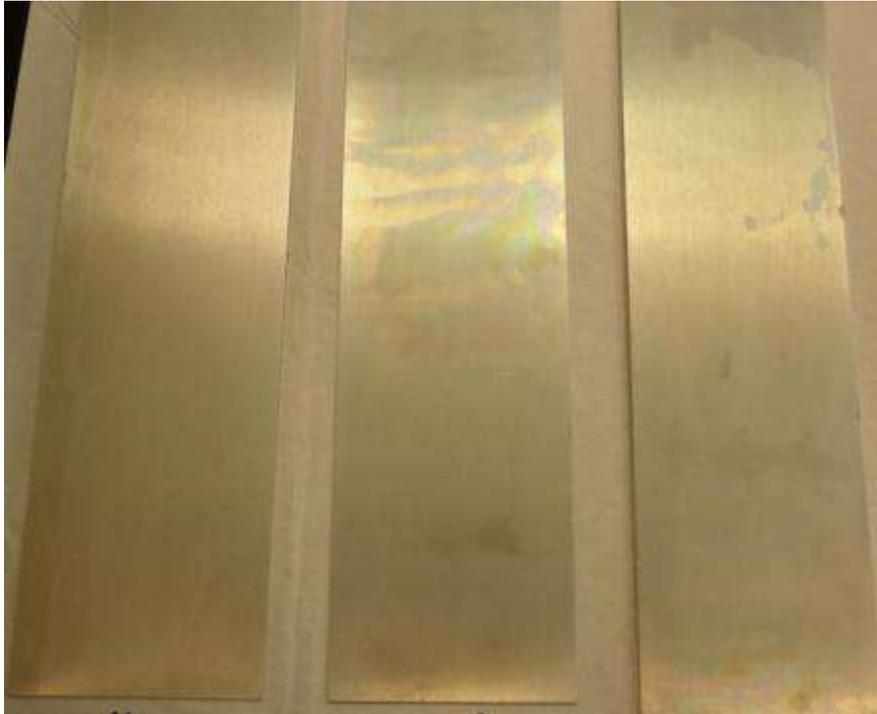


Figure 94 – Metalast HF-EPA, 5016, 5018 – 5019

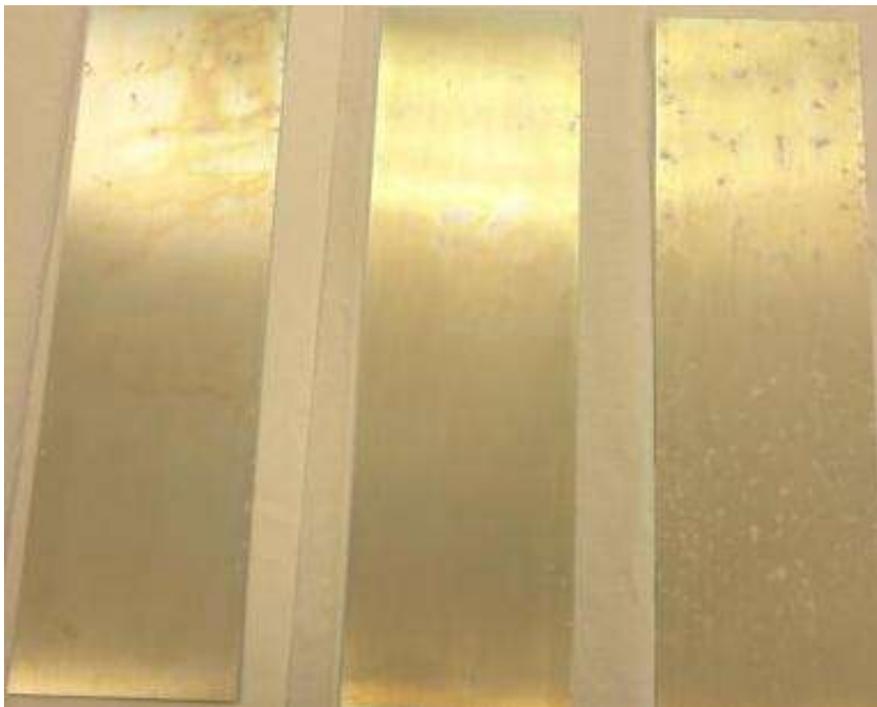


Figure 95 – Metalast HF-EPA, 5062 – 5064



Figure 96 – Metalast HF-EPA, 5100 - 5102



Figure 97 – Metalast HF-EPA, 5139 – 5141

3.2.4.6 SurTec 650



Figure 98 – SurTec 650, 6017 – 6019



Figure 99 – SurTec 650, 6062 – 6064



Figure 100 – SurTec 650, 6100 – 6102



Figure 101 – SurTec 650, 6139 – 6141

3.2.4.7 SurTec 650C

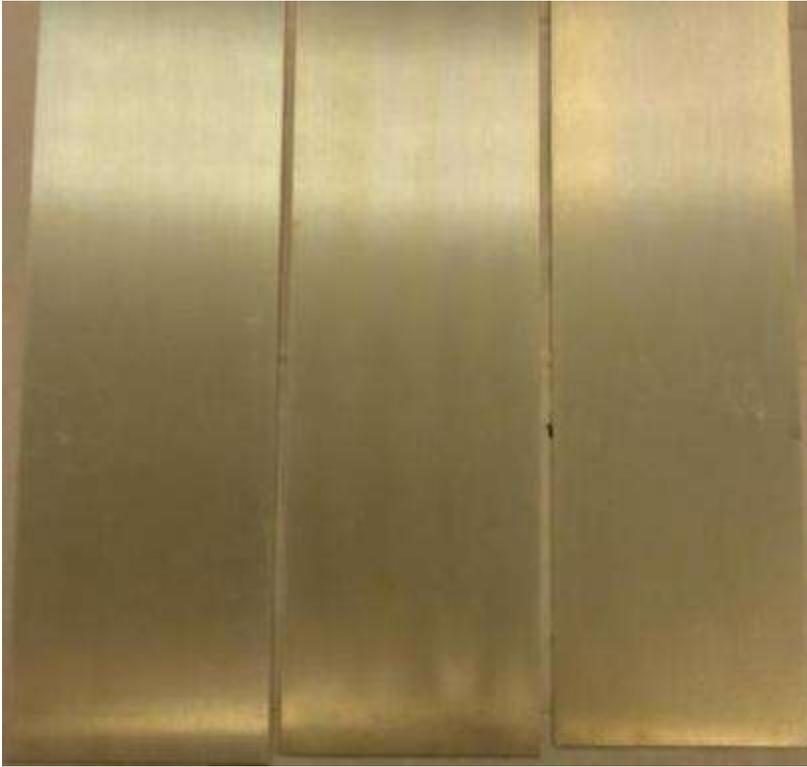


Figure 102 – SurTec 650C, 7017 – 7019

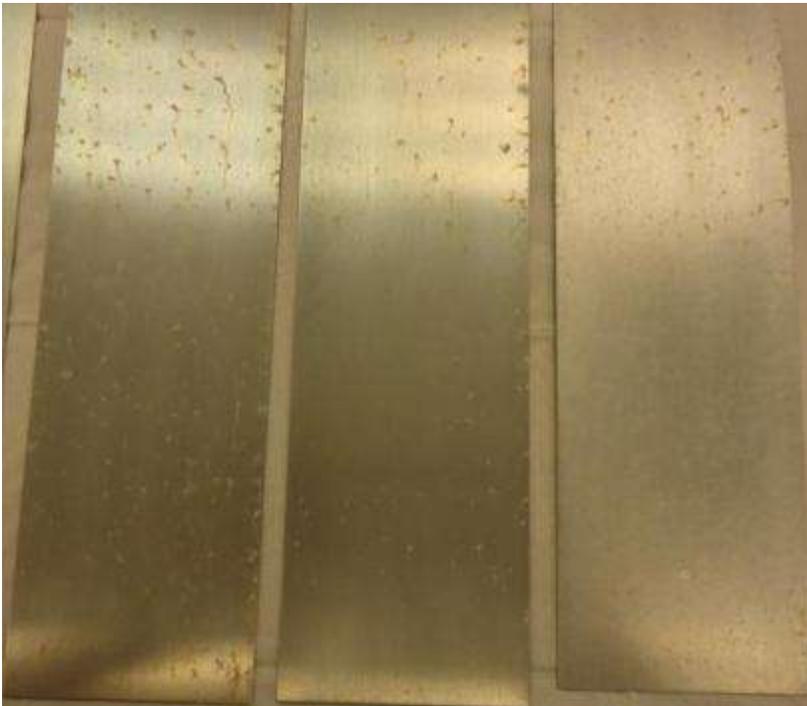


Figure 103 – SurTec 650C, 7062 – 7064



Figure 104 – SurTec 650C, 7100 – 7102



Figure 105 – SurTec 650C, 7139 – 7141

3.3 Marine Environment

This test evaluates the performance of the test and control coatings during an 18 month outdoor exposure in a marine environment. Accelerated testing is useful for comparing the performance of coatings under accelerated conditions however correlations to actual service performance has been difficult due to different corrosion mechanisms prevalent in the two situations. Therefore, outdoor exposure in the environment of performance is a critical test necessary to determine the effect actual weather patterns and real-world exposure has on the coatings of interest. Comparing data collected from atmospheric and accelerated testing will give insight into anticipated performance of a coating system before being field tested.

3.3.1 Test Procedure

Atmospheric exposure testing will follow ASTM D 1014 (Standard Practice for Conducting Exterior Exposure Tests of Paints and Coatings on Metal Substrates).

Three (3) replicates per substrate / per coating were installed at the KSC outdoor exposure facility, located at latitude 28.594°N, longitude -80.582°W, and approximately 100 feet (30 meters) from the high tide line. Testing followed KSC testing procedures for fasteners, exposure angle, and inspection intervals unless otherwise noted. Comparing data collected from atmospheric and accelerated testing will give insight into anticipated performance of a coating system before being field tested.

3.3.2 Evaluation Procedure

Test panels were evaluated and photographed weekly for five (5) weeks. After 5 weeks of exposure, the test panels were removed from the beach and evaluated as follows; MIL-DTL-81706B, section 3.5.1;”the specimens shall show no evidence of corrosion when compared to unexposed control panels using the naked eye. Areas within 0.25 inch (6.35 millimeters [mm]) from the edges of the panel, the identification markings, and the panel holding points during processing or salt spray exposure shall not be evaluated. Differences in color between the test panels and the control panels shall not be cause for rejection.”

3.3.3 Test Results – Beachside Corrosion, 5 Weeks

Following 5 weeks of atmospheric exposure, all test panels showed signs of pitting through the entire test panel regardless of pretreatment or alloy. Overall the pitting was fairly consistent across all test panels with numerous small pits throughout the test panels.

3.3.4 Test Panel Pictures – Beachside Corrosion Laboratory; Day 1



Figure 106 - Beachside Corrosion; Rack 1

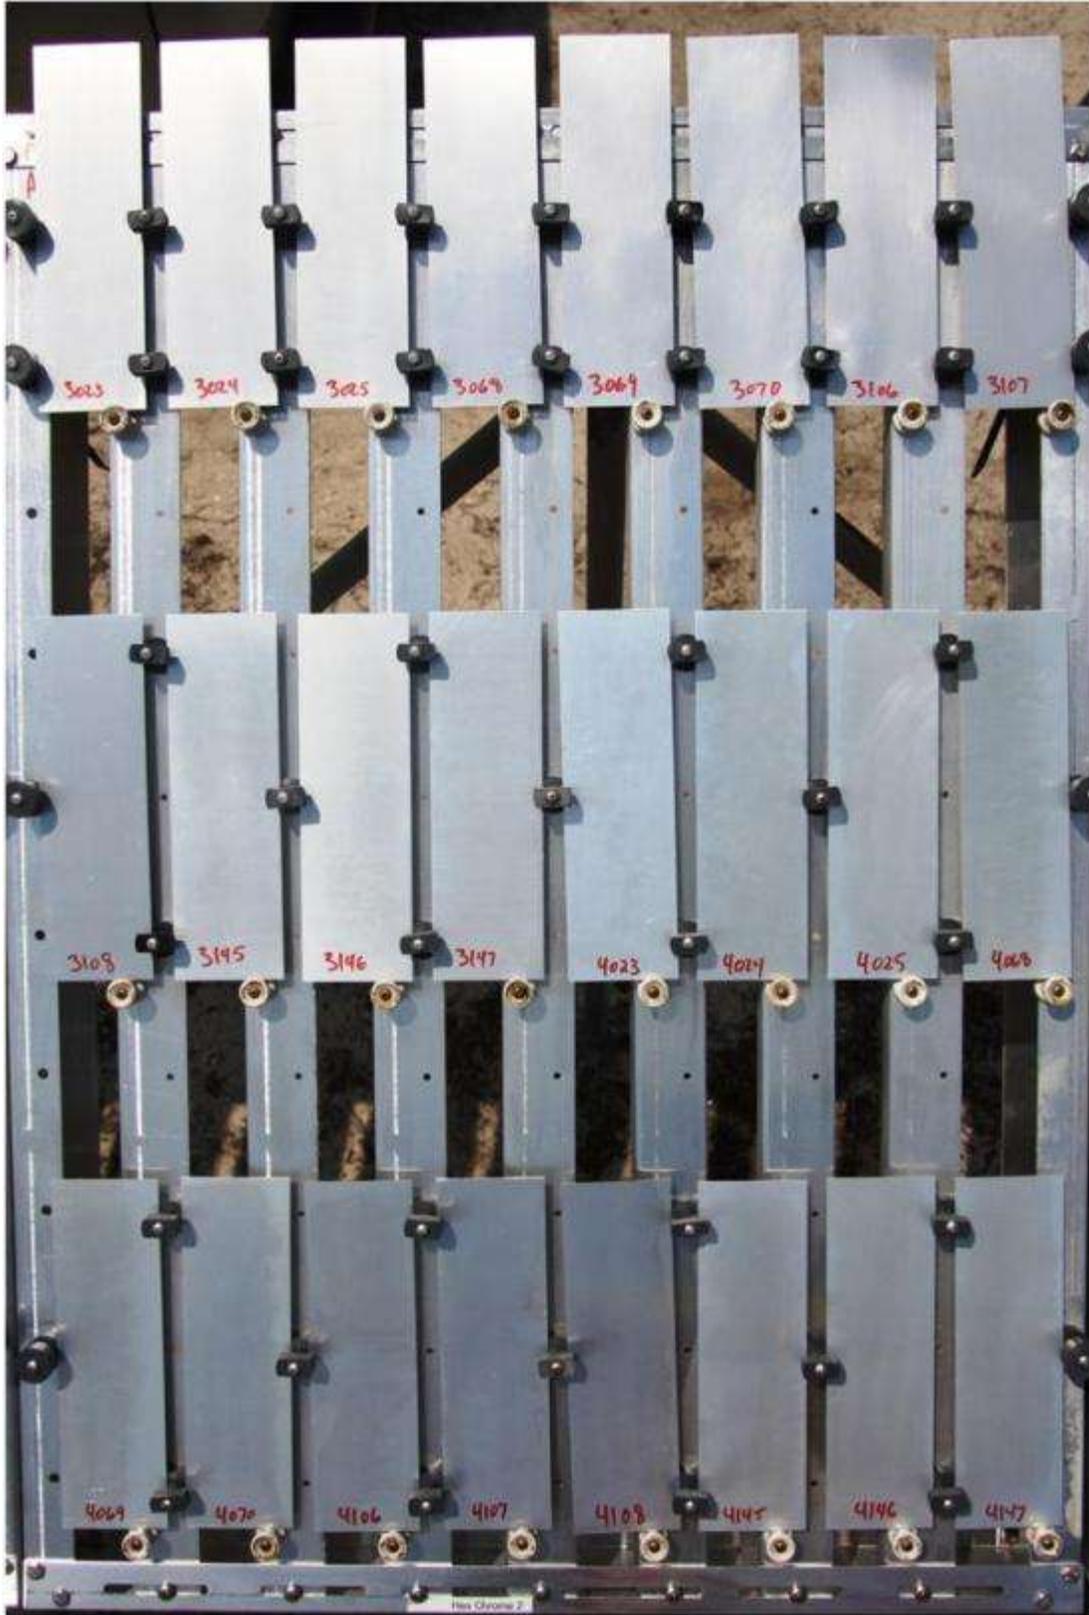


Figure 107 - Beachside Corrosion; Rack 2



Figure 108 - Beachside Corrosion; Rack 3



Figure 109 - Beachside Corrosion; Rack 4



Figure 110 - Beachside Corrosion; Rack 5

3.3.5 Test Panel Pictures – 5 Weeks of Beach Front Exposure

3.3.5.1 Alodine 1600



Figure 111 – Alodine 1600, 6061-T6

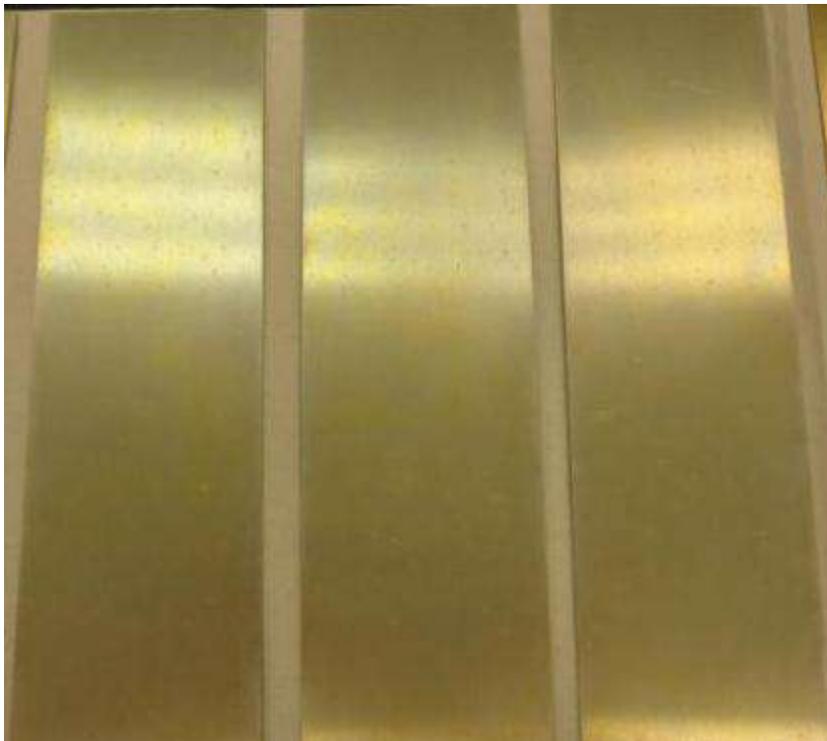


Figure 112 – Alodine 1600, 7075-T73



Figure 113 – Alodine 1600, 2024-T3



Figure 114 – Alodine 1600, 5052-H32

3.3.5.2 Alodine T 5900 RTU



Figure 115 – Alodine T 5900 RTU, 6061-T6



Figure 116 – Alodine T 5900 RTU, 7075-T73



Figure 117 – Alodine T 5900 RTU, 2024-T3

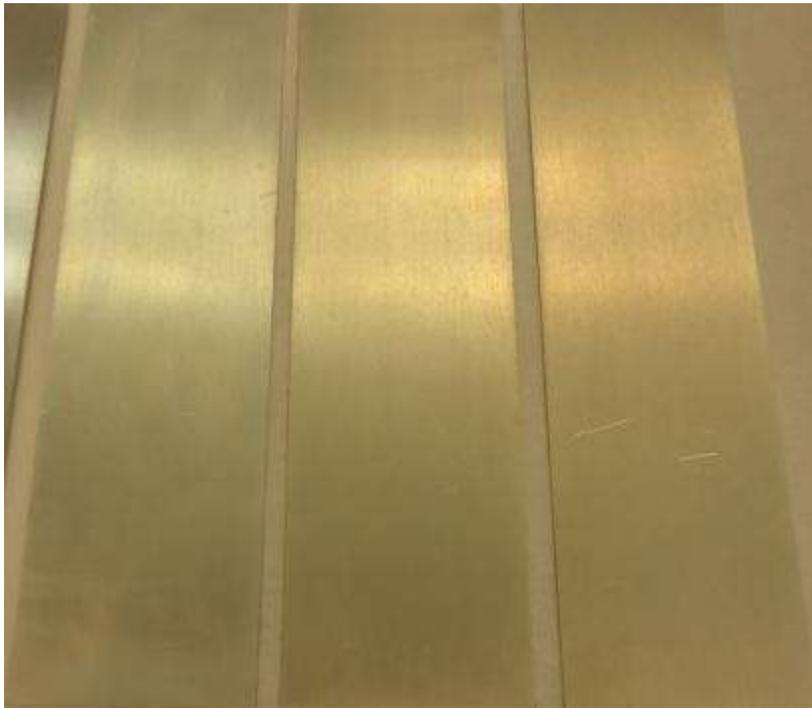


Figure 118 – Alodine T 5900 RTU, 5052-H32

3.3.5.3 Iridite NCP



Figure 119 – Iridite NCP, 6061-T6

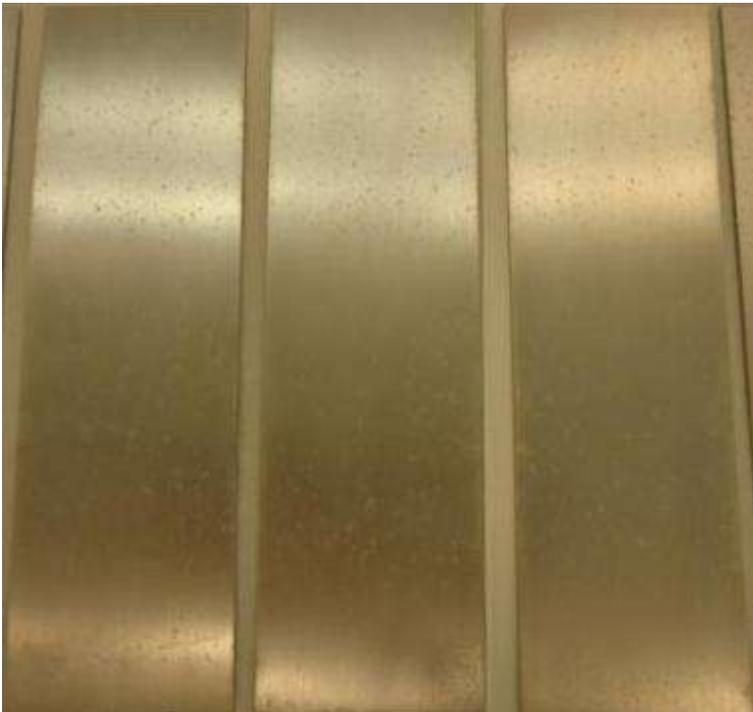


Figure 120 – Iridite NCP, 7075-T73



Figure 121 – Iridite NCP, 2024-T3

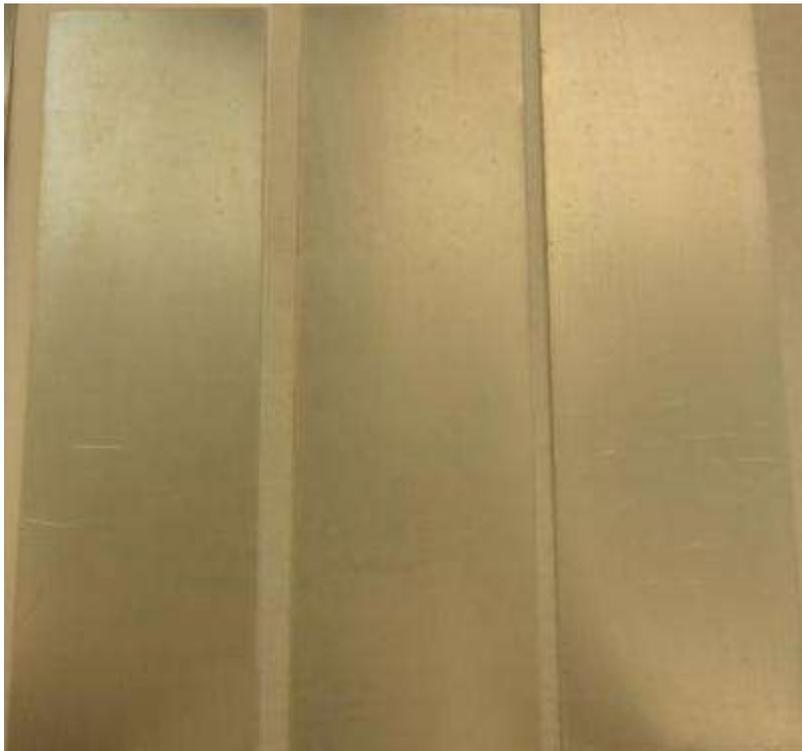


Figure 122 – Iridite NCP, 5052-H32

3.3.5.4 Metalast HF



Figure 123 – Metalast HF, 6061-T6

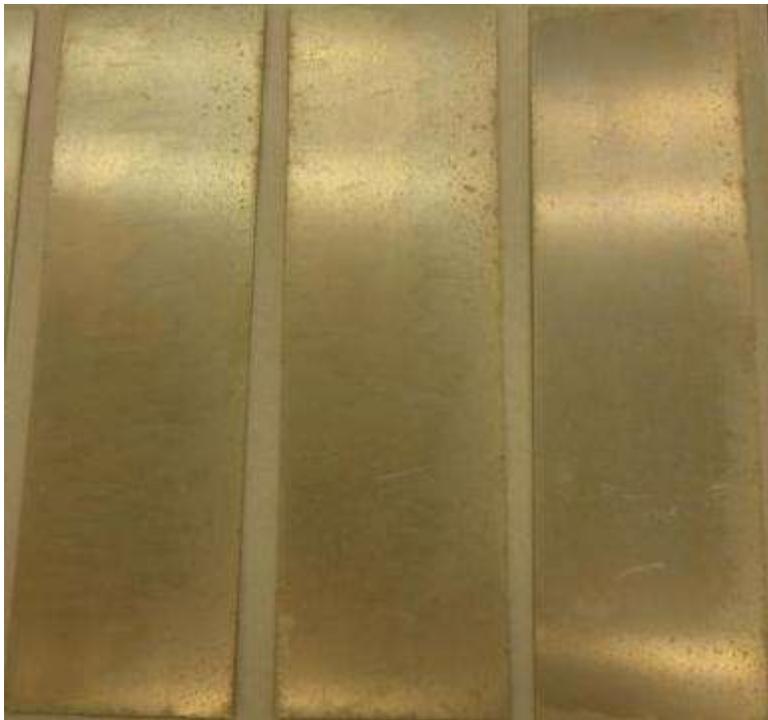


Figure 124 – Metalast HF, 7075-T73



Figure 125 – Metalast HF, 2024-T3



Figure 126 – Metalast HF, 5052-H32

3.3.5.5 Metalast HF-EPA

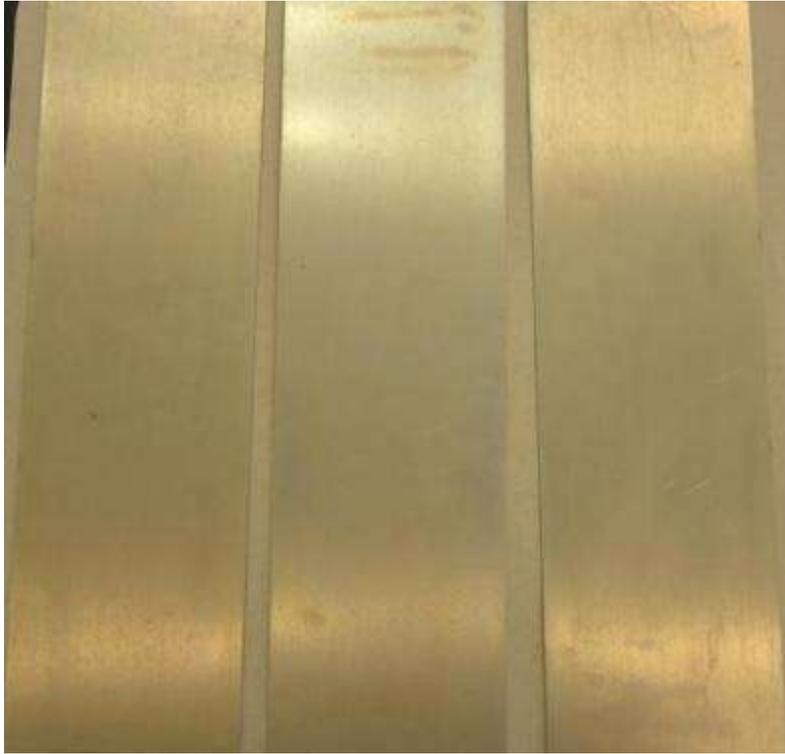


Figure 127 – Metalast HF-EPA, 6061-T6



Figure 128 – Metalast HF-EPA, 7075-T73



Figure 129 – Metalast HF-EPA, 2024-T3

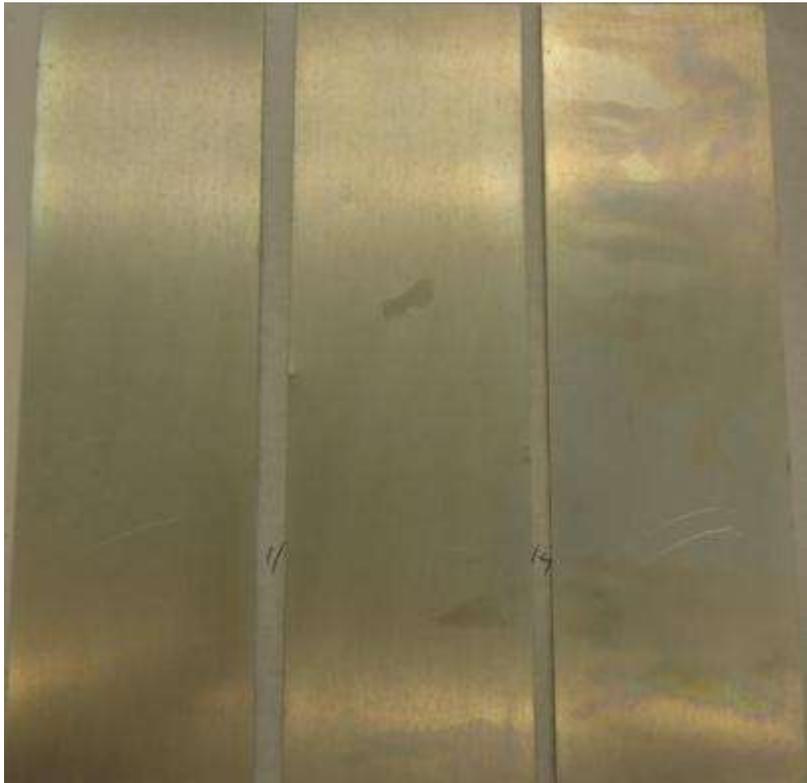


Figure 130 – Metalast HF-EPA, 5052-H32

3.3.5.6 SurTec 650



Figure 131 – SurTec 650, 6061-T6



Figure 132 – SurTec 650, 7075-T73



Figure 133 – SurTec 650, 2024-T3



Figure 134 – SurTec 650, 5052-H32

3.3.5.7 SurTec 650C



Figure 135 – SurTec 650C, 6061-T6



Figure 136 – SurTec 650C, 7075-T73



Figure 137 – SurTec 650C, 2024-T3



Figure 138 – SurTec 650C, 5052-H32

3.4 PATTI JR Pull Test

This test evaluates the pull-off strength (commonly referred to as adhesion) of a coating system from metal substrates.

3.4.1 Test Procedure

This test was conducted per ASTM D 4541 (Standard Test Method for Pull-Off Strength of Coatings Using Portable Adhesion Testers, approved February 1, 2009); Annex 3, Self-Alignment Adhesion Tester Type IV (Test Method D).

Two (2) panels per substrate (6061-T6 and 5052-H32) / per pretreatment were finished with one coat of a volatile organic compound (VOC) compliant epoxy-polyamide primer to a dry film thickness of 0.0006 to 0.0009 inch (0.6 to 0.9 mil). One panel was finished with one coat of epoxy primer conforming to MIL-PRF-23377 (PPG CA7233) while the other was finished with one coat of epoxy primer conforming to MIL-PRF-85582 (Deft 44-GN-07A). Panels were allowed to dry in accordance with the primer specification.

An Elcometer 110 PATTI portable pneumatic adhesion tester was used during testing in conjunction with an F-4 piston and 0.5” pull-stub.

Only hexavalent chrome free pretreatments on alloys 6061-T6 and 5052-H32 were evaluated during this test. Due to the unexpected poor performance of Alodine 1600 during salt spray and cyclic corrosion testing, none of the Alodine 1600 test panels were submitted to pull-off strength adhesion testing for cost saving purposes. Hexavalent chrome free pretreatments on alloys 2024-T3 and 7075-T73 were also omitted from pull-off strength adhesion testing due to unexpected poor performance during salt spray and cyclic corrosion testing.

3.4.2 Evaluation Procedure

This is a qualitative test performed in order to determine adhesion (both inner-coat adhesion and intra-coat cohesion) of coating systems. This test is a measure of the direct normal applied force required to remove one or more layers from a coating system as a measure of adhesion strength.

The stakeholders of the Hex Chrome Free Coatings for Electronics Applications project did not set pass / fail criteria for this test.

3.4.3 Test Results – PATTI JR Pull Test

Test results from PATTI JR Pull Testing are contained in Figure 139 and Figure 140. Primer thicknesses for the PPG CA7233 primer were thicker than specified per MIL-PRF-23377. Primer thicknesses for the Deft 44-GN-07A primer met specification or were slightly thicker than specified per MIL-PRF-85582. For the PPG CA7233 primer, the high occurrence of adhesive failures at the primer / substrate interface may be attributed to the primer being inadvertently thicker after application than specified in MIL-PRF-23377. Test results from the Deft 44-GN-07A coated panels show a high occurrence of failures attributed to bad adhesive. This may be attributed to a pot life issue with the adhesive.

Pretreatment	Alloy	Primer	Primer Thickness	Panel #	Pull-Off Tensile Strength (POTS)			Average (psi)
					(psi)			
Alodine T 5900 RTU	6061-T6	PPG CA7233	1.9	2029	399	401	381	394
	Fracture Mode				100% adhesive primer/substrate	100% adhesive primer/substrate	100% adhesive primer/substrate	
	5052-H32	PPG CA7233	1.7	2151	399	428	416	414
	Fracture Mode				100% adhesive primer/substrate	100% adhesive primer/substrate	100% adhesive primer/substrate	
Iridite NCP	6061-T6	PPG CA7233	1.8	3029	436	470	449	452
	Fracture Mode				100% adhesive primer/substrate	100% adhesive primer/substrate	100% adhesive primer/substrate	
	5052-H32	PPG CA7233	1.9	3151	428	436	410	425
	Fracture Mode				100% adhesive primer/substrate	100% adhesive primer/substrate	100% adhesive primer/substrate	
Metalast HF	6061-T6	PPG CA7233	1.7	4029	560	569	560	563
	Fracture Mode				85% adhesive primer/substrate 15% bad adhesive	85% adhesive primer/substrate 15% bad adhesive	85% adhesive primer/substrate 15% bad adhesive	
	5052-H32	PPG CA7233	1.8	4151	544	523	517	528
	Fracture Mode				85% adhesive primer/substrate 15% bad adhesive	90% adhesive primer/substrate 10% bad adhesive	90% adhesive primer/substrate 10% bad adhesive	
Metalast HF-EPA	6061-T6	PPG CA7233	1.9	5029	391	418	360	390
	Fracture Mode				100% adhesive primer/substrate	100% adhesive primer/substrate	100% adhesive primer/substrate	
	5052-H32	PPG CA7233	2	5151	393	443	230	355
	Fracture Mode				100% adhesive primer/substrate	70% adhesive primer/substrate 30% bad adhesive	100% adhesive primer/substrate	
SurTec 650	6061-T6	PPG CA7233	1.5	6029	467	441	453	454
	Fracture Mode				100% adhesive primer/substrate	100% adhesive primer/substrate	100% adhesive primer/substrate	
	5052-H32	PPG CA7233	1.8	6151	436	426	436	433
	Fracture Mode				100% adhesive primer/substrate	100% adhesive primer/substrate	100% adhesive primer/substrate	
SurTec 650C	6061-T6	PPG CA7233	2	7029	449	445	428	441
	Fracture Mode				100% adhesive primer/substrate	100% adhesive primer/substrate	100% adhesive primer/substrate	
	5052-H32	PPG CA7233	2.3	7151	447	428	401	425
	Fracture Mode				100% adhesive primer/substrate	100% adhesive primer/substrate	100% adhesive primer/substrate	

Figure 139 - PATTI JR Pull Test Results; Primer (MIL-PRF-23377) - PPG CA7233

Pretreatment	Alloy	Primer	Primer Thickness	Panel #	Pull-Off Tensile Strength (POTS) (psi)			Average (psi)
Alodine T 5900 RTU	6061-T6	Deft 44-GN-07A	0.96	2030	298	306	362	322
	Fracture Mode				100% cohesive primer	100% cohesive primer	85% cohesive primer 15% adhesive primer/substrate	
	5052-H32	Deft 44-GN-07A	0.78	2152	300	350	372	341
	Fracture Mode				100% cohesive primer	100% cohesive primer	100% cohesive primer	
Iridite NCP	6061-T6	Deft 44-GN-07A	1	3030	215	269	346	277
	Fracture Mode				10% cohesive primer 90% bad adhesive	30% cohesive primer 70% bad adhesive	100% bad adhesive	
	5052-H32	Deft 44-GN-07A	1	3152	271	228	259	253
	Fracture Mode				45% cohesive primer 55% bad adhesive	35% cohesive primer 65% bad adhesive	20% cohesive primer 80% bad adhesive	
Metalast HF	6061-T6	Deft 44-GN-07A	1	4030	292	372	275	313
	Fracture Mode				100% cohesive primer	100% cohesive primer	90% cohesive primer 10% bad adhesive	
	5052-H32	Deft 44-GN-07A	0.8	4152	329	288	277	298
	Fracture Mode				100% cohesive primer	75% cohesive primer 25% bad adhesive	100% cohesive primer	
Metalast HF-EPA	6061-T6	Deft 44-GN-07A	1.1	5030	286	385	286	319
	Fracture Mode				10% cohesive primer 90% bad adhesive	100% cohesive primer	50% cohesive primer 50% bad adhesive	
	5052-H32	Deft 44-GN-07A	1.3	5152	393	313	389	365
	Fracture Mode				100% cohesive primer	80% cohesive primer 20% bad adhesive	85% cohesive primer 15% bad adhesive	
SurTec 650	6061-T6	Deft 44-GN-07A	1.1	6030	197	222	240	220
	Fracture Mode				100% bad adhesive	85% cohesive primer 15% bad adhesive	100% bad adhesive	
	5052-H32	Deft 44-GN-07A	1.3	6152	352	310	453	372
	Fracture Mode				100% cohesive primer	100% cohesive primer	95% cohesive primer 5% bad adhesive	
SurTec 650C	6061-T6	Deft 44-GN-07A	1.38	7030	352	354	337	348
	Fracture Mode				100% cohesive primer	100% cohesive primer	100% cohesive primer	
	5052-H32	Deft 44-GN-07A	1.1	7152	381	348	389	372
	Fracture Mode				100% cohesive primer	100% cohesive primer	100% cohesive primer	

Figure 140 - PATTI JR Pull Test Results; Primer (MIL-PRF-85582) - Deft 44-GN-07A

3.4.4 Test Panel Pictures with Burst Pressure Readings (psi)

3.4.4.1 Alodine T 5900 RTU – PPG CA7233

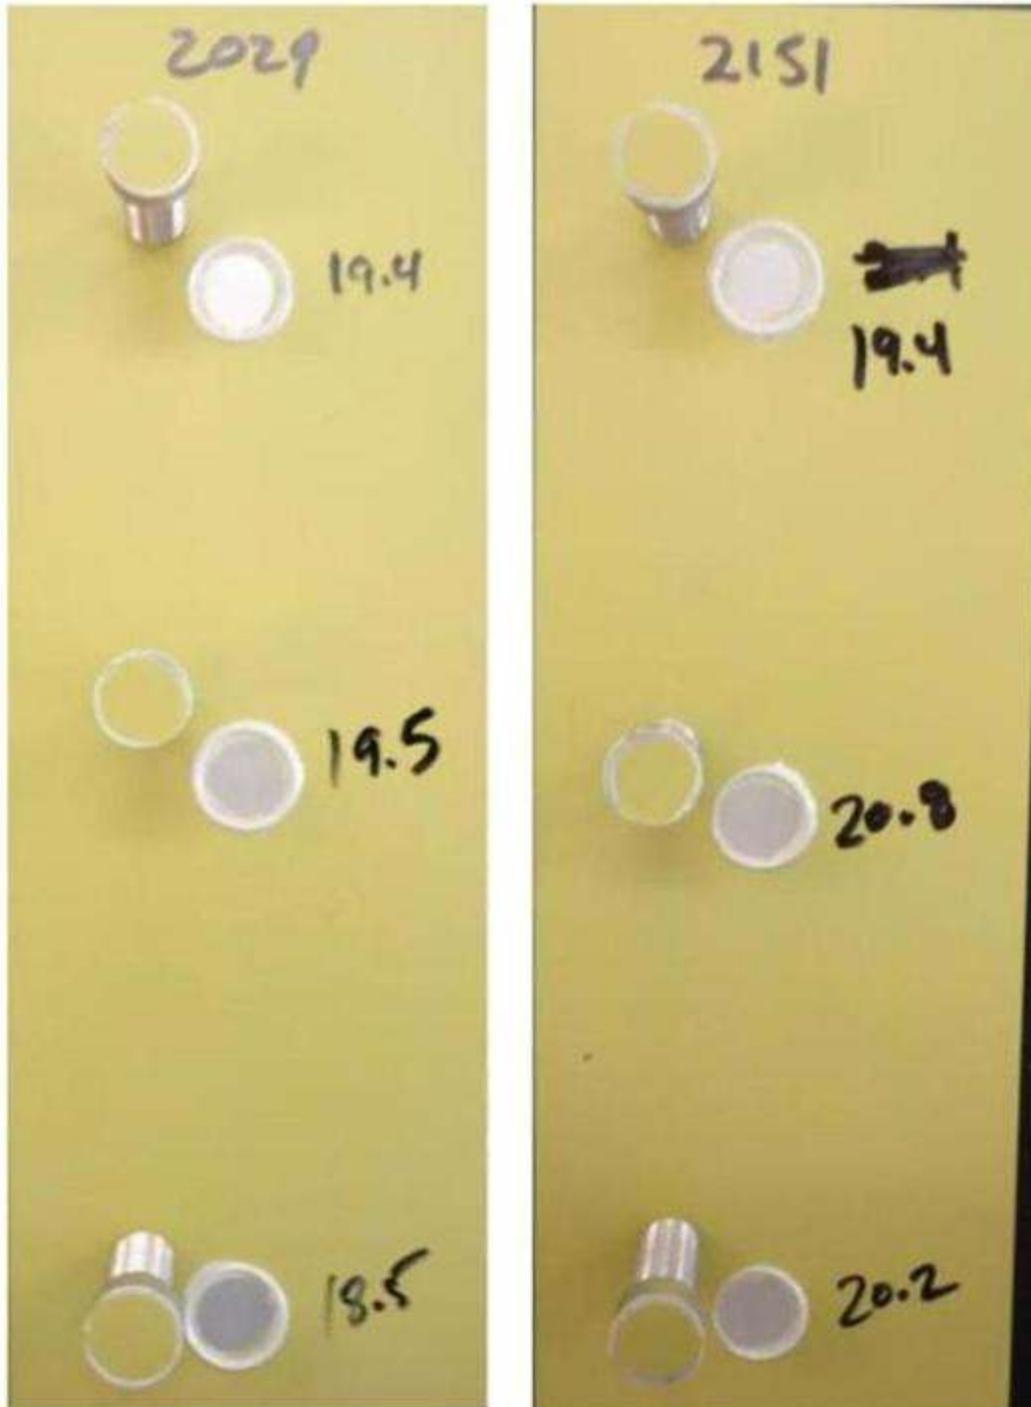


Figure 141 – Alodine T 5900 RTU; 6061-T6 (Left), 5052-H32 (Right)

3.4.4.2 Iridite NCP - PPG CA7233



Figure 142 – Iridite NCP; 6061-T6 (Left), 5052-H32 (Right)

3.4.4.3 Metalast HF - PPG CA7233

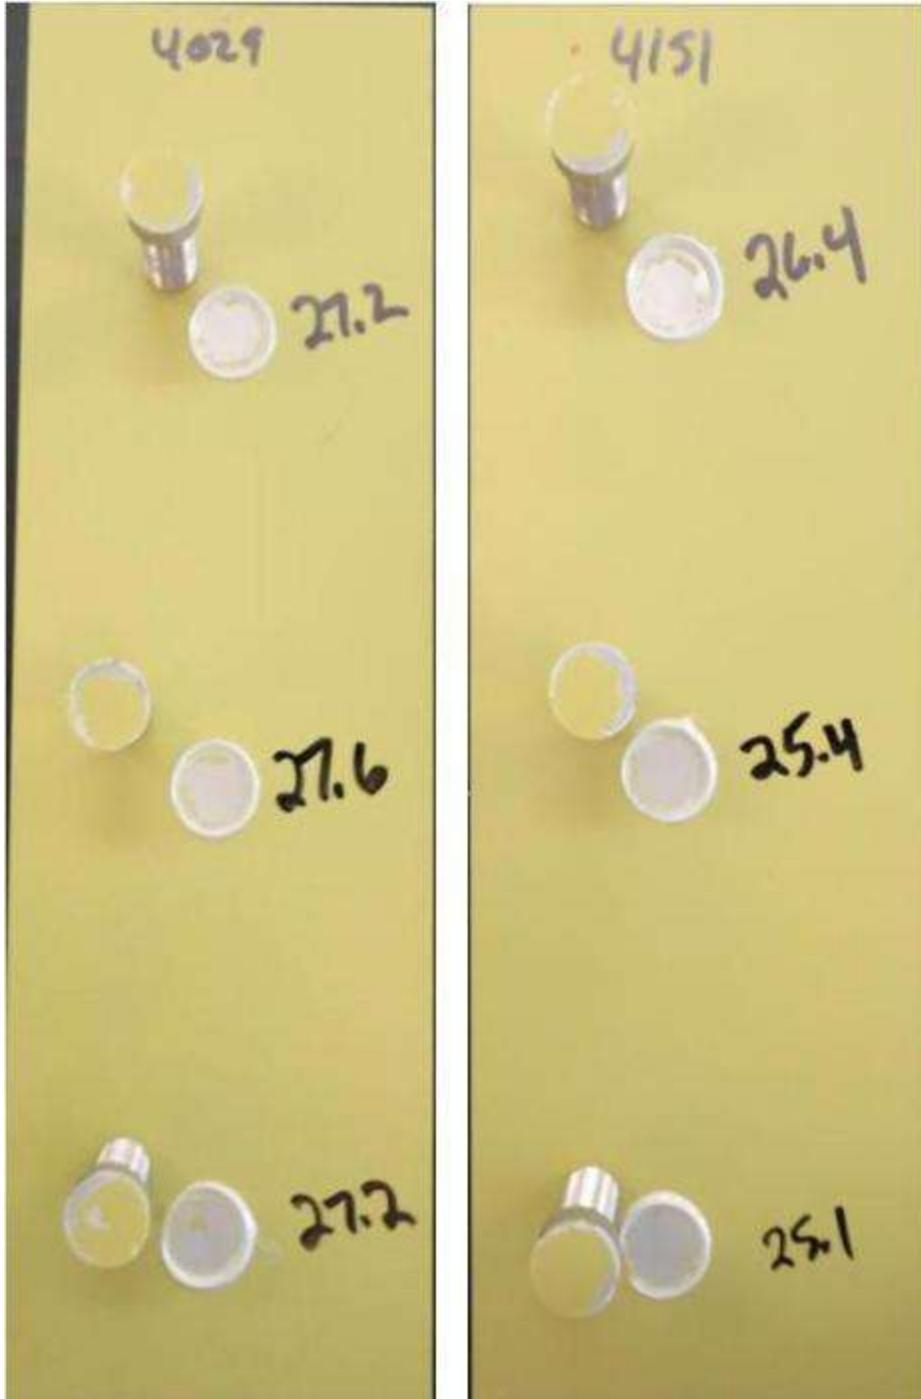


Figure 143 – Metalast HF; 6061-T6 (Left), 5052-H32 (Right)

3.4.4.4 Metalast HF-EPA - PPG CA7233



Figure 144 – Metalast HF-EPA; 6061-T6 (Left), 5052-H32 (Right)

3.4.4.5 SurTec 650 - PPG CA7233



Figure 145 – SurTec 650; 6061-T6 (Left), 5052-H32 (Right)

3.4.4.6 SurTec 650C - PPG CA7233

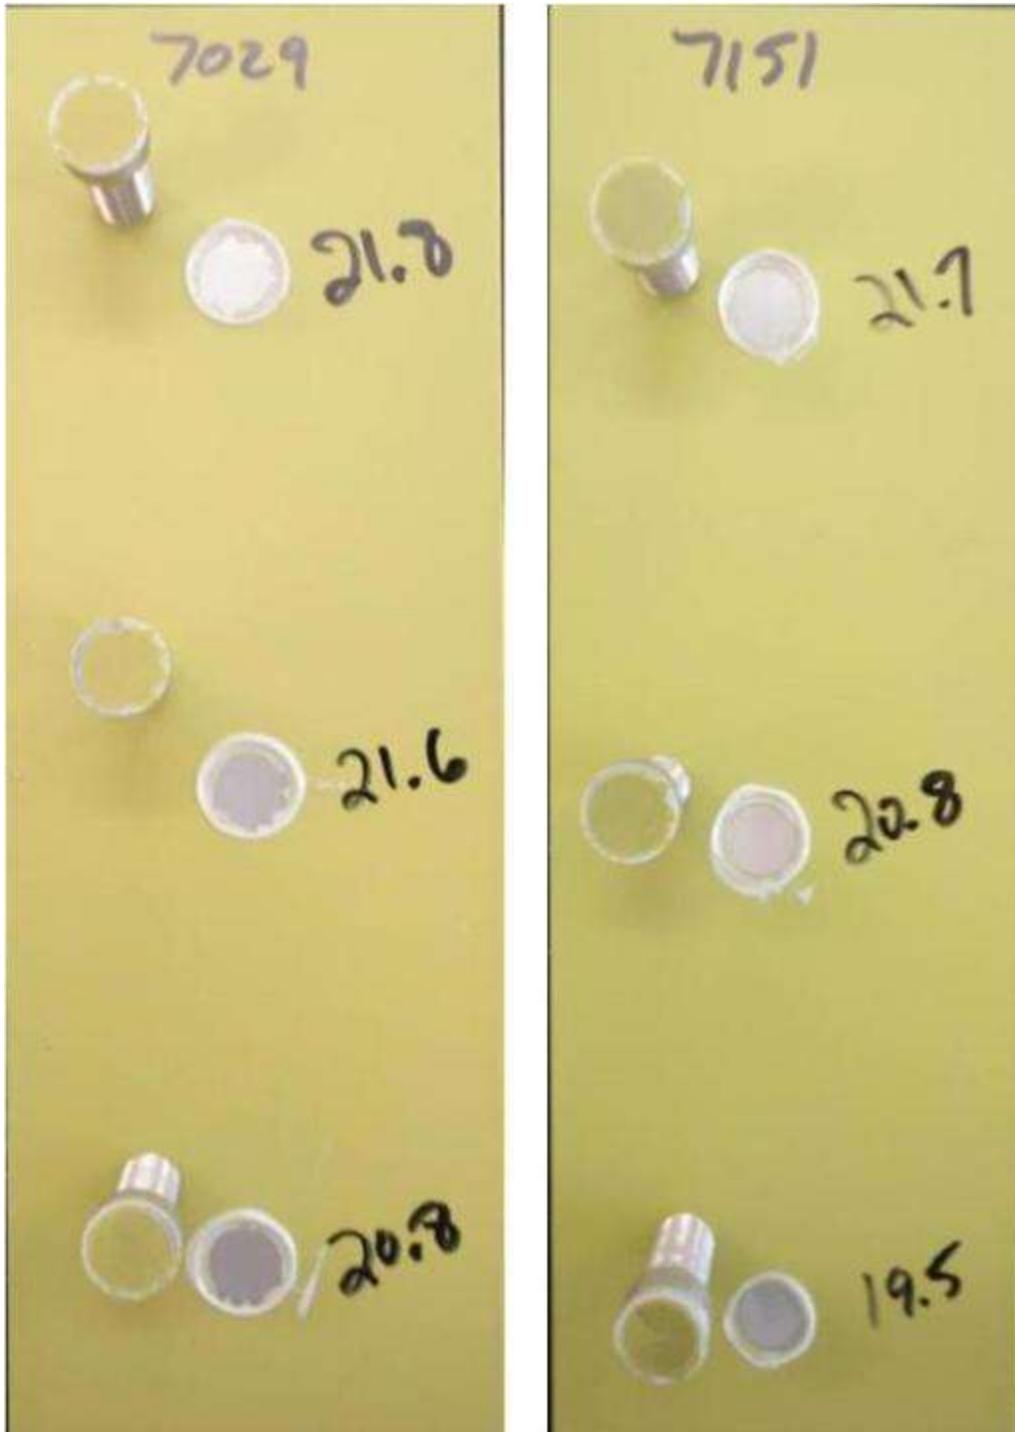


Figure 146 – SurTec 650C; 6061-T6 (Left), 5052-H32 (Right)

3.4.5 Test Panel Pictures with Burst Pressure Readings (psi)

3.4.5.1 Alodine T 5900 RTU - Deft 44-GN-07A

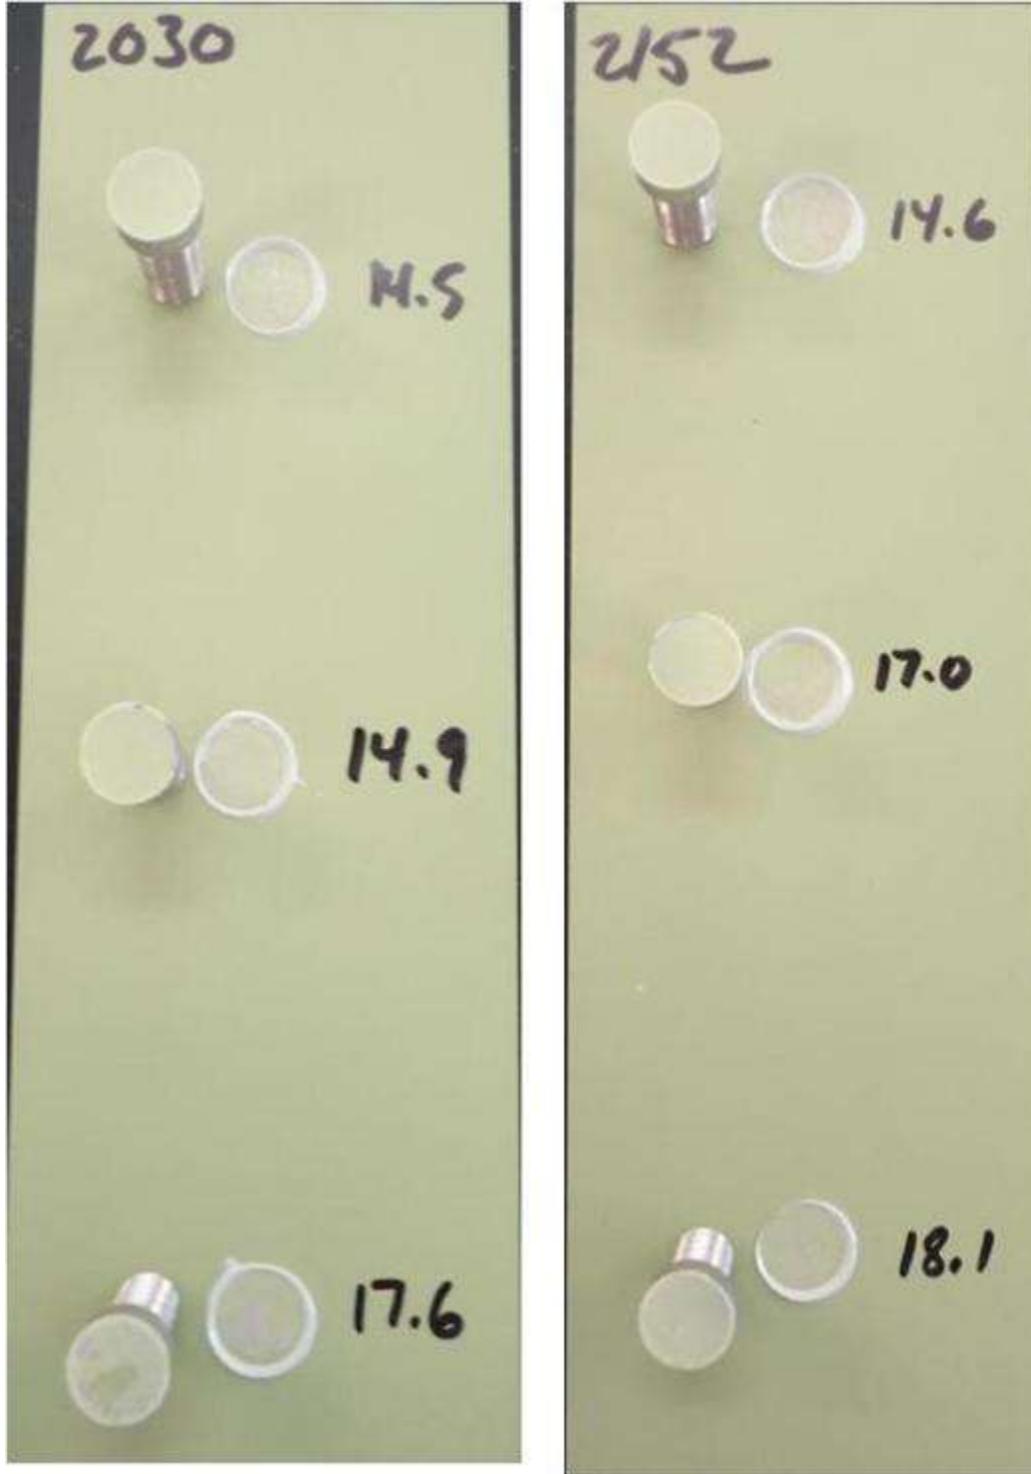


Figure 147 – Alodine T 5900 RTU; 6061-T6 (Left), 5052-H32 (Right)

3.4.5.2 Iridite NCP - Deft 44-GN-07A



Figure 148 – Iridite NCP; 6061-T6 (Left), 5052-H32 (Right)

3.4.5.3 Metalast HF - Deft 44-GN-07A

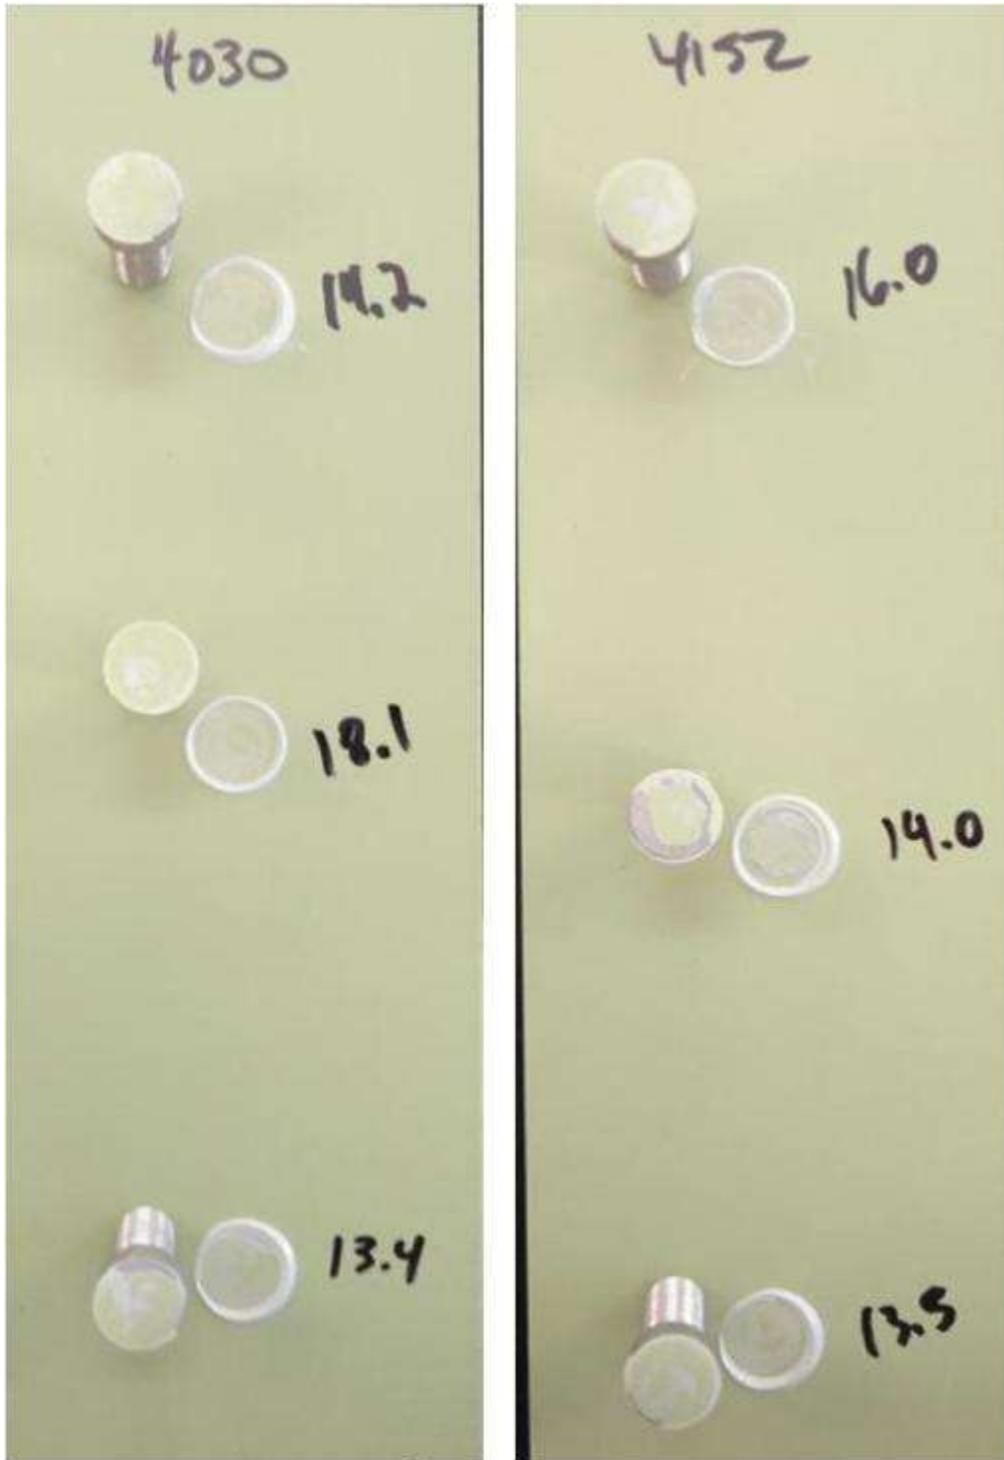


Figure 149 – Metalast HF; 6061-T6 (Left), 5052-H32 (Right)

3.4.5.4 Metalast HF-EPA - Deflt 44-GN-07A

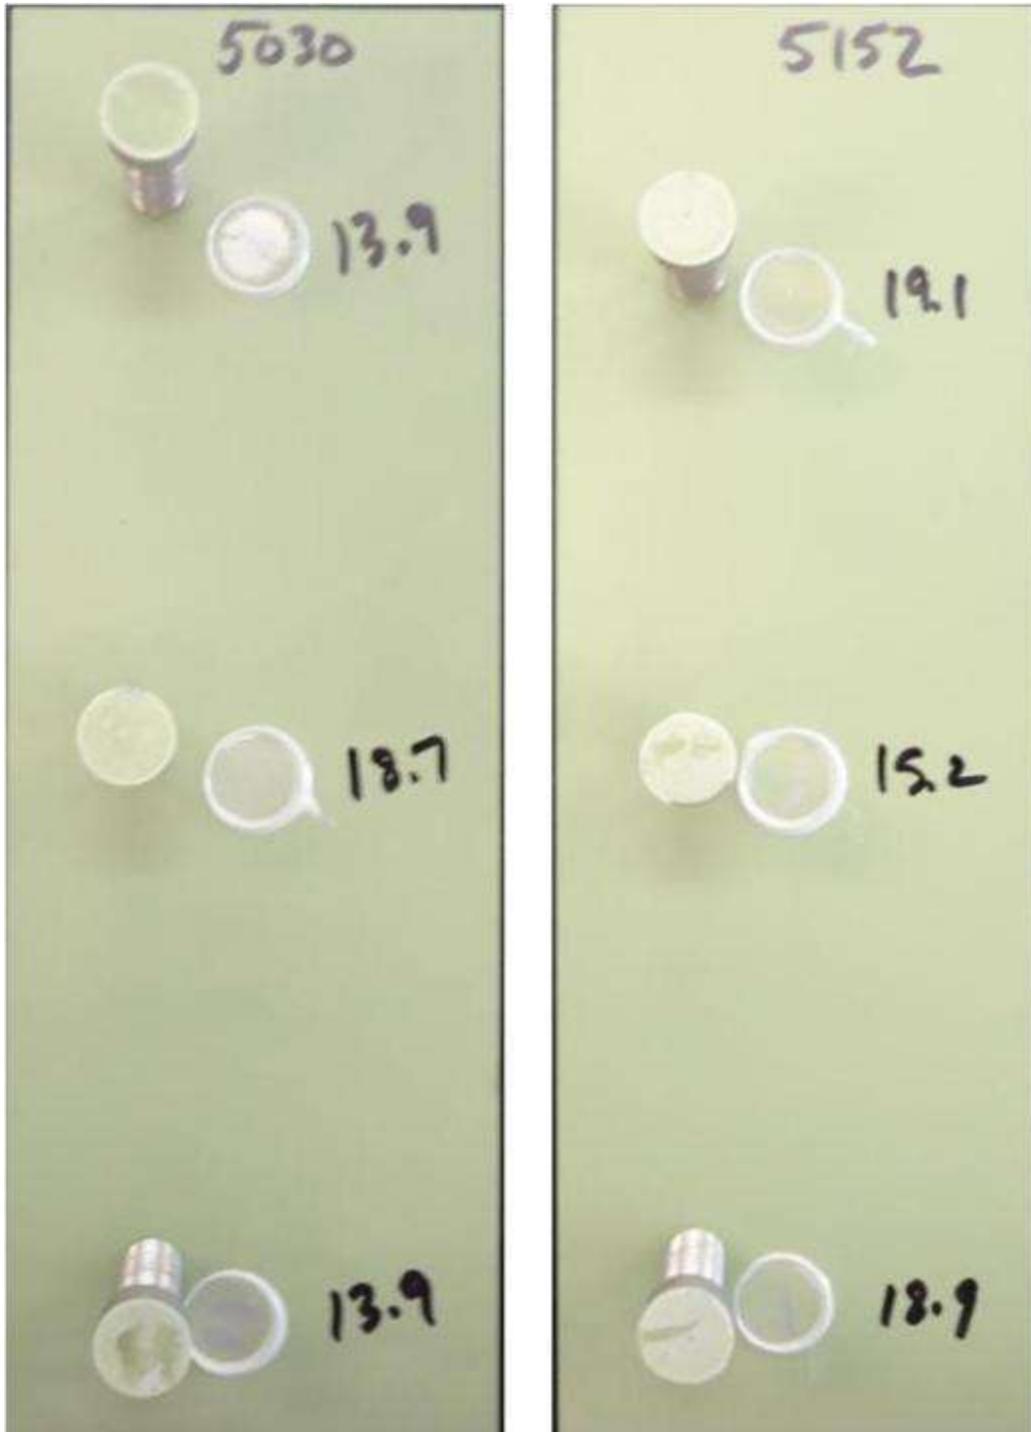


Figure 150 – Metalast HF-EPA; 6061-T6 (Left), 5052-H32 (Right)

3.4.5.5 SurTec 650 - Deft 44-GN-07A

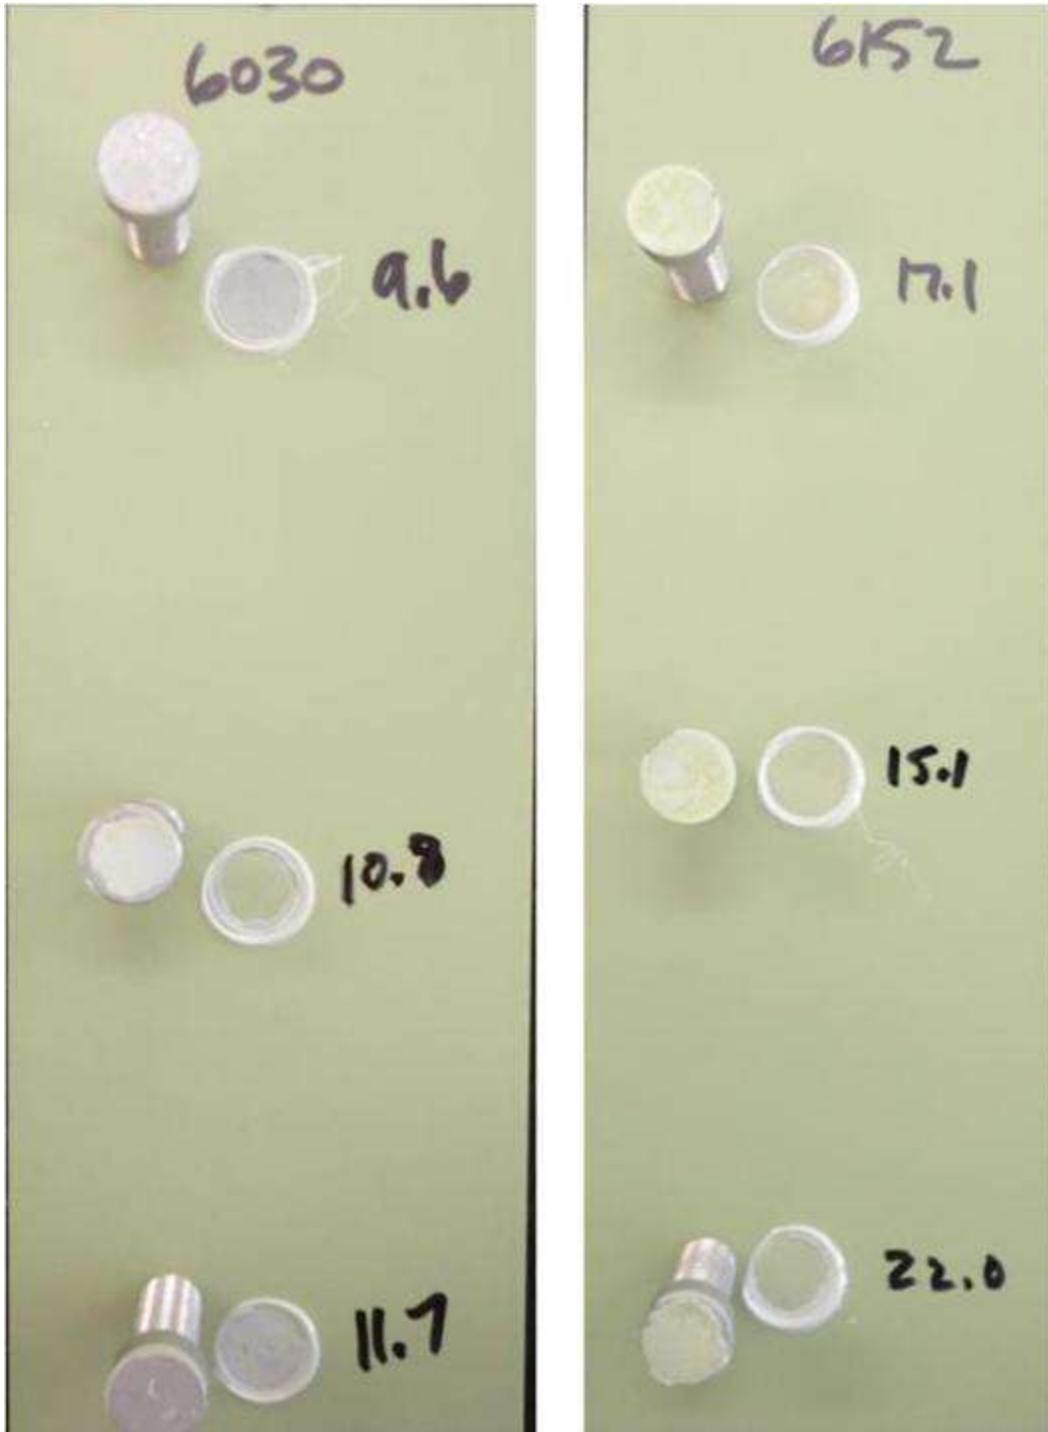


Figure 151 – SurTec 650; 6061-T6 (Left), 5052-H32 (Right)

3.4.5.6 SurTec 650C - Deft 44-GN-07A

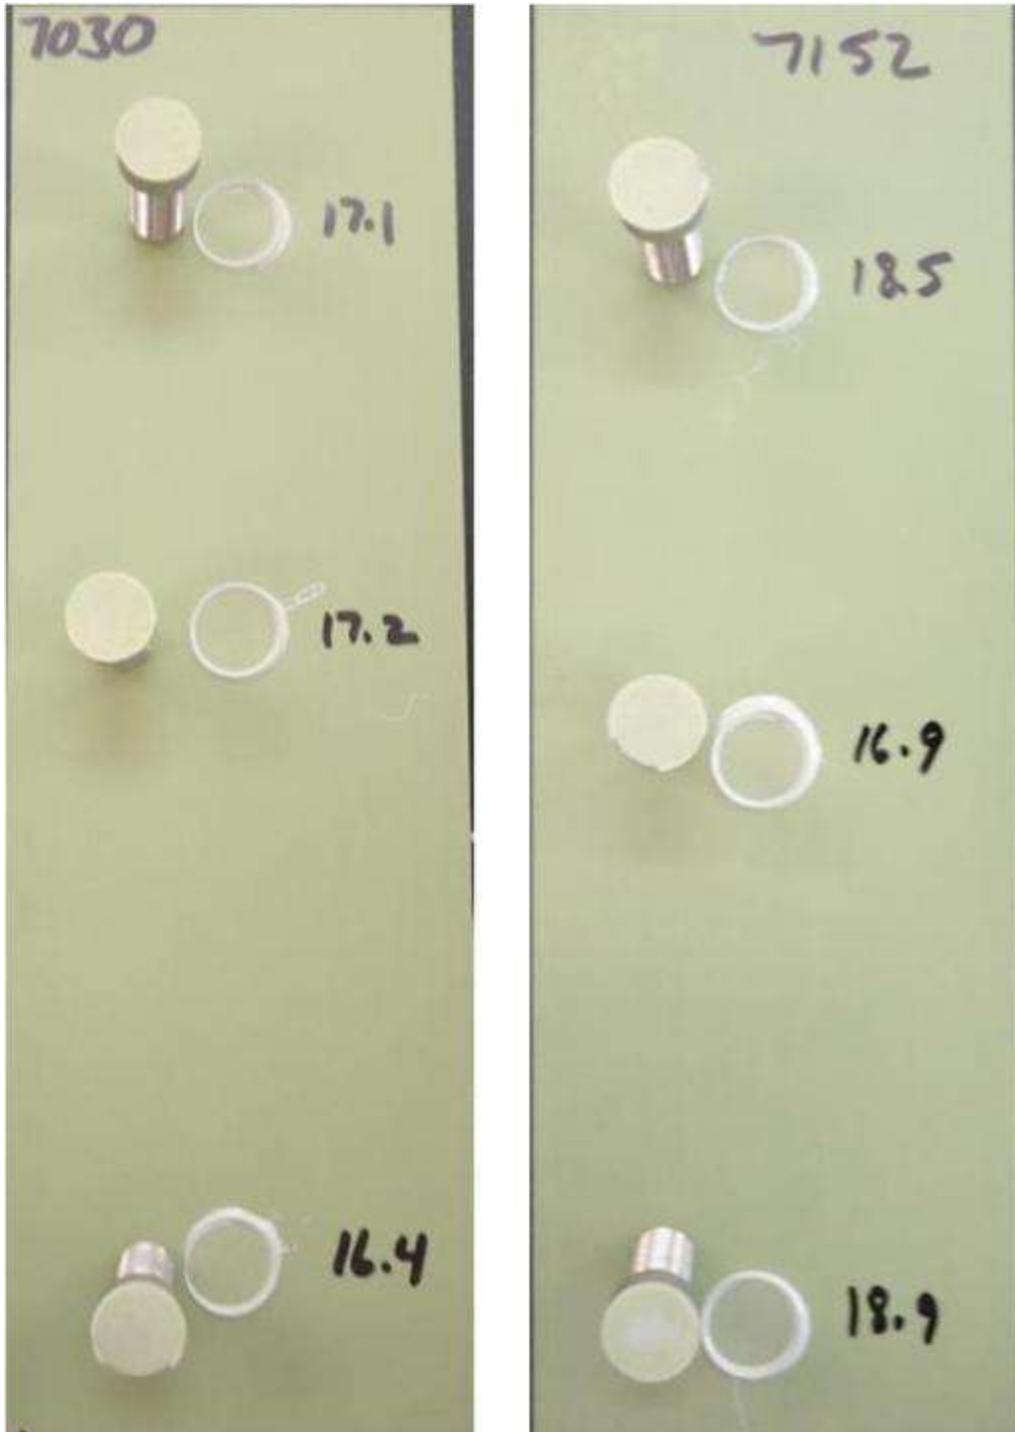


Figure 152 – SurTec 650C; 6061-T6 (Left), 5052-H32 (Right)

3.5 Cross-Cut Tape Test

This test is used for assessing the adhesion of coating films to metallic substrates by applying and removing pressure-sensitive tape over cuts made in the film.

3.5.1 Test Procedure

The panels were tested in accordance with ASTM D 3359 (Standard Test Methods for Measuring Adhesion by Tape Test), Test Method B, Cross-Cut Tape Test.

Two (2) panels per substrate / per pretreatment were finished with one coat of a volatile organic compound (VOC) compliant epoxy-polyamide primer conforming to MIL PRF 23377 and MIL PRF 85582 (for a total of four panels per substrate) to a dry film thickness of 0.0006 to 0.0009 inch (0.6 to 0.9 mil). A polyurethane topcoat conforming to MIL PRF 85285 (PPG CA9311) was applied.

Per ASTM D 3359, Test Method B, a lattice pattern was made in each direction in the coatings to the substrate. Pressure-sensitive tape was applied over the lattice and then removed, and adhesion is evaluated.

An Elcometer 107 cross hatch cutter was used in conjunction with Elcometer adhesive tape.

Only hexavalent chrome free pretreatments on alloys 6061-T6 and 5052-H32 were evaluated during this test. Due to the unexpected poor performance of Alodine 1600 during salt spray and cyclic corrosion testing, none of the Alodine 1600 test panels were submitted to cross-cut tape testing for cost saving purposes. Hexavalent chrome free pretreatments on alloys 2024-T3 and 7075-T73 were also omitted from cross-cut tape testing due to unexpected poor performance during salt spray and cyclic corrosion testing.

3.5.2 Evaluation Procedure

Panels were evaluated per ASTM D 3359, Test Method B, Figure 1 Classification of Adhesion Test Results (see Figure 153).



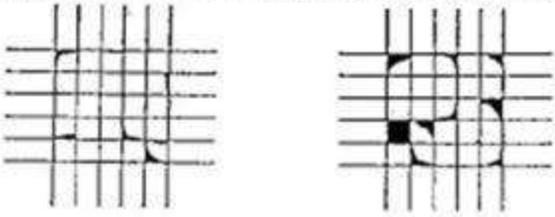
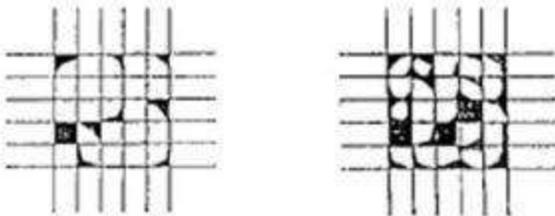
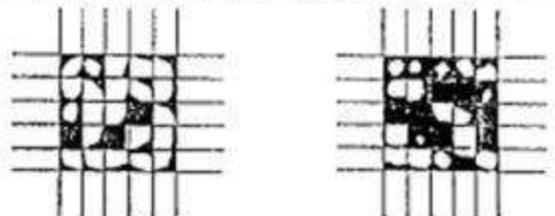

CLASSIFICATION	PERCENT AREA REMOVED	SURFACE OF CROSS-CUT AREA FROM WHICH FLAKING HAS OCCURRED FOR SIX PARALLEL CUTS AND ADHESION RANGE BY PERCENT
5B	0% None	
4B	Less than 5%	
3B	5 - 15%	
2B	15 - 35%	
1B	35 - 65%	
0B	Greater than 65%	

Figure 153 - ASTM D 3359, Test Method B, Figure 1 Classification of Adhesion Test Results

3.5.3 Test Results – Cross-Cut Tape Test

Test results from the Cross-Cut Tape Testing are contained in Figure 154 and Figure 155. Test panels with PPG CA 7233 primer rated poorly for most of the pretreatments. Only one set of test panels, Metalast HF with PPG CA 7233 primer, received perfect ratings for all test panels analyzed. Iridite NCP with PPG CA 7233 performed adequately on the 5052-H32 test panels. Ratings for Iridite NCP with PPG CA 7233 on 6061-T6 test panels were mixed with one test panel receiving a flawless rating while the other test panel rated below acceptable criteria. Test panels with Deft 44-GN-07A primer were rated as flawless across all test panels regardless of pretreatment or alloy combination. The diversity of results between the two primers may be attributed to the fact that the PPG CA 7233 was thicker than specified in the specifications for this testing after it was applied. It is recommended to consider re-testing with that primer applied more consistently with the specification.

Pretreatment	Alloy	Unique Panel #	Batch #	Result
Alodine T 5900 RTU	6061-T6	2031	B4	1B
		2032	B3	1B
	5052-H32	2153	B7	1B
		2154	B7	1B
Iridite NCP	6061-T6	3031	B4	5B
		3032	B3	2B
	5052-H32	3153	B7	4B
		3154	B7	5B
Metalast HF	6061-T6	4031	B4	5B
		4032	B3	5B
	5052-H32	4153	B7	5B
		4154	B7	5B
Metalast HF-EPA	6061-T6	5031	B4	1B
		5032	B3	1B
	5052-H32	5153	B7	1B
		5154	B7	1B
SurTec 650	6061-T6	6031	B4	2B
		6032	B3	1B
	5052-H32	6153	B7	1B
		6154	B7	1B
SurTec 650C	6061-T6	7031	B4	2B
		7032	B3	2B
	5052-H32	7153	B7	2B
		7154	B7	2B

Figure 154 – Cross-Cut Tape Test Results; Primer (MIL-PRF-23377) - PPG CA7233

Pretreatment	Alloy	Unique Panel #	Batch #	Result
Alodine T 5900 RTU	6061-T6	2033	B2	5B
		2034	B7	5B
	5052-H32	2155	B5	5B
		2156	B2	5B
Iridite NCP	6061-T6	3033	B2	5B
		3034	B7	5B
	5052-H32	3155	B5	5B
		3156	B2	5B
Metalast HF	6061-T6	4033	B2	5B
		4034	B7	5B
	5052-H32	4155	B5	5B
		4156	B2	5B
Metalast HF-EPA	6061-T6	5033	B2	5B
		5034	B7	5B
	5052-H32	5155	B5	5B
		5156	B2	5B
SurTec 650	6061-T6	6033	B2	5B
		6034	B7	5B
	5052-H32	6155	B5	4B
		6156	B2	5B
SurTec 650C	6061-T6	7033	B2	5B
		7034	B7	5B
	5052-H32	7155	B5	5B
		7156	B2	5B

Figure 155 – Cross-Cut Tape Test Results; Primer (MIL-PRF-85582) - Deft 44-GN-07A

3.5.4 Test Panel Pictures with ASTM D 3359, Test Method B Ratings

3.5.4.1 Alodine T 5900 RTU - PPG CA7233 - PPG CA9311

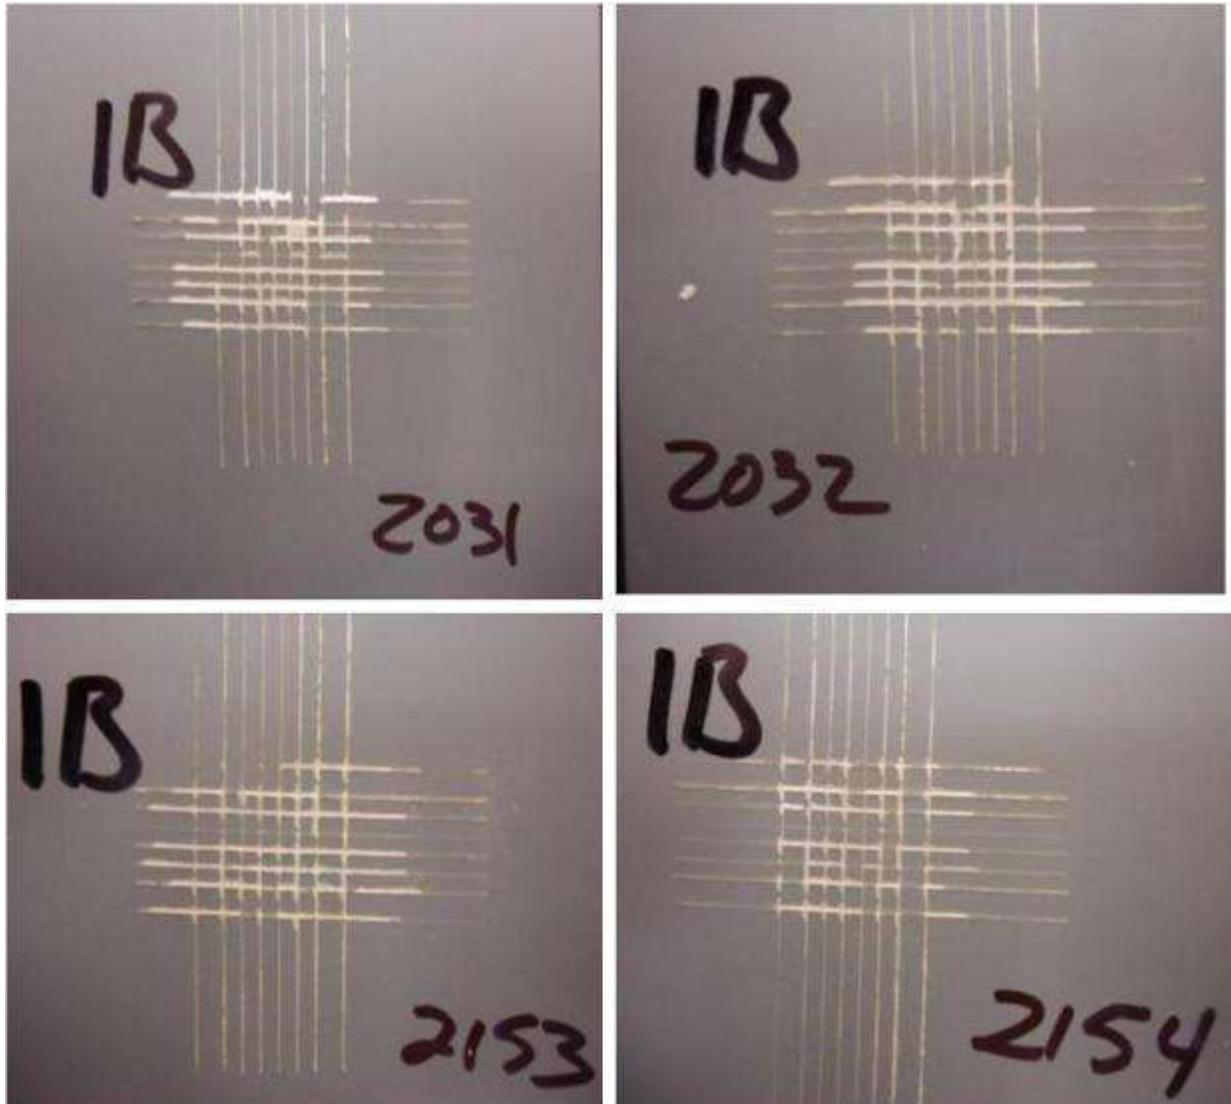


Figure 156 – Alodine T 5900 RTU; 6061-T6 (Top), 5052-H32 (Bottom)

3.5.4.2 Iridite NCP - PPG CA7233 - PPG CA9311

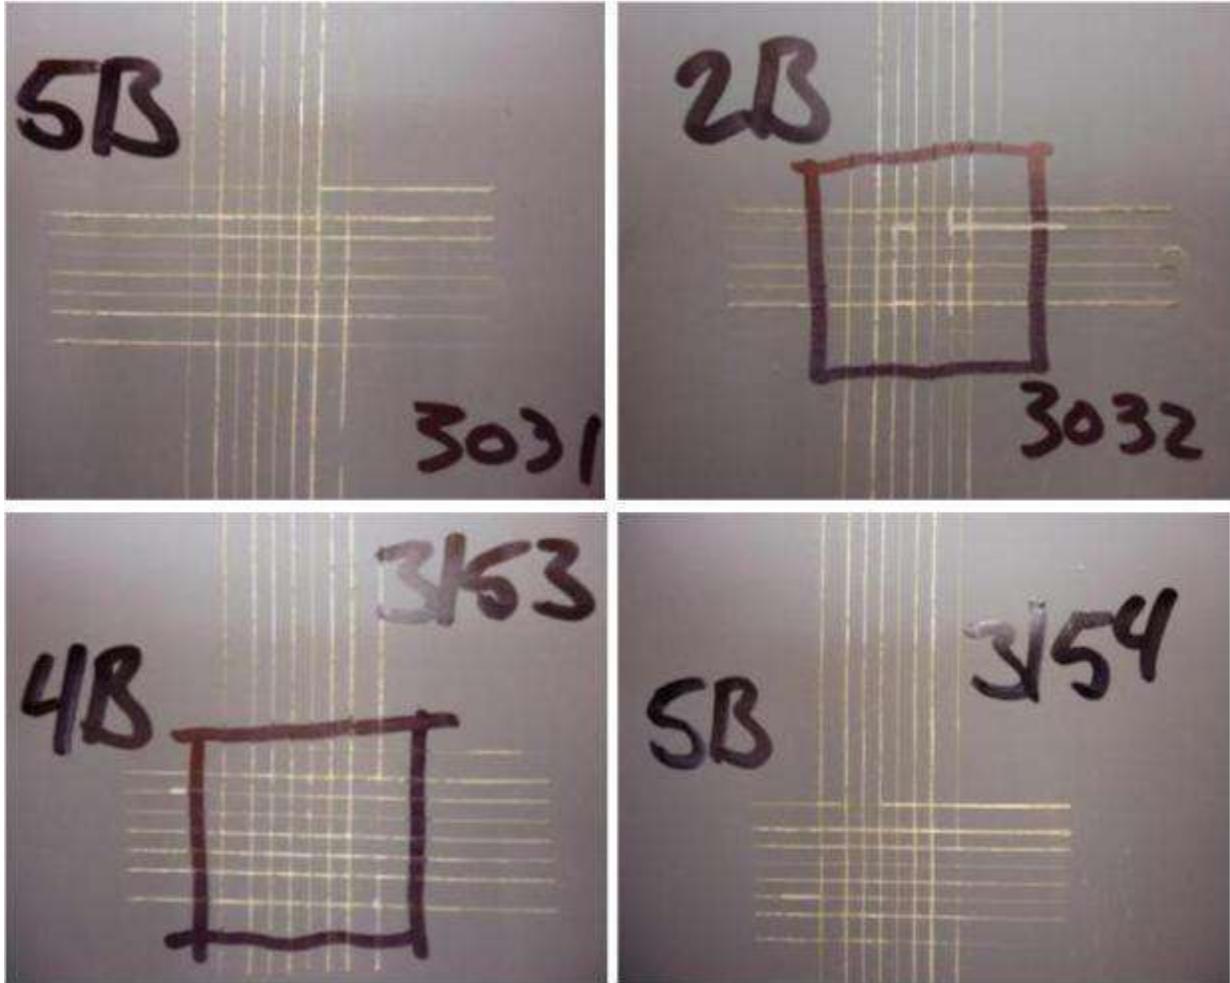


Figure 157 – Iridite NCP; 6061-T6 (Top), 5052-H32 (Bottom)

3.5.4.3 Metalast HF - PPG CA7233 - PPG CA9311

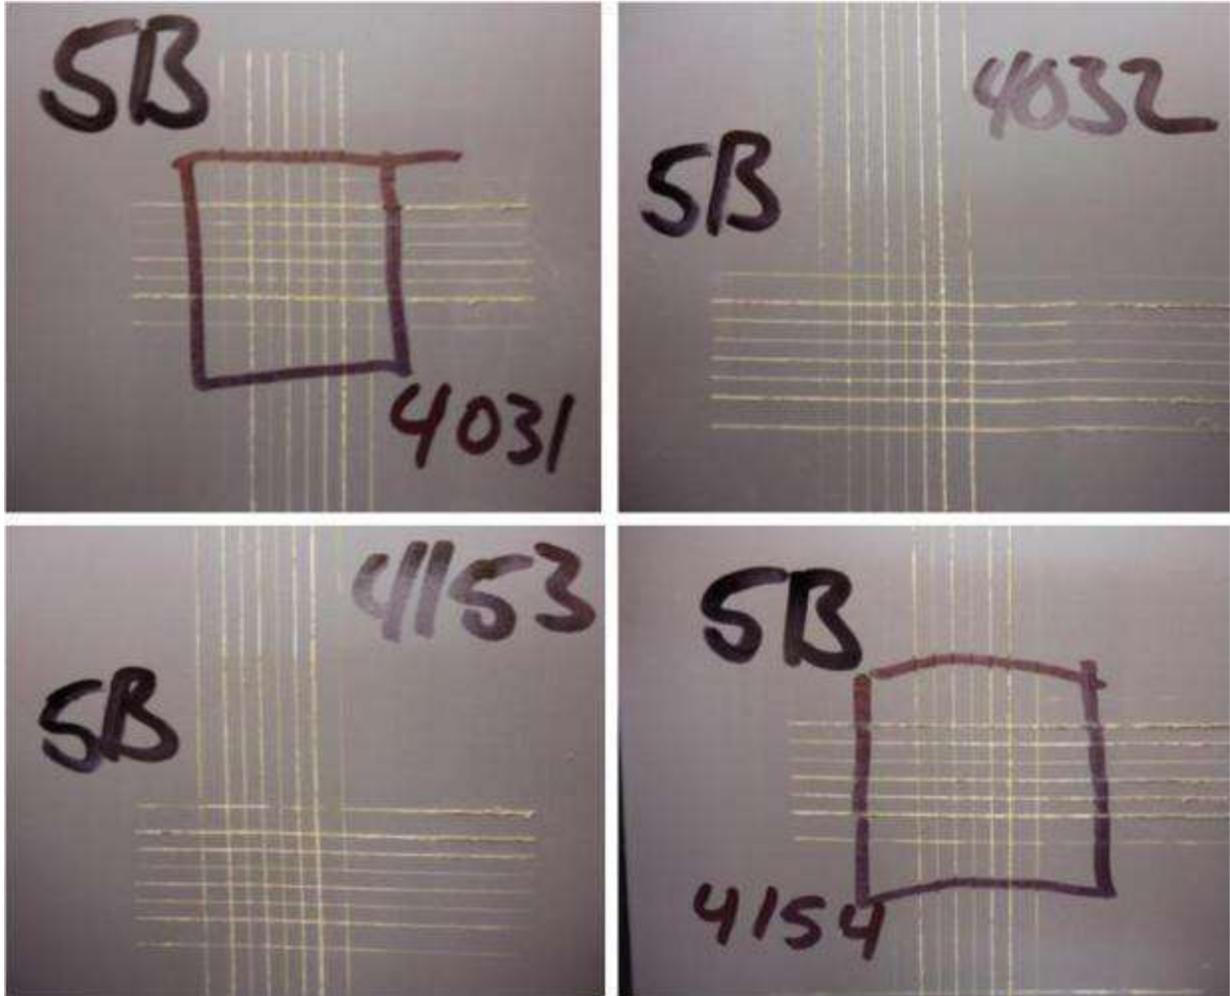


Figure 158 – Metalast HF; 6061-T6 (Top), 5052-H32 (Bottom)

3.5.4.4 Metalast HF-EPA - PPG CA7233 - PPG CA9311

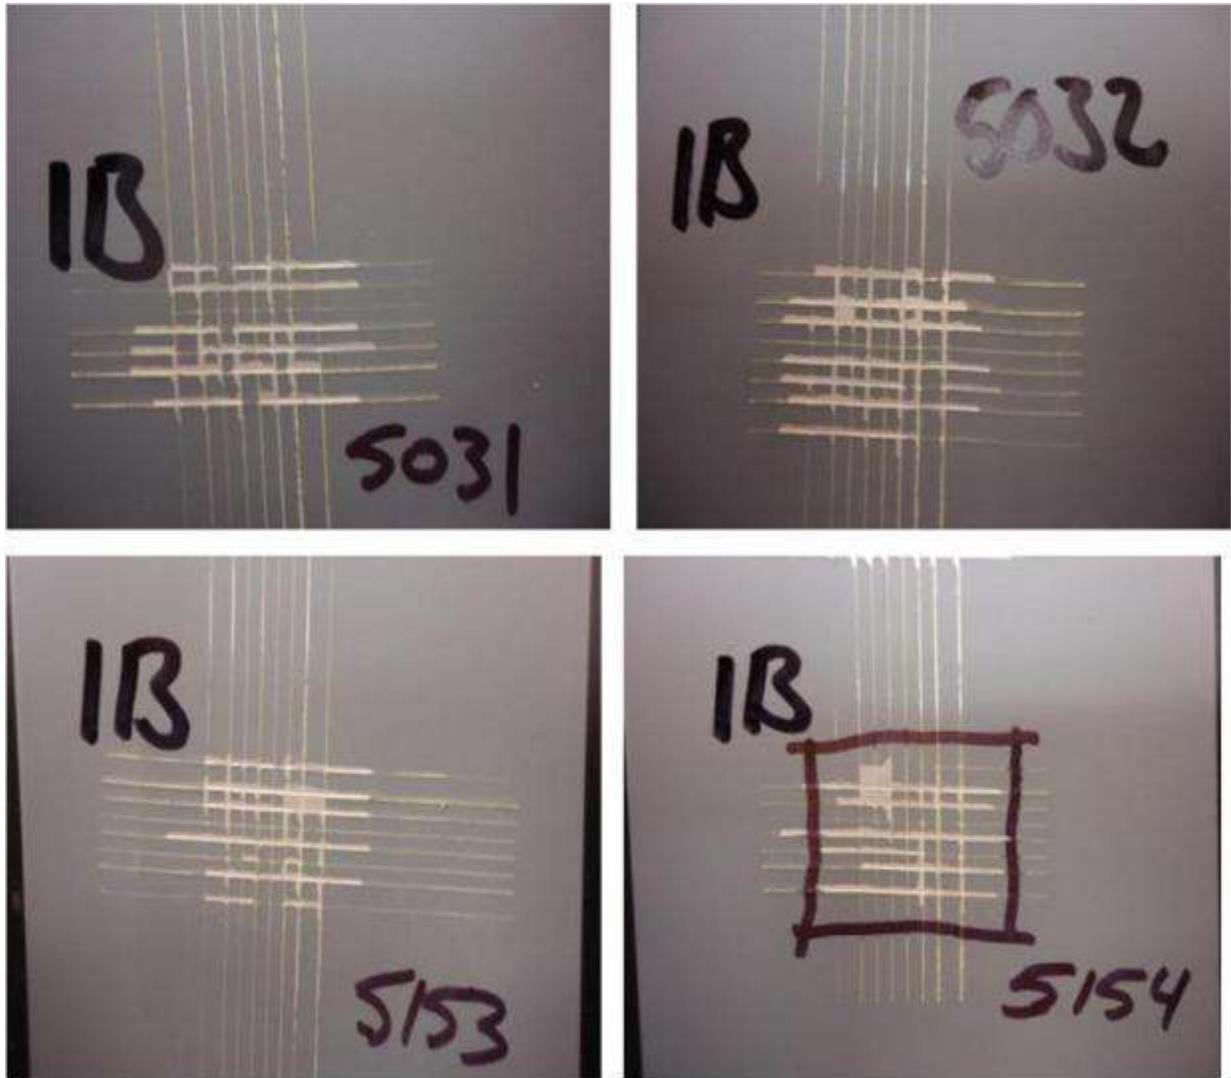


Figure 159 – Metalast HF-EPA; 6061-T6 (Top), 5052-H32 (Bottom)

3.5.4.5 SurTec 650 - PPG CA7233 - PPG CA9311

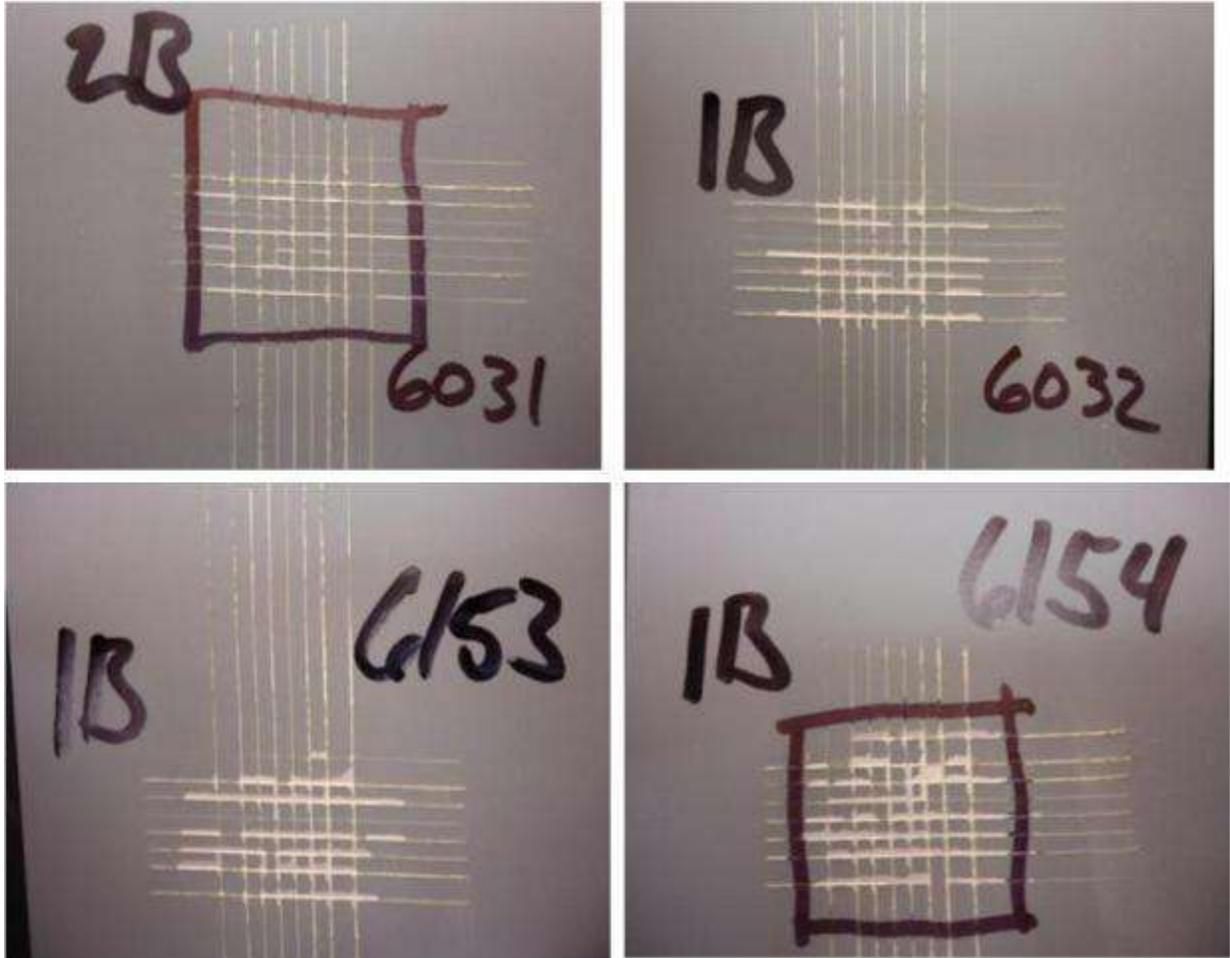


Figure 160 – SurTec 650; 6061-T6 (Top), 5052-H32 (Bottom)

3.5.4.6 SurTec 650C - PPG CA7233 - PPG CA9311

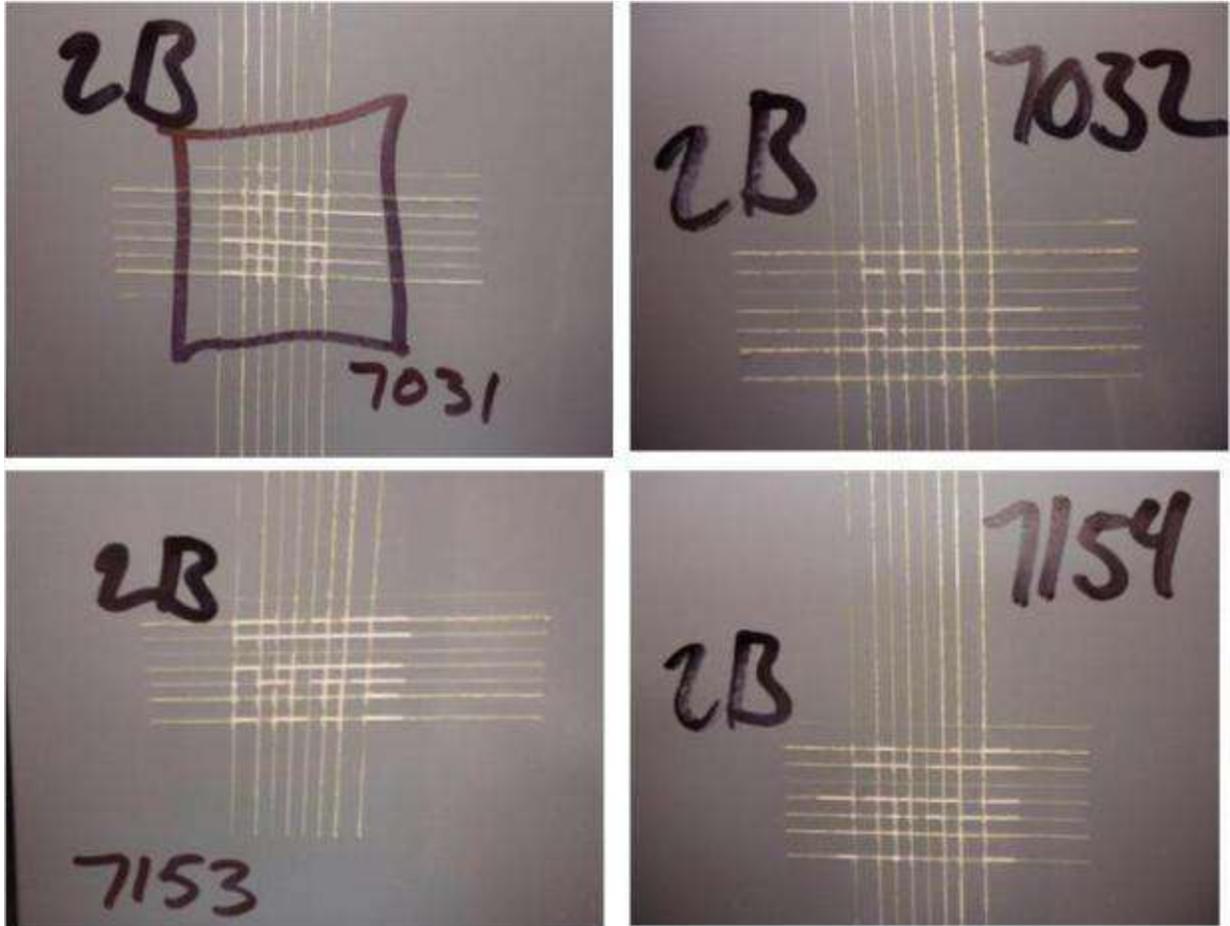


Figure 161 – SurTec 650C; 6061-T6 (Top), 5052-H32 (Bottom)

3.5.5 Test Panel Pictures with ASTM D 3359, Test Method B Ratings

3.5.5.1 Alodine T 5900 RTU – Deft-44-GN-07A - PPG CA9311

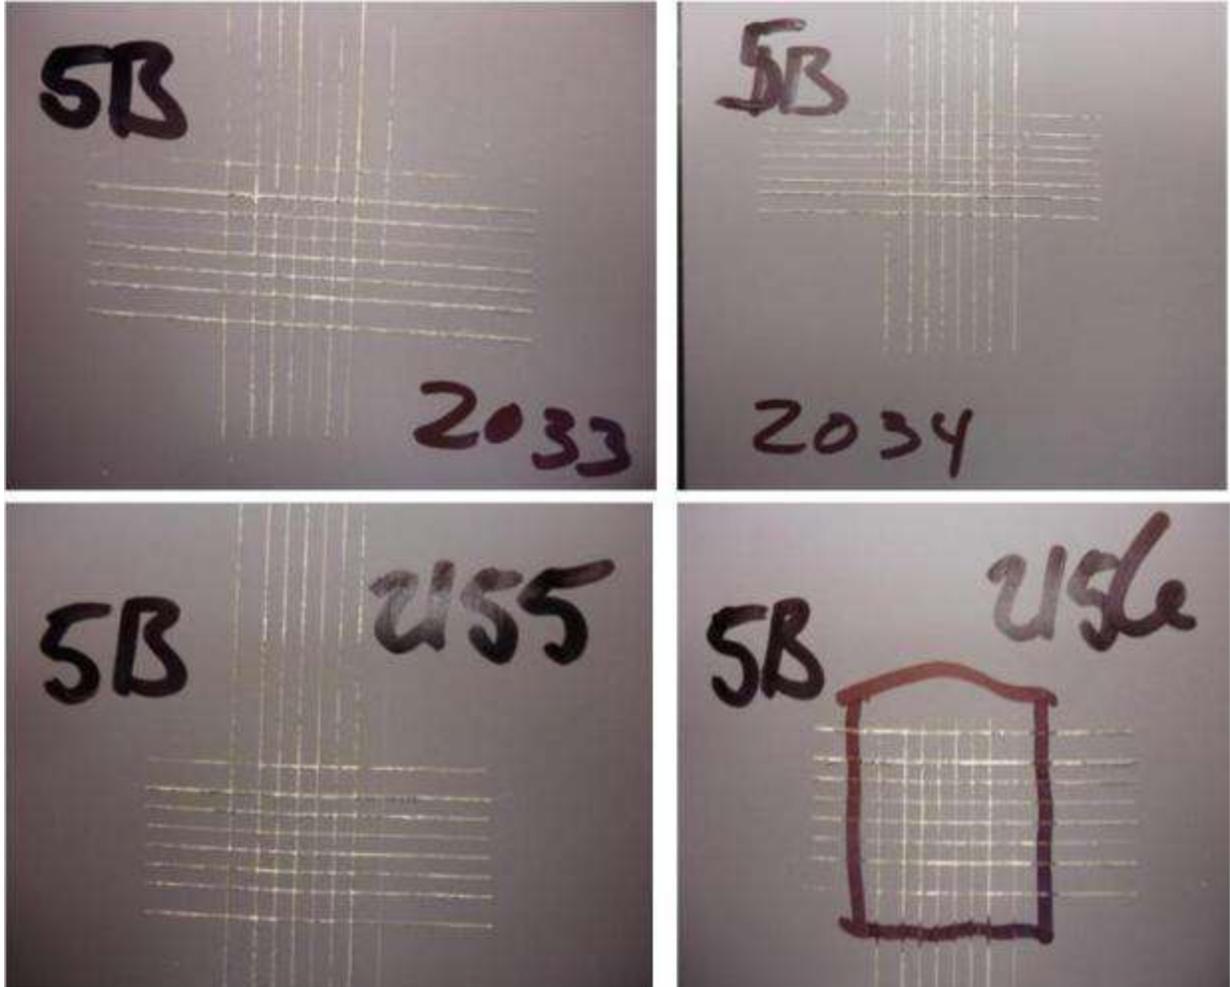


Figure 162 – Alodine T 5900 RTU; 6061-T6 (Top), 5052-H32 (Bottom)

3.5.5.2 Iridite NCP - Deft-44-GN-07A - PPG CA9311

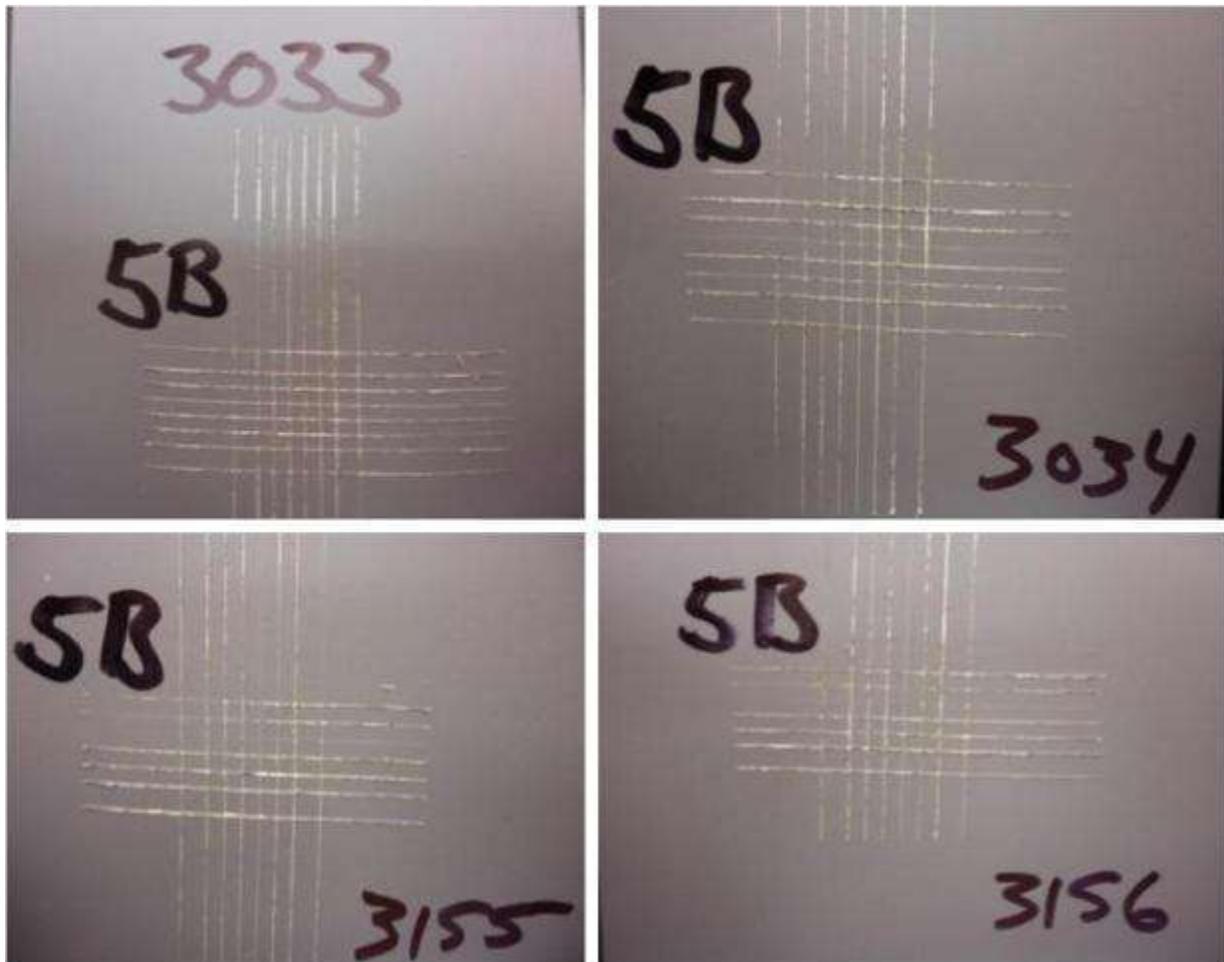


Figure 163 – Iridite NCP; 6061-T6 (Top), 5052-H32 (Bottom)

3.5.5.3 Metalast HF – Deft-44-GN-07A - PPG CA9311

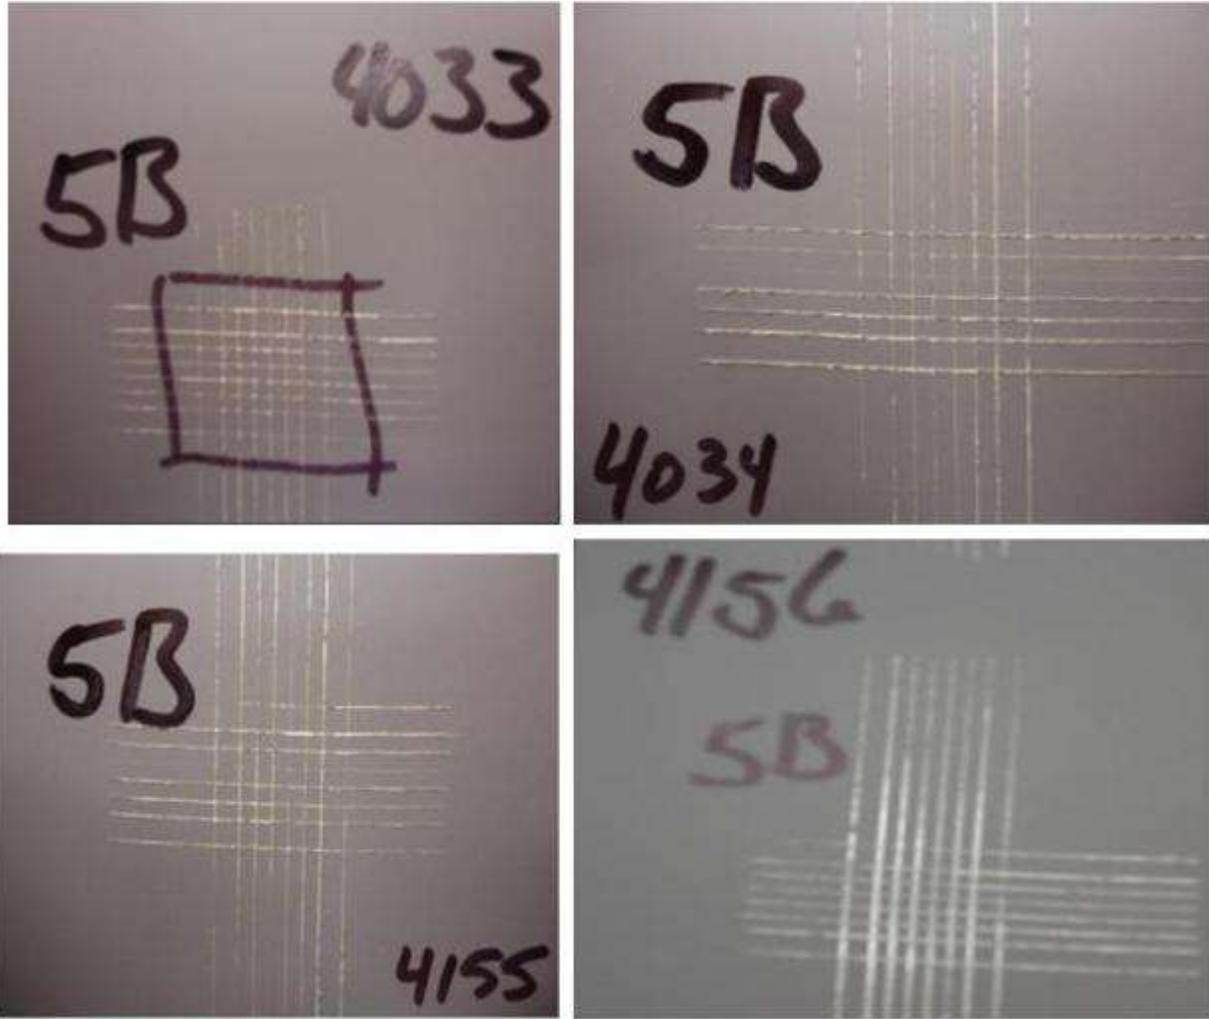


Figure 164 – Metalast HF; 6061-T6 (Top), 5052-H32 (Bottom)

3.5.5.4 Metalast HF-EPA – Deft-44-GN-07A - PPG CA9311

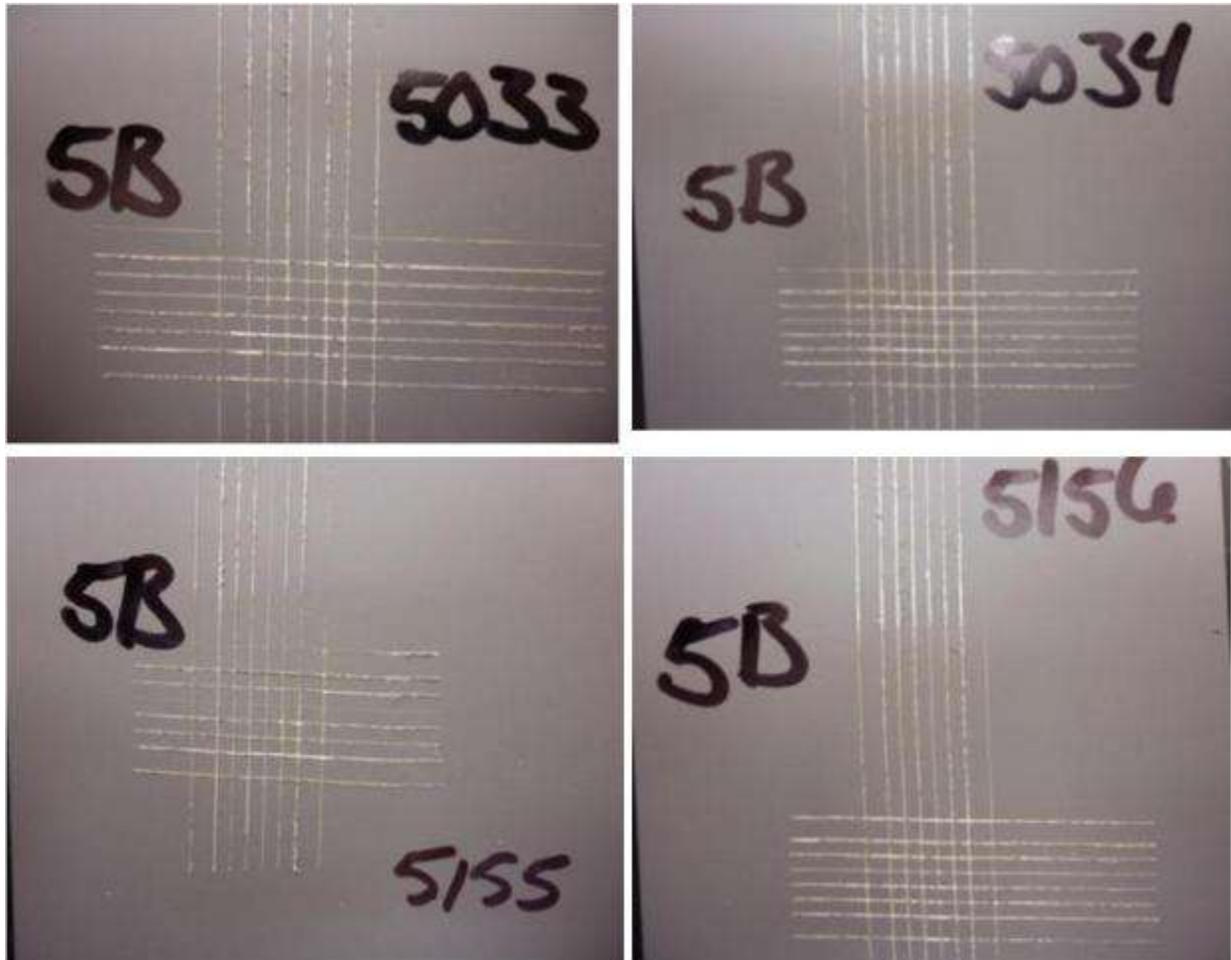


Figure 165 – Metalast HF-EPA; 6061-T6 (Top), 5052-H32 (Bottom)

3.5.5.5 SurTec 650 – Deft-44-GN-07A - PPG CA9311

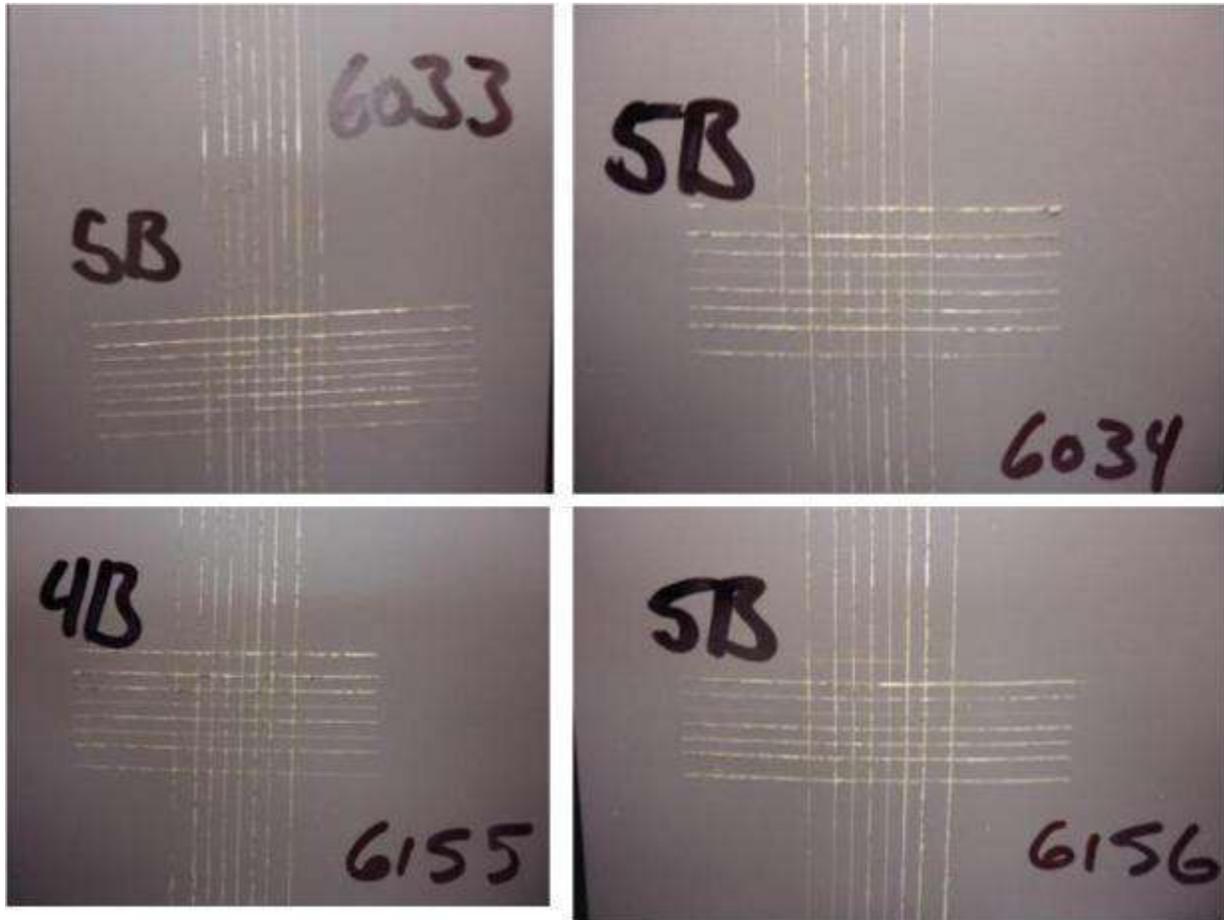


Figure 166 – SurTec 650; 6061-T6 (Top), 5052-H32 (Bottom)

3.5.5.6 SurTec 650C – Deft-44-GN-07A - PPG CA9311

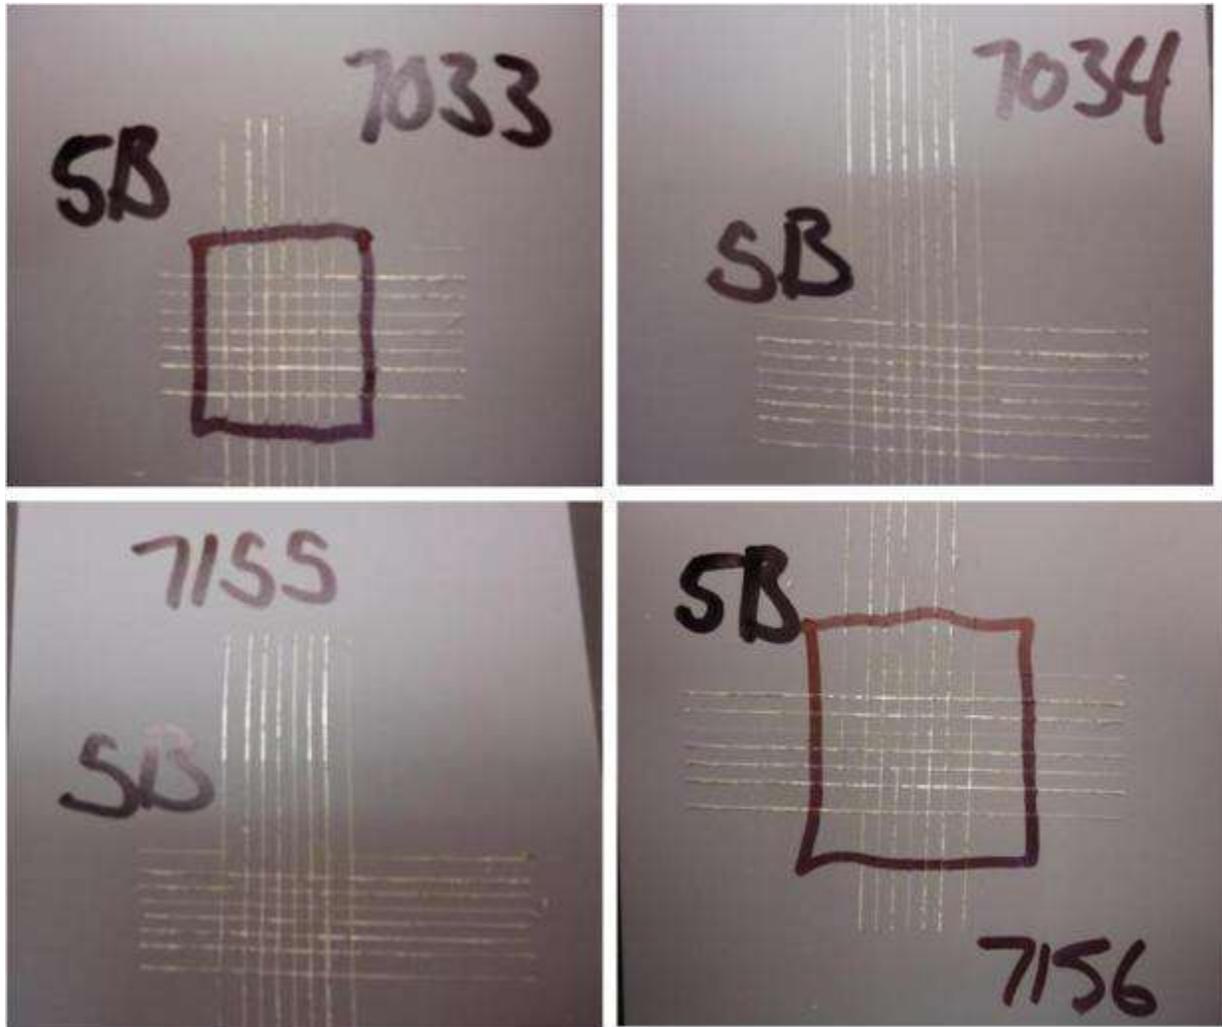


Figure 167 – SurTec 650C; 6061-T6 (Top), 5052-H32 (Bottom)

3.6 Wet Tape Paint Adhesion

This test evaluates intercoat and surface adhesion of coating systems immersed in water.

3.6.1 Test Procedure

Panels were tested for paint adhesion in accordance with FED-STD-141 (Paint, Varnish, Lacquer and Related Materials: Methods of Inspection, Sampling and Testing), Method 6301.3(Adhesion (Wet) Tape Test).

Two (2) panels per substrate / per pretreatment shall each be finished with one coat of a volatile organic compound (VOC) compliant epoxy-polyamide primer to a dry film thickness of 0.0006 to 0.0009 inch (0.6 to 0.9 mil). One was finished with one coat of epoxy primer conforming to MIL PRF 23377 (PPG CA7233) while the other was finished with one coat of epoxy primer conforming to MIL PRF 85582 (Deft 44-GN-07A). All other panels shall be allowed to dry in accordance with the primer specification.

Two immersion procedures were used for this test.

- Test panels immersed in distilled water for 24 hours
- Test panels immersed in distilled water for 96 hours at 120°F

Since a test panel size of 3"x5" is adequate for testing, the original 3"x10" test panels were sheared in half to accommodate two immersion procedures.

Once the test panels were removed from the water and dried, the test panels were scribed with two parallel scratches one inch apart with an x-cut through the middle of the parallel lines (see Figure 168). Immediately after scribing, a 1-inch wide strip of tape (the same Elcometer adhesive tape used for cross-cut tape test) is applied with the adhesive side down across the scratches. The tape was firmly pressed against the surface of the coating; a roller was used to ensure good adhesion. The tape was removed with one quick motion.

Only hexavalent chrome free pretreatments on alloys 6061-T6 and 5052-H32 were evaluated during this test. Due to the unexpected poor performance of Alodine 1600 during salt spray and cyclic corrosion testing, none of the Alodine 1600 test panels were submitted to wet tape adhesion testing for cost saving purposes. Hexavalent chrome free pretreatments on alloys 2024-T3 and 7075-T73 were also omitted from wet tape adhesion testing due to unexpected poor performance during salt spray and cyclic corrosion testing.

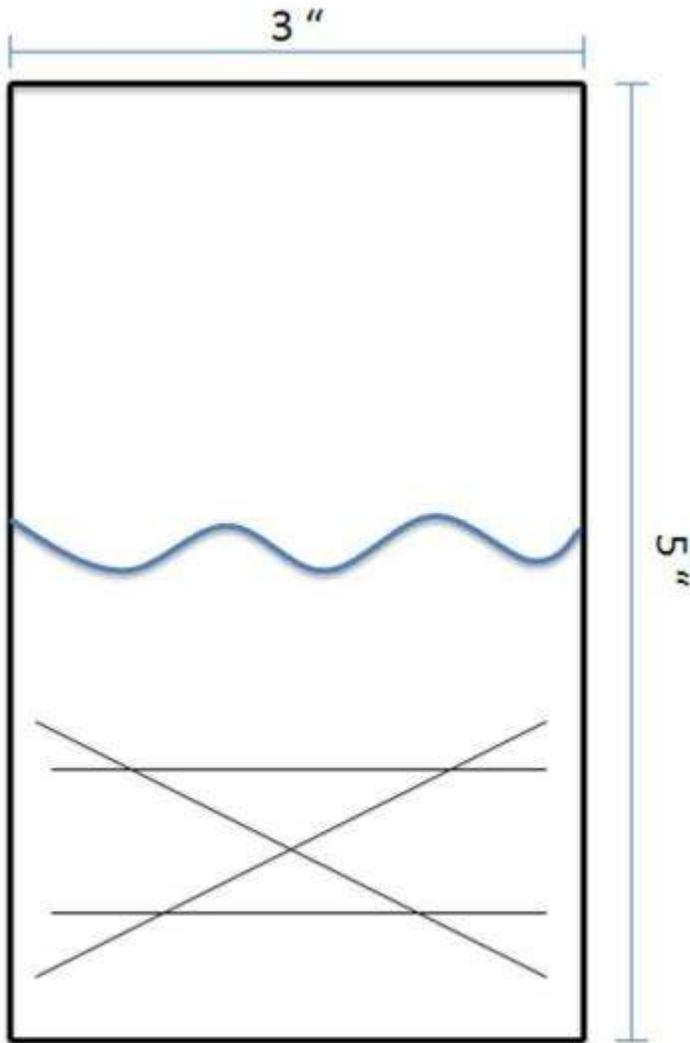


Figure 168 – Wet Tape Adhesion Test Panel

3.6.2 Evaluation Procedure

Panels were evaluated per ASTM D 3359, Test Method A, X-Cut Tape Test per the following criteria:

- 5A No peeling or removal
- 4A Trace peeling or removal along incisions or at their intersection
- 3A Jagged removal along incisions up to 1.6 mm (1/16 in.) on either side
- 2A Jagged removal along most of incisions up to 3.2 mm (1/8 in.) on either side
- 1A Removal from most of the area of the X under the tape
- 0A Removal beyond the area of the X

3.6.3 Test Results – Wet Tape Adhesion, 24 Hour Immersion

Test results from wet tape adhesion testing, 24 hour immersion, are contained in Figure 169 and Figure 170. Test panels with PPG CA7233 primer had acceptable ratings (4A or better) for most

of the hexavalent chrome free pretreatments on 5052-H32 and 6061-T6 test panels. Only Metalast HF-EPA with PPG CA7233 primer rated below 4A on 5052-H32 and 6061-T6 test panels. Results for Alodine T 5900 RTU with PPG CA7233 primer were mixed; a perfect rating was recorder for the 5052-H32 test panel while a failing rating of 3A was recorded for the 6061-T6 test panel. Test panels with Deft 44-GN-07A primer were rated as flawless across all test panels regardless of pretreatment or alloy combination. See the comment in section 3.5.3 regarding coating thickness of PPG CA7233.

Pretreatment	Alloy	Panel #	Evaluation
Alodine T 5900 RTU	6061-T6	2035	3A
	5052-H32	2157	5A
Iridite NCP	6061-T6	3035	5A
	5052-H32	3157	5A
Metalast HF	6061-T6	4035	5A
	5052-H32	4157	5A
Metalast HF-EPA	6061-T6	5035	3A
	5052-H32	5157	3A
SurTec 650	6061-T6	6035	5A
	5052-H32	6157	4A
SurTec 650C	6061-T6	7035	4A
	5052-H32	7157	4A

Figure 169 - Wet Tape Adhesion Test Results, 24 Hour; Primer (MIL-PRF-23377) - PPG CA7233

Pretreatment	Alloy	Panel #	Evaluation
Alodine T 5900 RTU	6061-T6	2036	5A
	5052-H32	2158	5A
Iridite NCP	6061-T6	3036	5A
	5052-H32	3158	5A
Metalast HF	6061-T6	4036	5A
	5052-H32	4158	5A
Metalast HF-EPA	6061-T6	5036	5A
	5052-H32	5158	5A
SurTec 650	6061-T6	6036	5A
	5052-H32	6158	5A
SurTec 650C	6061-T6	7036	5A
	5052-H32	7158	5A

Figure 170 - Wet Tape Adhesion Test Results, 24 Hour; Test Results; Primer (MIL-PRF-85582) - Deft 44-GN-07A

3.6.4 Test Panel Pictures - Wet Tape Adhesion, 24 Hour Immersion

3.6.4.1 Alodine T 5900 RTU - PPG CA7233



Figure 171 – Alodine T 5900 RTU; 6061-T6 (Left), 5052-H32 (Right)

3.6.4.2 Iridite NCP - PPG CA7233



Figure 172 – Iridite NCP - ; 6061-T6 (Left), 5052-H32 (Right)

3.6.4.3 Metalast HF - PPG CA7233

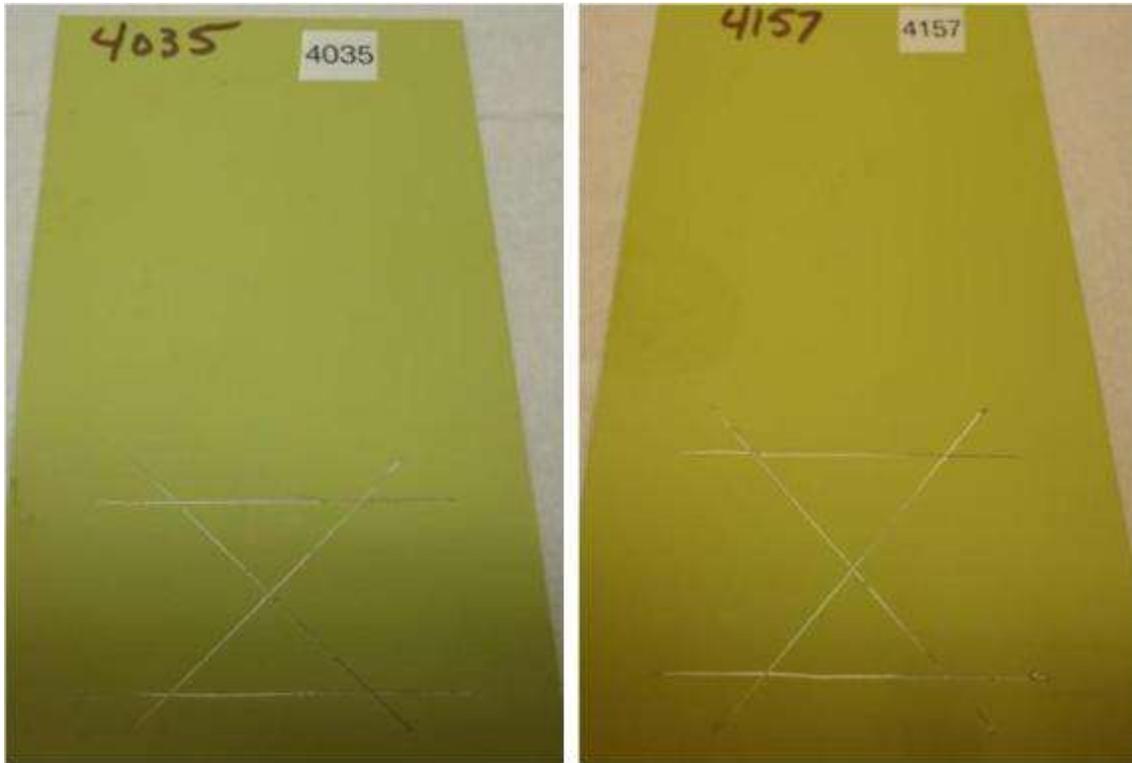


Figure 173 – Metalast HF; 6061-T6 (Left), 5052-H32 (Right)

3.6.4.4 Metalast HF-EPA - PPG CA7233



Figure 174 – Metalast HF-EPA; 6061-T6 (Left), 5052-H32 (Right)

3.6.4.5 SurTec 650 - PPG CA7233

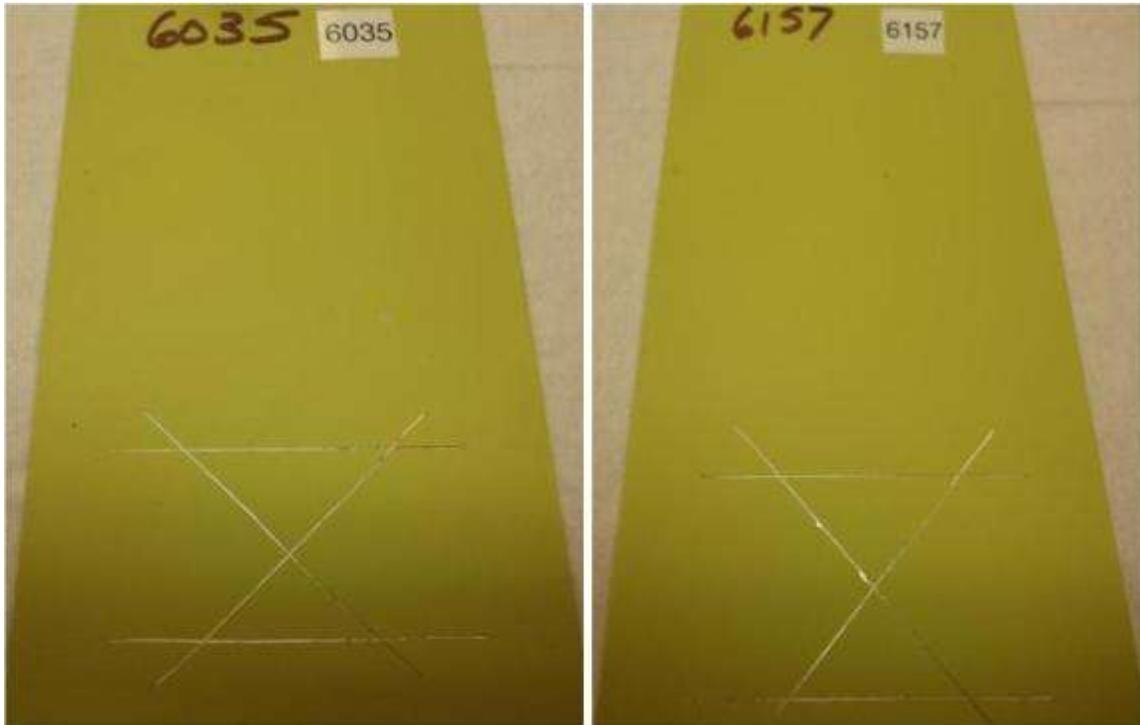


Figure 175 – SurTec 650; 6061-T6 (Left), 5052-H32 (Right)

3.6.4.6 SurTec 650C - PPG CA7233



Figure 176 – SurTec 650C; 6061-T6 (Left), 5052-H32 (Right)

3.6.5 Test Panel Pictures - Wet Tape Adhesion, 24 Hour Immersion

3.6.5.1 Alodine T 5900 RTU – Deft 44-GN-07A

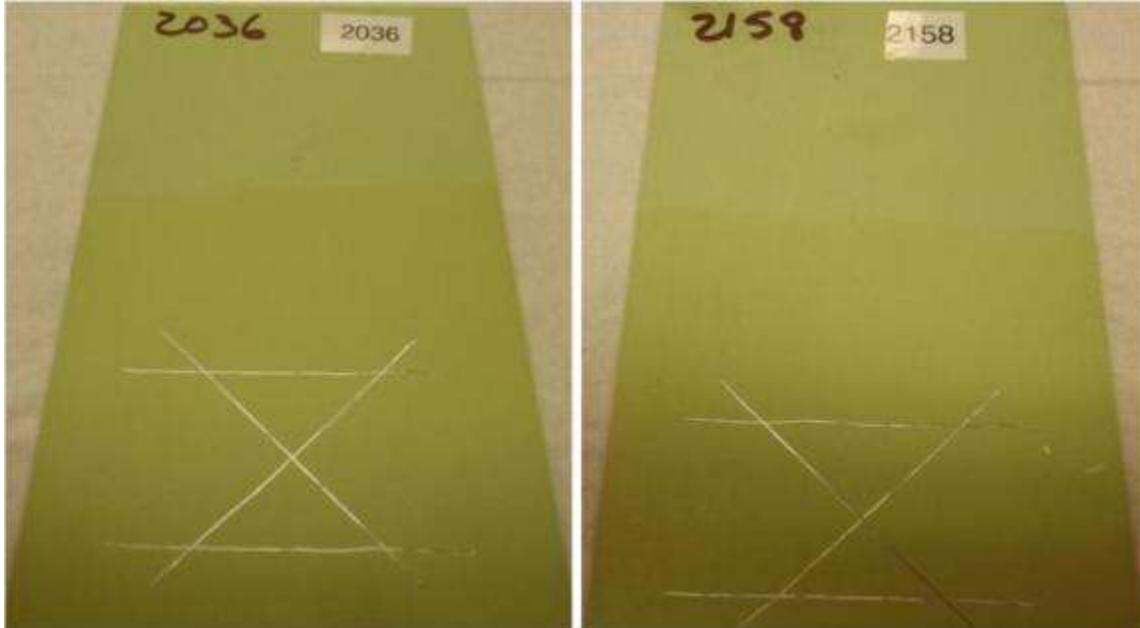


Figure 177 – Alodine T 5900 RTU; 6061-T6 (Left), 5052-H32 (Right)

3.6.5.2 Iridite NCP - Deft 44-GN-07A



Figure 178 – Iridite NCP; 6061-T6 (Left), 5052-H32 (Right)

3.6.5.3 Metalast HF - Deft 44-GN-07A

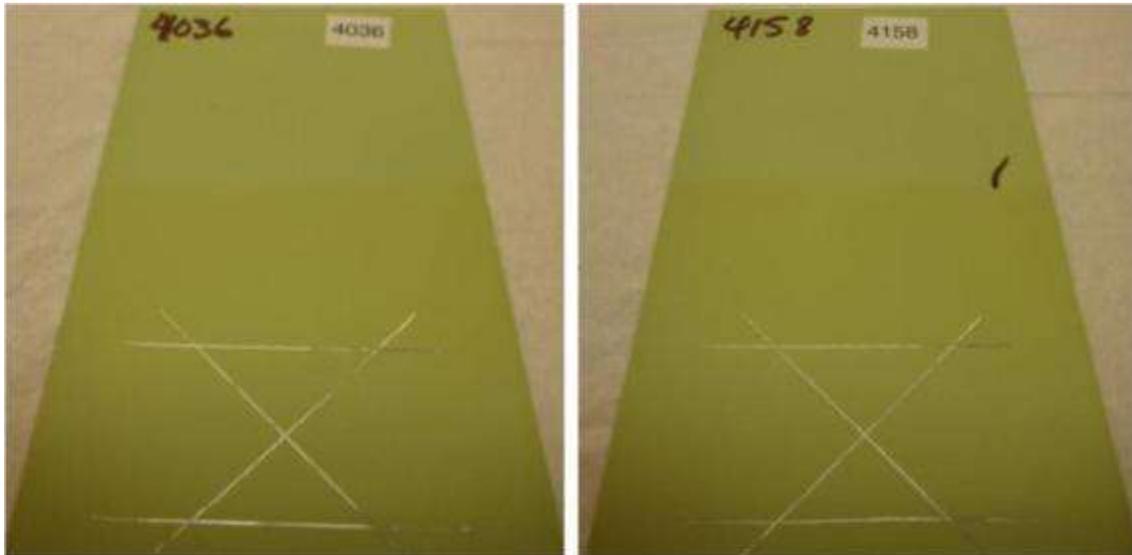


Figure 179 – Metalast HF; 6061-T6 (Left), 5052-H32 (Right)

3.6.5.4 Metalast HF-EPA - Deft 44-GN-07A

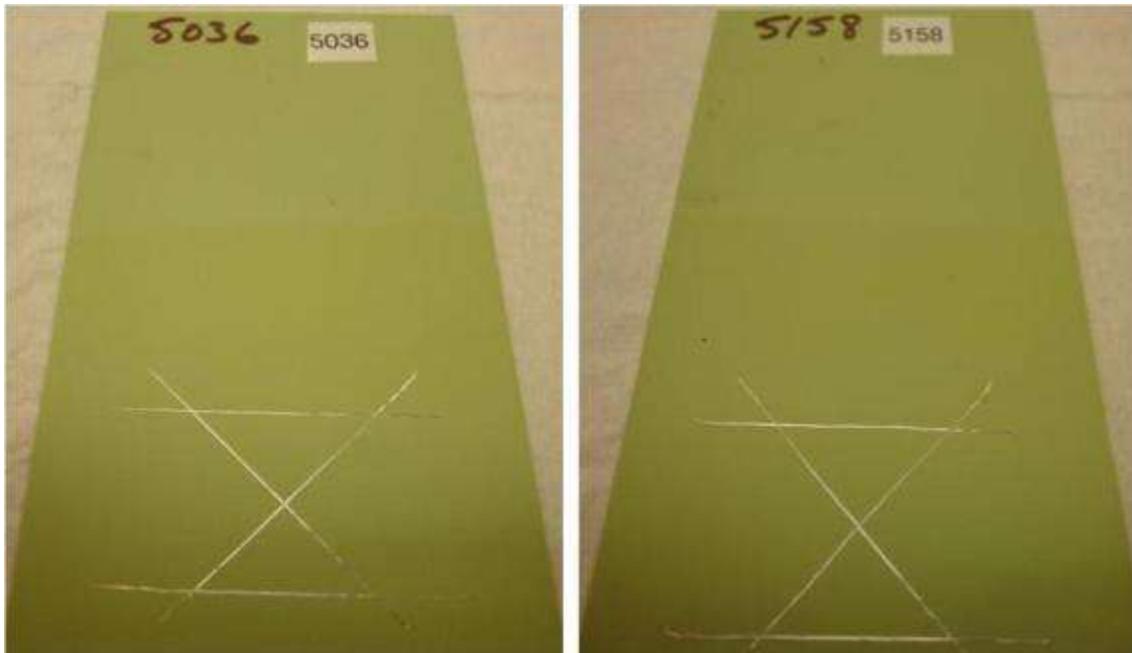


Figure 180 – Metalast HF-EPA; 6061-T6 (Left), 5052-H32 (Right)

3.6.5.5 SurTec 650 - Deft 44-GN-07A



Figure 181 - SurTec 650; 6061-T6 (Left), 5052-H32 (Right)

3.6.5.6 SurTec 650C - Deft 44-GN-07A

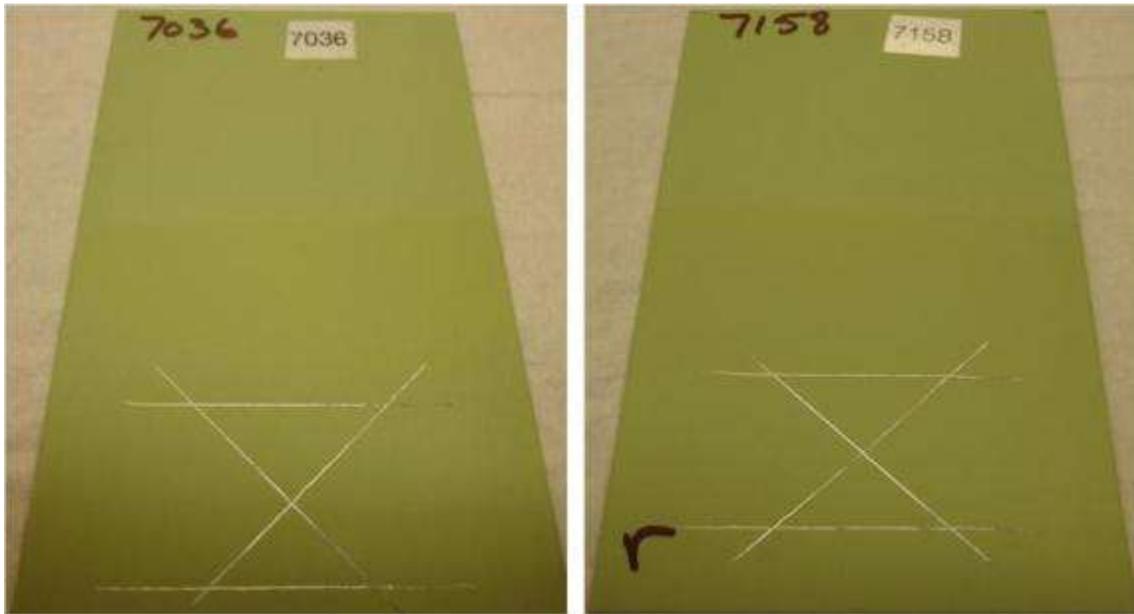


Figure 182 - SurTec 650C; 6061-T6 (Left), 5052-H32 (Right)

3.6.6 Test Results – Wet Tape Adhesion, 96 Hour Immersion at 120°F

Test results from wet tape adhesion testing, 96 hour immersion at 120°F, are contained in Figure 183 and Figure 184. Only two hexavalent chrome free pretreatments, Iridite NCP and Metalast HF, with PPG CA7233 primer received a perfect 5A rating on 5052-H32 and 6061-T6 test panels. Results for SurTec 650 with PPG CA7233 primer were mixed; a perfect rating was recorded for the 6061-T6 test panel while a failing rating of 3A was recorded for the 5052-H32 test panel. Alodine T 5900 RTU, Metalast HF-EPA, and SurTec 650 with PPG CA7233 primer received a failing rating of 3A on both (5052-H32 and 6061-T6) test panels. Test panels with Deft 44-GN-07A primer were rated as flawless across all test panels regardless of pretreatment or alloy combination. See the comment in section 3.5.3 regarding coating thickness of PPG CA7233.

Pretreatment	Alloy	Panel #	Evaluation
Alodine T 5900 RTU	6061-T6	2035	3A
	5052-H32	2157	3A
Iridite NCP	6061-T6	3035	5A
	5052-H32	3157	5A
Metalast HF	6061-T6	4035	5A
	5052-H32	4157	5A
Metalast HF-EPA	6061-T6	5035	3A
	5052-H32	5157	3A
SurTec 650	6061-T6	6035	5A
	5052-H32	6157	3A
SurTec 650C	6061-T6	7035	3A
	5052-H32	7157	3A

Figure 183 - Wet Tape Adhesion Test Results, 96 Hour @ 120°F; Primer (MIL-PRF-23377) - PPG CA7233

Pretreatment	Alloy	Panel #	Evaluation
Alodine T 5900 RTU	6061-T6	2036	5A
	5052-H32	2158	5A
Iridite NCP	6061-T6	3036	5A
	5052-H32	3158	5A
Metalast HF	6061-T6	4036	5A
	5052-H32	4158	5A
Metalast HF-EPA	6061-T6	5036	5A
	5052-H32	5158	5A
SurTec 650	6061-T6	6036	5A
	5052-H32	6158	5A
SurTec 650C	6061-T6	7036	5A
	5052-H32	7158	5A

**Figure 184 - Wet Tape Adhesion Test Results, 96 Hour @ 120°F; Primer (MIL-PRF-85582)
- Deft 44-GN-07A**

3.6.7 Test Panel Pictures - Wet Tape Adhesion, 96 Hour Immersion @ 120°F

3.6.7.1 Alodine T 5900 RTU – PPG CA7233

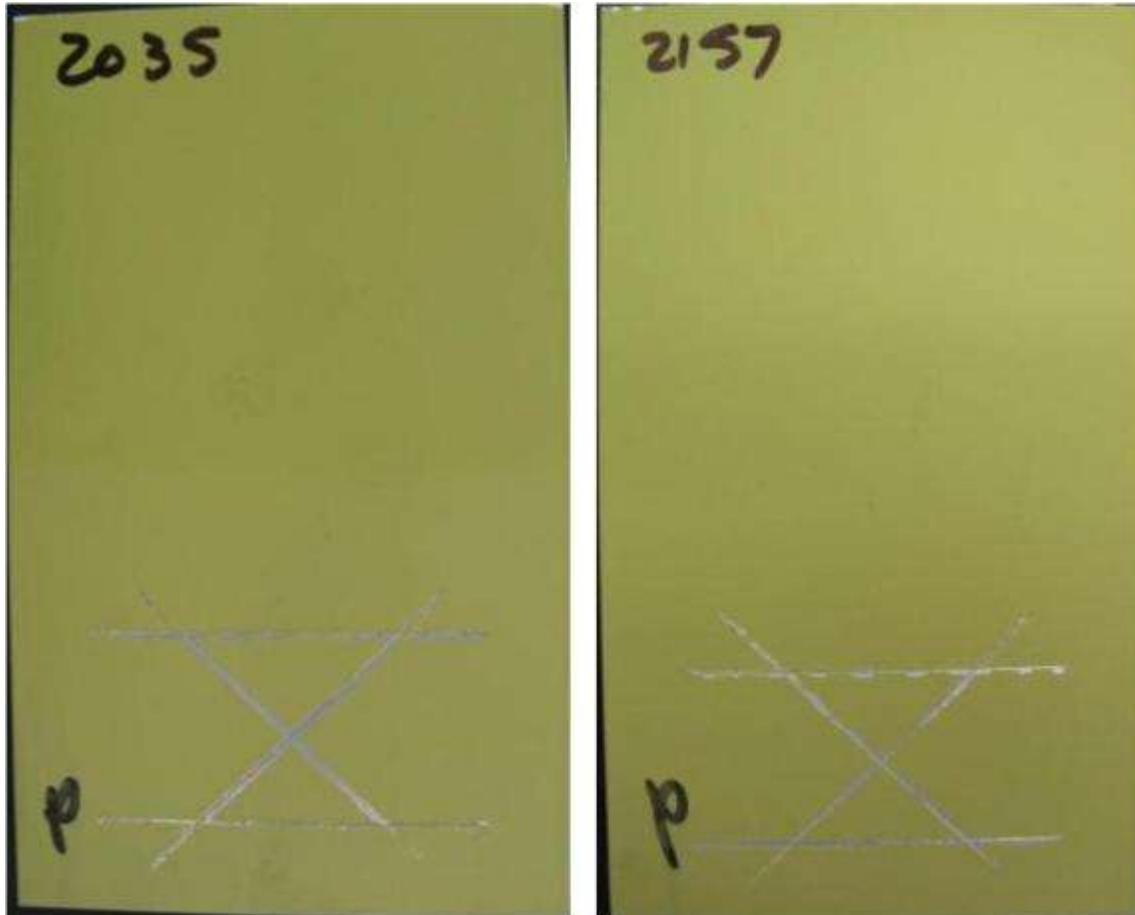


Figure 185 – Alodine T 5900 RTU; 6061-T6 (Left), 5052-H32 (Right)

3.6.7.2 Iridite NCP - PPG CA7233

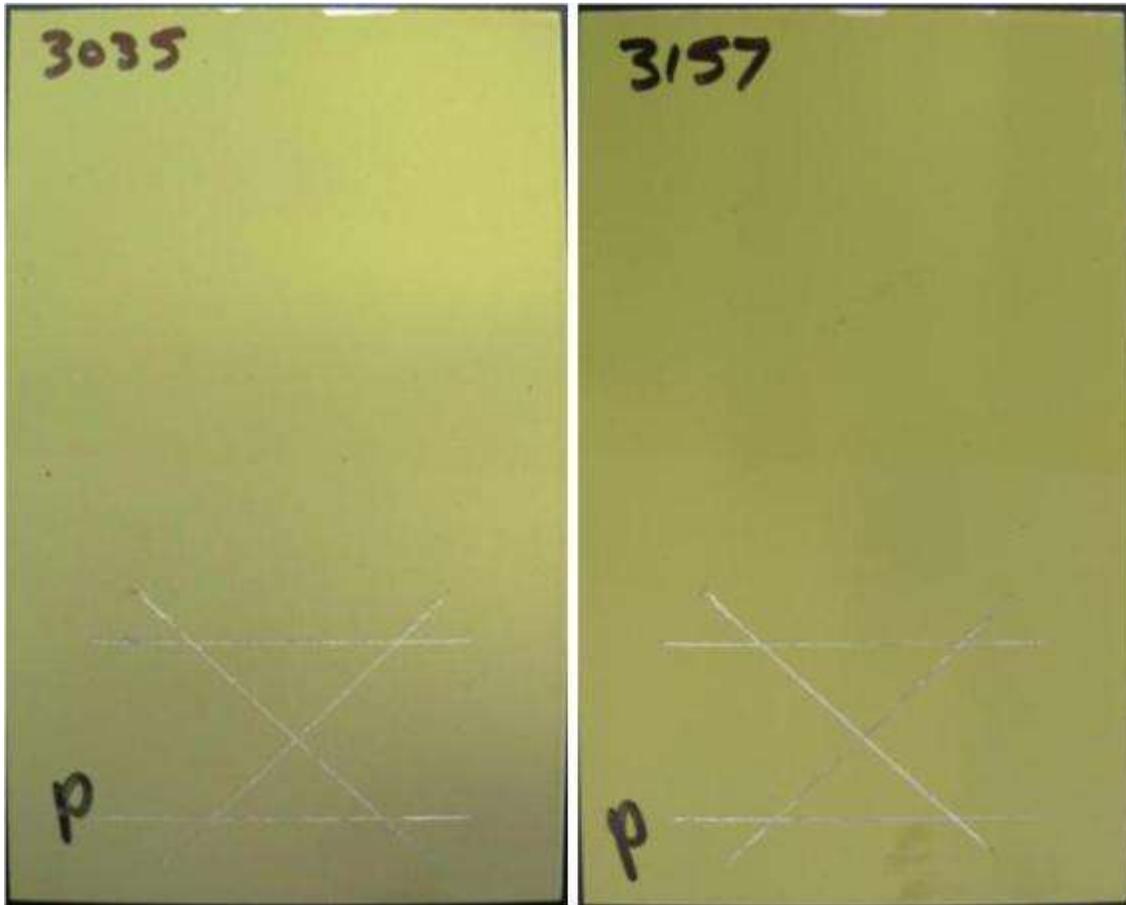


Figure 186 – Iridite NCP; 6061-T6 (Left), 5052-H32 (Right)

3.6.7.3 Metalast HF - PPG CA7233

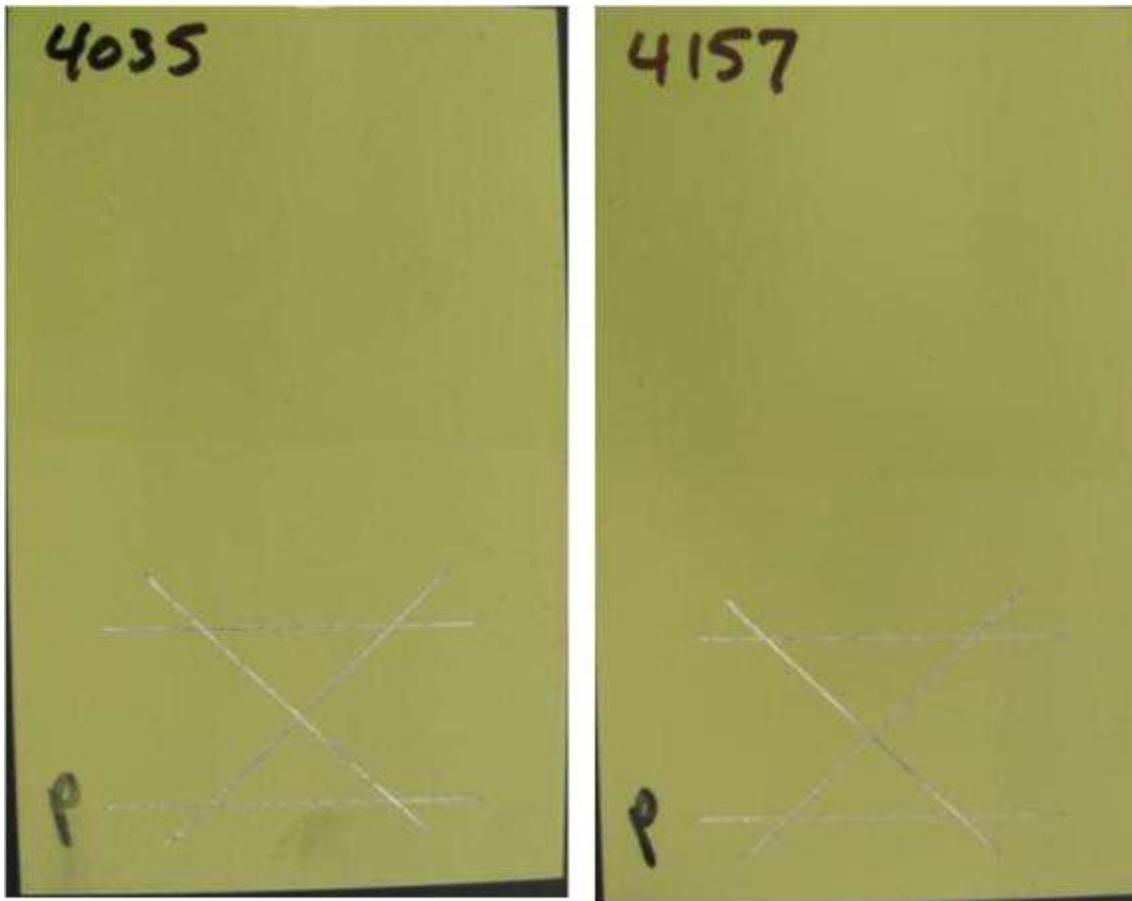


Figure 187 – Metalast HF; 6061-T6 (Left), 5052-H32 (Right)

3.6.7.4 Metalast HF-EPA - PPG CA7233

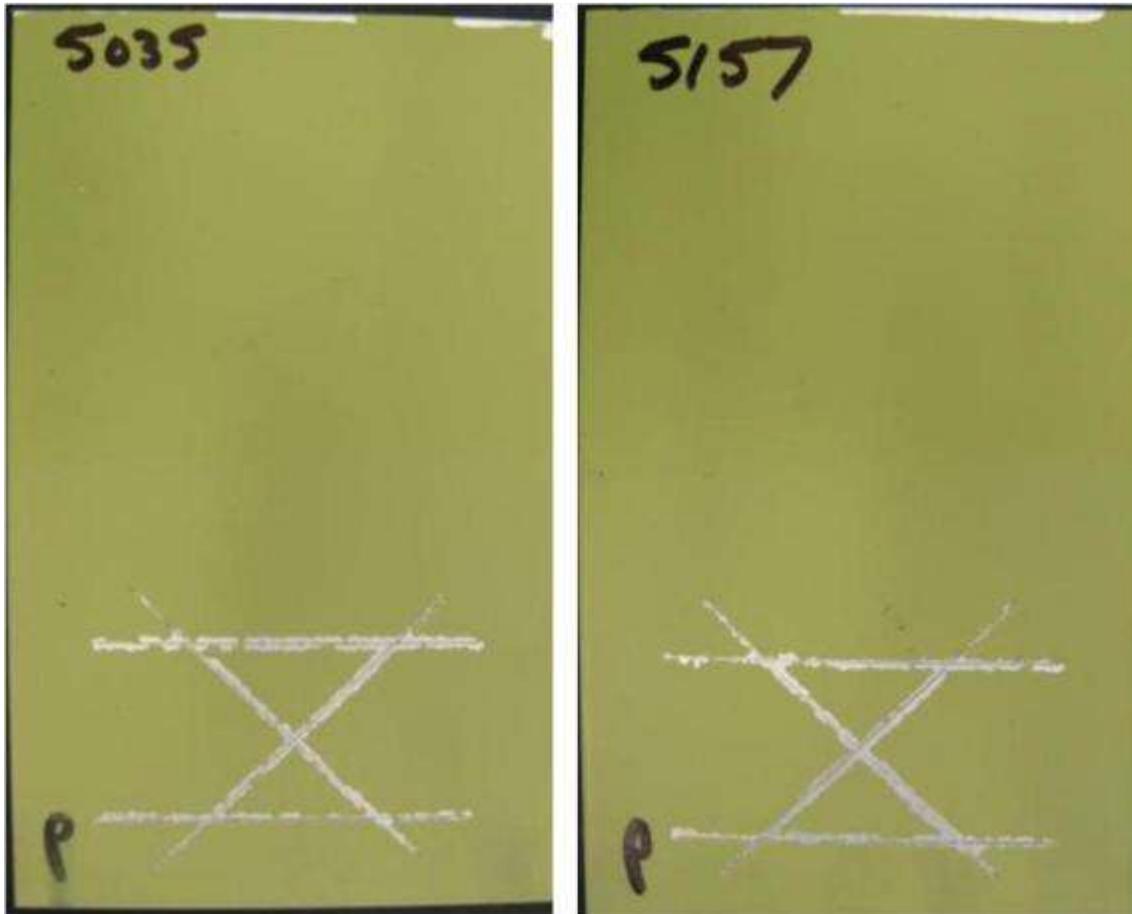


Figure 188 – Metalast HF-EPA; 6061-T6 (Left), 5052-H32 (Right)

3.6.7.5 SurTec 650 - PPG CA7233

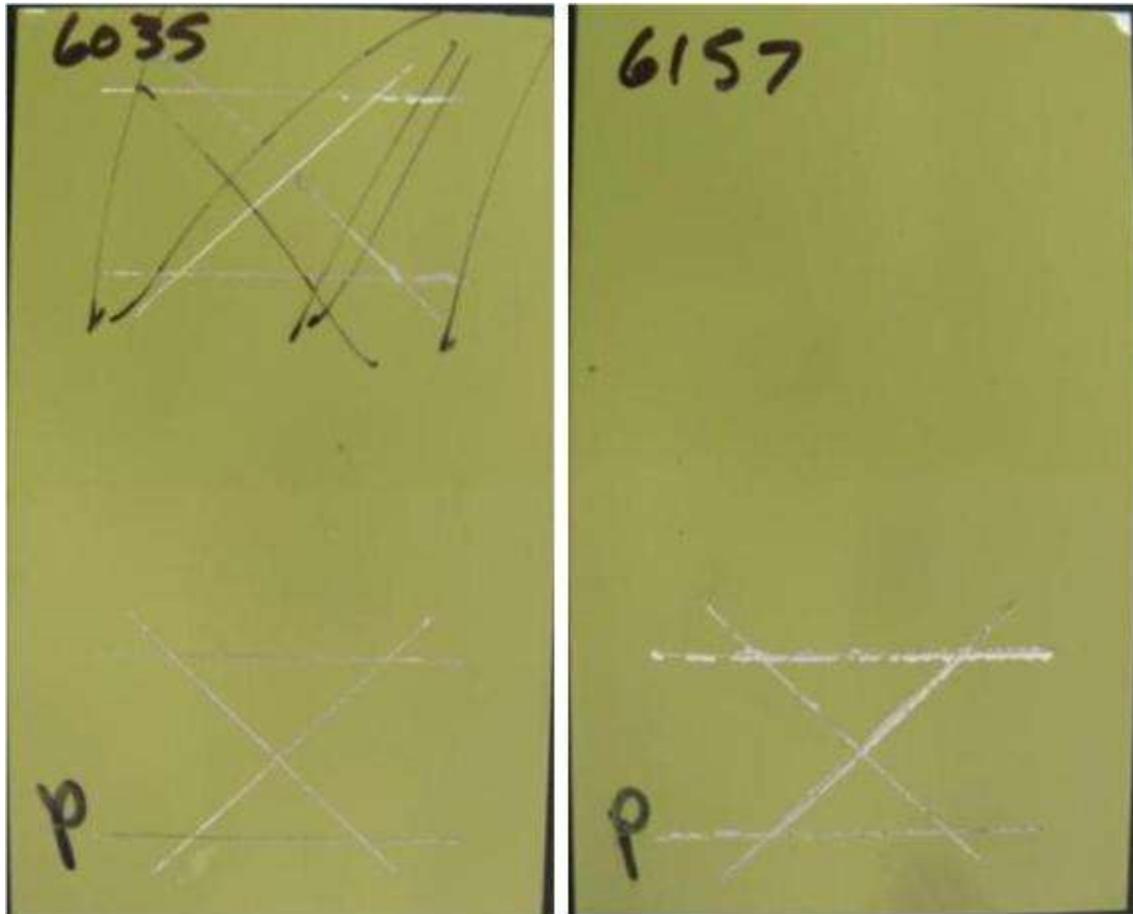


Figure 189 – SurTec 650; 6061-T6 (Left), 5052-H32 (Right)

3.6.7.6 SurTec 650C - PPG CA7233

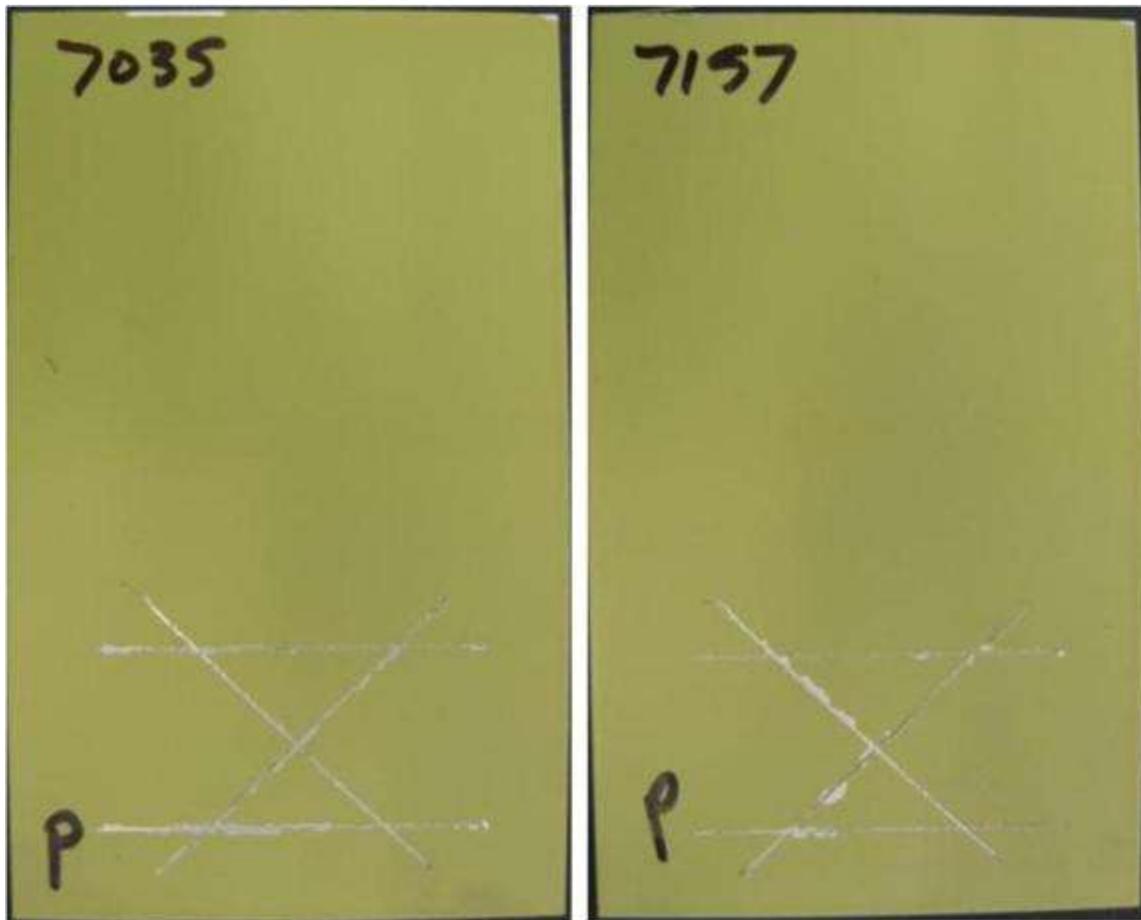


Figure 190 – SurTec 650C; 6061-T6 (Left), 5052-H32 (Right)

3.6.8 Test Panel Pictures - Wet Tape Adhesion, 96 Hour Immersion @ 120°F

3.6.8.1 Alodine T 5900 RTU – Deft 44-GN-07A

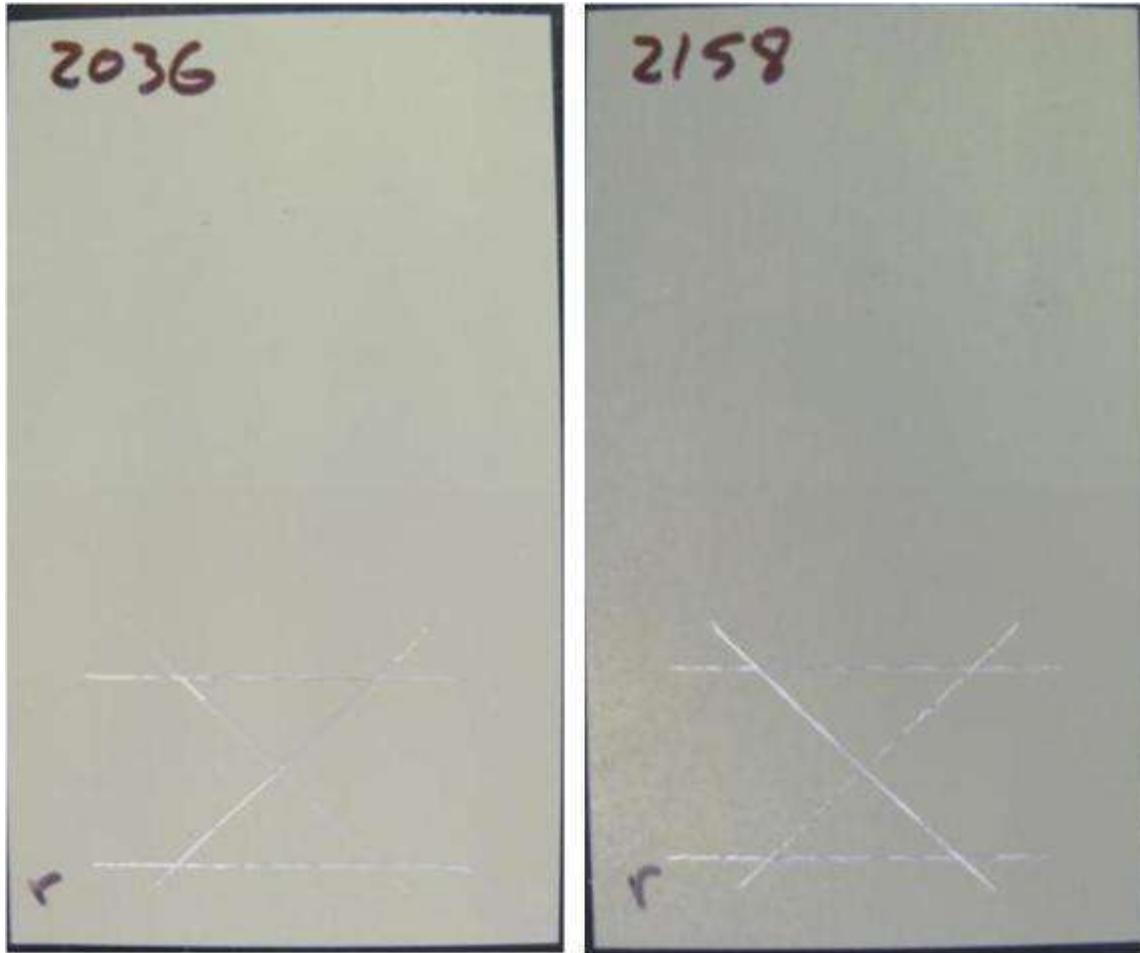


Figure 191 – Alodine T 5900 RTU; 6061-T6 (Left), 5052-H32 (Right)

3.6.8.2 Iridite NCP - Deft 44-GN-07A

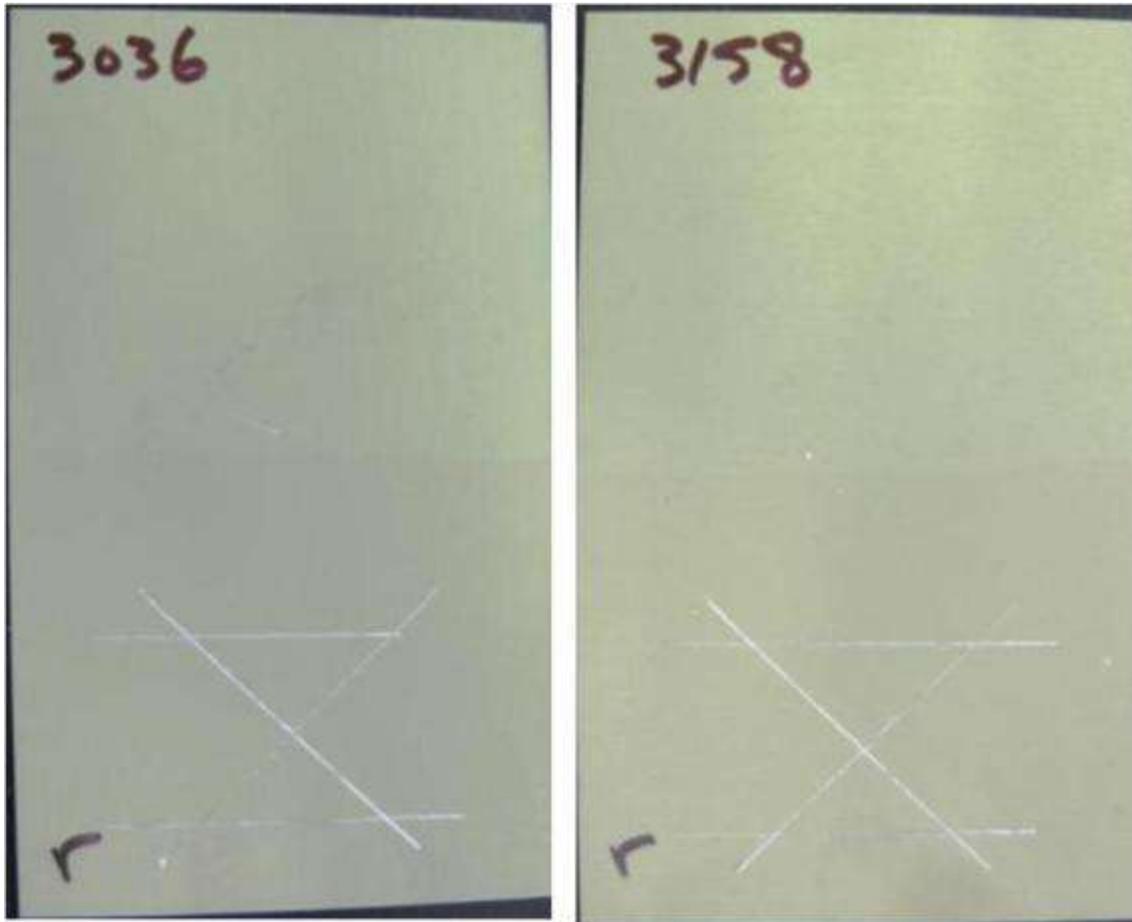


Figure 192 – Iridite NCP; 6061-T6 (Left), 5052-H32 (Right)

3.6.8.3 Metalast HF - Deft 44-GN-07A

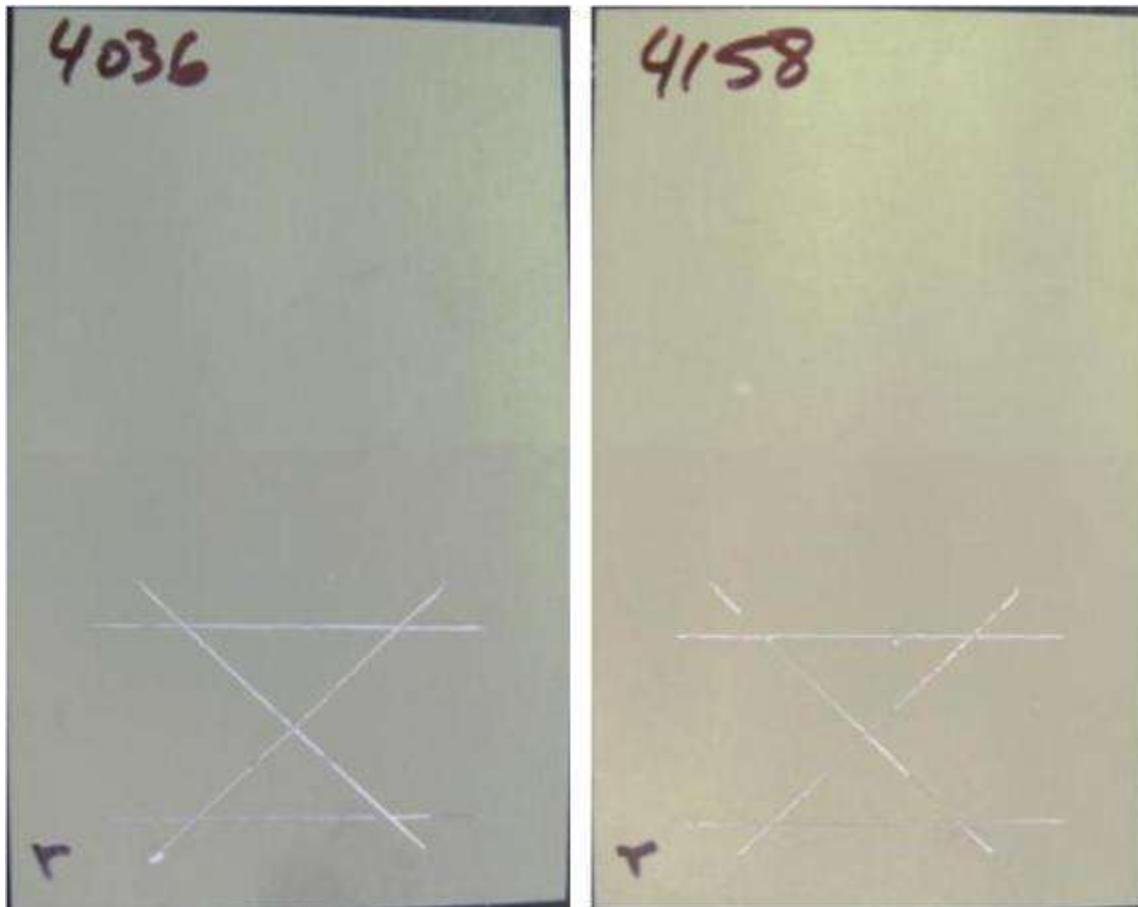


Figure 193 – Metalast HF; 6061-T6 (Left), 5052-H32 (Right)

3.6.8.4 Metalast HF-EPA - Defect 44-GN-07A

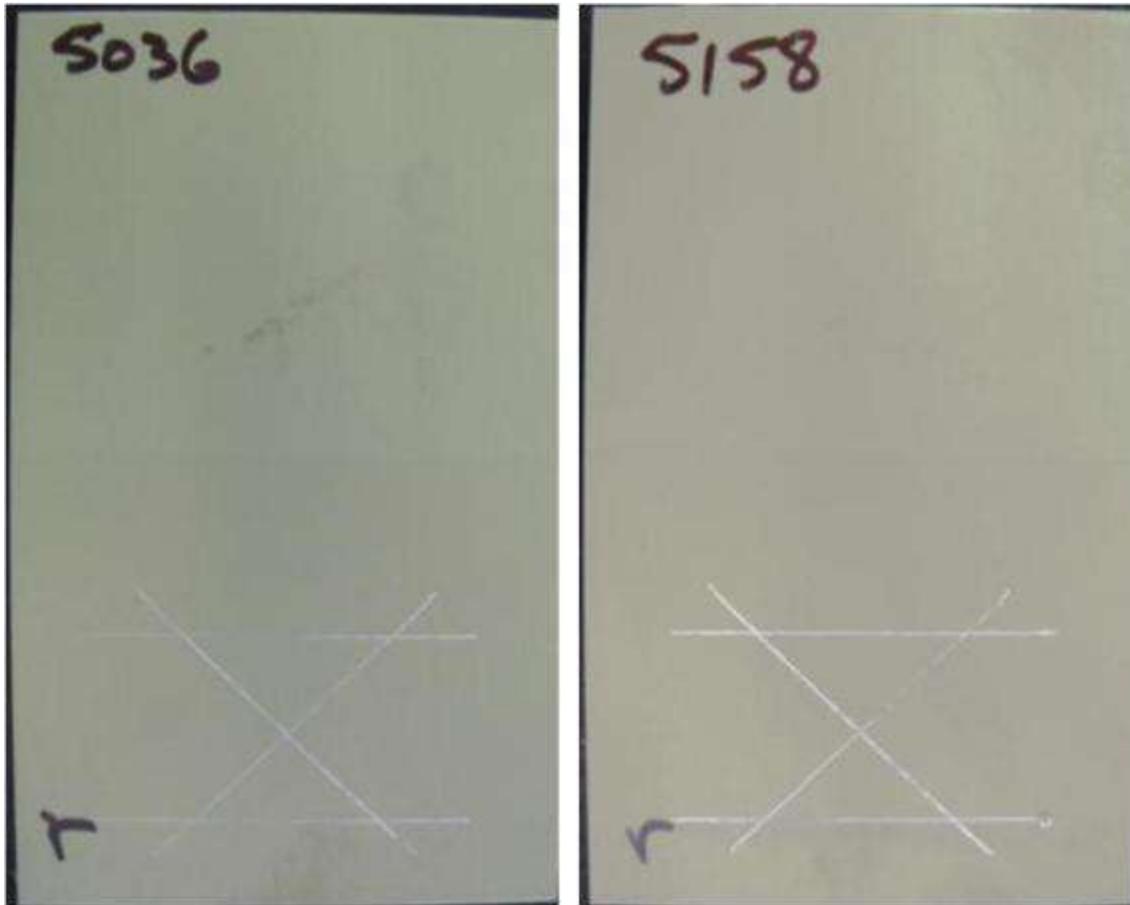


Figure 194 – Metalast HF-EPA; 6061-T6 (Left), 5052-H32 (Right)

3.6.8.5 SurTec 650 - Deft 44-GN-07A

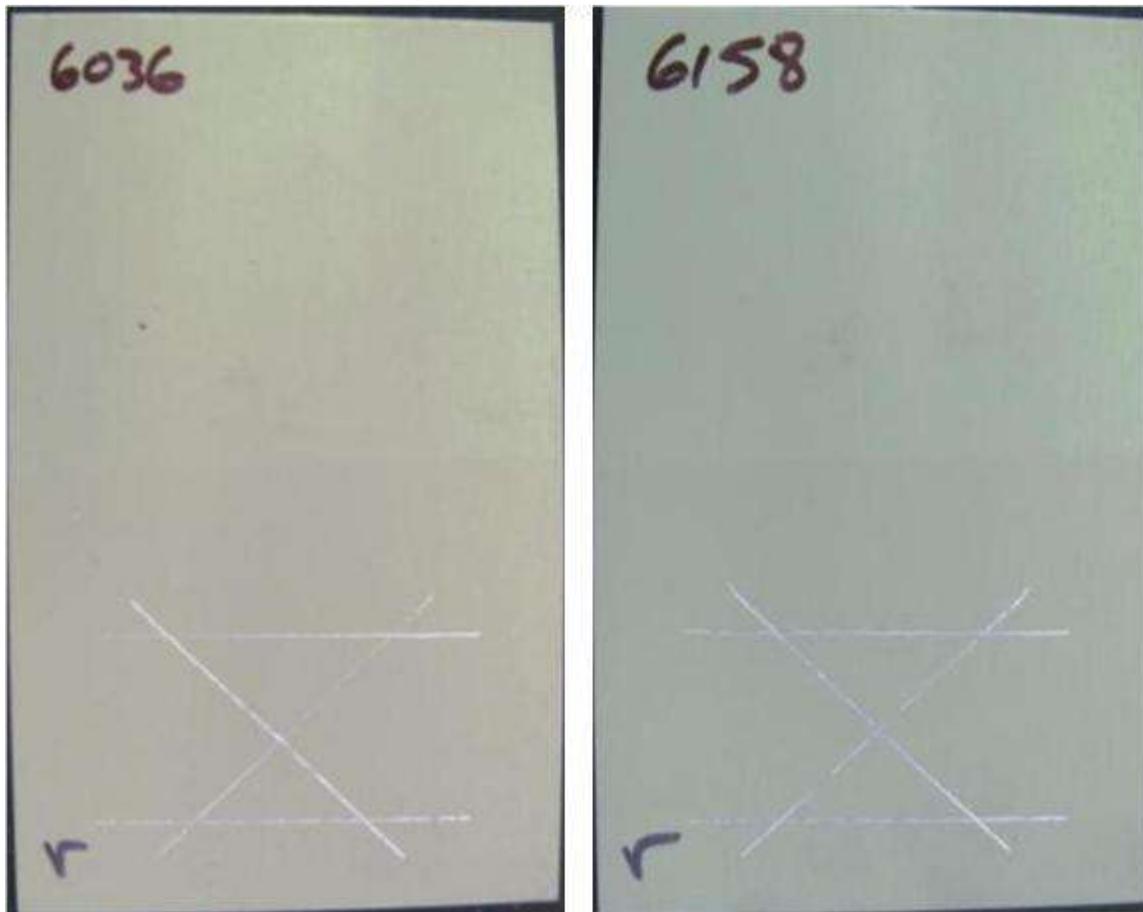


Figure 195 – SurTec 650; 6061-T6 (Left), 5052-H32 (Right)

3.6.8.6 SurTec 650C - Deft 44-GN-07A

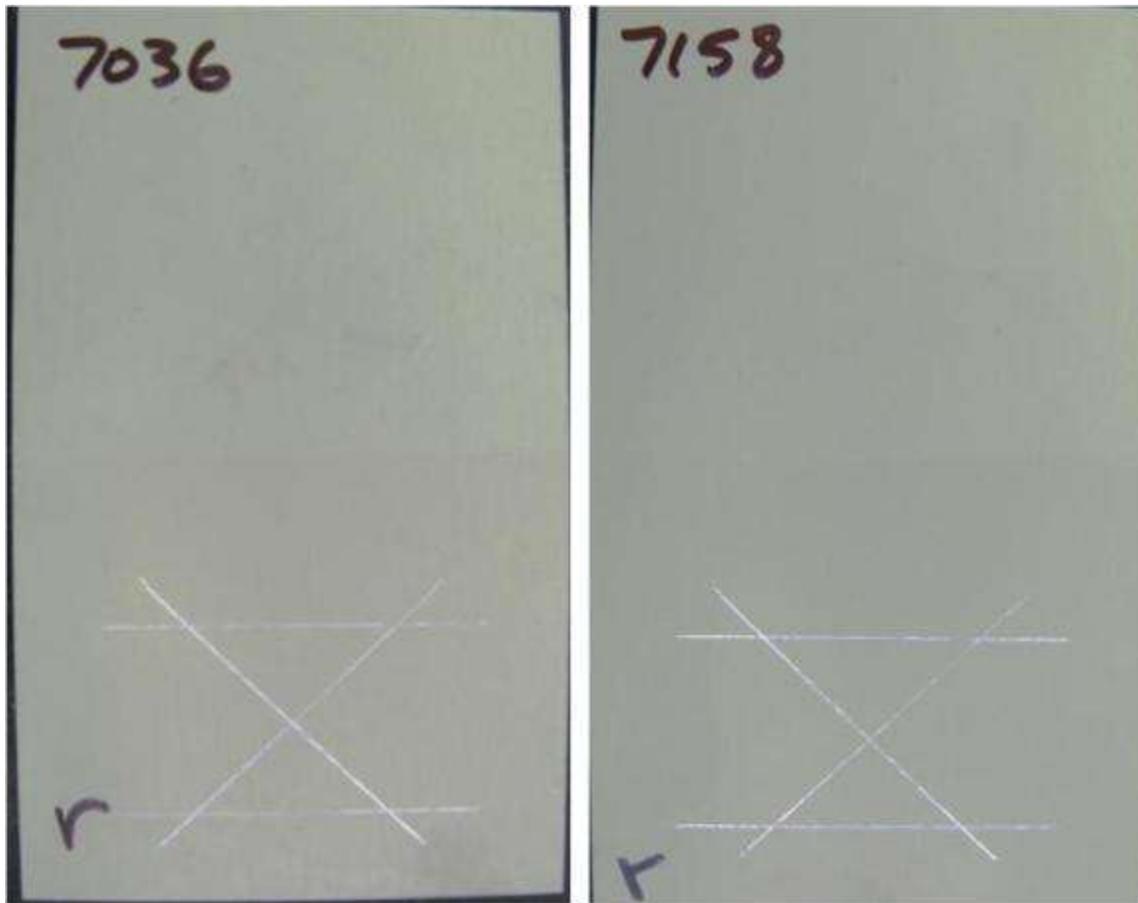


Figure 196 – SurTec 650C; 6061-T6 (Left), 5052-H32 (Right)

3.7 Surface Resistance Test

Stakeholders expressed interest in having this test for comparison with the contact electrical resistance procedure listed in MIL-DTL-81706B. A major difference in the ASTM D 257 procedure is the greatly reduced applied pressure on the electrodes.

3.7.1 Test Procedure

This test was conducted per ASTM D 257 (Standard Test Methods for DC Resistance or Conductance of Insulating Materials). An Electro-Tech Systems, model 803B surface, volume resistance, and resistivity probe connected to a Fluke 8846A multimeter with 4 point hook up set to 4 point resistance measurements was used to obtain measured resistance. The 803B probe is placed onto the surface of the test panel ensuring full contact is made. Pressure is then applied to the probe by hand (see Figure 197). Resistance measurements are recorded once readings on the multimeter stabilize. Surface resistance in ohms per square is equal to measured resistance times 10. Measures were taken before and after ASMT B 117 salt spray testing.



Figure 197 - Electro-Tech Systems, Model 803B Probe

3.7.2 Evaluation Procedure

The stakeholders of the Hex Chrome Free Coatings for Electronics Applications project did not set pass / fail criteria for this test.

3.7.3 Test Results - Surface Resistance Test

Surface resistance (ohms per square) data is contained in Figure 198 and Figure 199.

Pretreatment	Alloy	Unique Panel #	ohms per square 1	ohms per square 2	ohms per square 3	ohms per square 4	ohms per square 5	Average	Standard Deviation
Alodine 1600	6061-T6	1011	4.4	4.5	4.4	4.4	4.6	4.46	0.09
		1012	4.4	4.4	4.5	4.6	4.4	4.46	0.09
		1013	4.4	4.3	4.4	4.4	4.3	4.36	0.05
		1014	4.4	4.4	4.5	4.3	4.4	4.40	0.07
		1015	4.4	4.5	4.4	4.3	4.5	4.42	0.08
	7075-T73	1060	4.4	4.5	4.4	4.4	4.4	4.42	0.04
	2024-T3	1098	4.3	4.5	4.4	4.4	4.4	4.40	0.07
5052-H32	1137	4.4	4.3	4.4	4.4	4.5	4.40	0.1	
Alodine T 5900 RTU	6061-T6	2011	4	4.1	4.2	4.3	4.1	4.14	0.11
		2012	4.1	4.3	4.2	4.2	4.3	4.22	0.08
		2013	4.2	4.1	4.3	4.2	4.2	4.20	0.07
		2014	4	4.2	4.2	4.2	4.3	4.18	0.11
		2015	4	4.2	4.1	4.2	4	4.10	0.10
	7075-T73	2060	4	4.1	4.2	4	4.2	4.10	0.10
	2024-T3	2098	4.2	4.2	4.3	4.2	4.2	4.22	0.04
5052-H32	2137	4.3	4.1	4.2	4.1	4.2	4.18	0.08	
Iridite NCP	6061-T6	3011	4.7	4.5	4.6	4.5	4.6	4.58	0.08
		3012	4.4	4.6	4.7	4.6	4.5	4.56	0.11
		3013	4.4	4.5	4.7	4.6	4.6	4.56	0.11
		3014	4.6	4.4	4.5	4.5	4.4	4.48	0.08
		3015	4.4	4.5	4.4	4.5	4.4	4.44	0.05
	7075-T73	3060	4.4	4.6	4.4	4.5	4.4	4.46	0.09
	2024-T3	3098	4.4	4.4	4.5	4.6	4.5	4.48	0.08
5052-H32	3137	4.5	4.4	4.4	4.5	4.4	4.44	0.05	
Metalast HF	6061-T6	4011	4	4.1	4.2	4.1	4	4.08	0.08
		4012	4.2	4.1	4.3	4.2	4.4	4.24	0.11
		4013	4.3	4.1	4.3	4.2	4.3	4.24	0.09
		4014	4.3	4.1	4.3	4.2	4.2	4.22	0.08
		4015	4.1	4.1	4.2	4.1	4.2	4.14	0.05
	7075-T73	4060	4.1	4.2	4	4.1	4.2	4.12	0.08
	2024-T3	4098	4.1	4.3	4.2	4	4.2	4.16	0.11
5052-H32	4137	4.2	4.3	4	4.1	4.2	4.16	0.11	

Figure 198 – Surface Resistance Data, Pre ASTM B 117 Testing

Pretreatment	Alloy	Unique Panel #	ohms per square 1	ohms per square 2	ohms per square 3	ohms per square 4	ohms per square 5	Average	Standard Deviation
Metalast HF-EPA	6061-T6	5011	4.2	4.1	4.3	4.2	4.1	4.18	0.08
		5012	4.1	4.2	4.3	4.2	4.3	4.22	0.08
		5013	4.4	4.1	4.2	4.2	4.3	4.24	0.11
		5014	4.4	4.6	4.3	4.2	4.3	4.36	0.15
		5015	4.8	4.5	4.5	4.4	4.6	4.56	0.15
	7075-T73	5060	4.2	4.2	4.1	4.3	4.2	4.20	0.07
	2024-T3	5098	5.1	5	5.2	5.1	5.2	5.12	0.08
	5052-H32	5137	4.1	4.2	4.1	4.2	4.2	4.16	0.05
SurTec 650	6061-T6	6011	4.4	4.4	4.2	4.5	4.3	4.36	0.11
		6012	4.2	4.3	4.5	4.4	4.3	4.34	0.11
		6013	4.4	4.4	4.5	4.2	4.3	4.36	0.11
		6014	4.3	4.3	4.4	4.5	4.4	4.38	0.08
		6015	4.4	4.3	4.4	4.4	4.3	4.36	0.05
	7075-T73	6060	4.4	4.4	4.5	4.3	4.4	4.40	0.07
	2024-T3	6098	4.3	4.5	4.4	4.3	4.2	4.34	0.11
	5052-H32	6137	4.3	4.5	4.3	4.4	4.4	4.38	0.08
SurTec 650C	6061-T6	7011	4.3	4.2	4.5	4.4	4.4	4.36	0.11
		7012	4.5	4.4	4.4	4.5	4.3	4.42	0.08
		7013	4.4	4.2	4.3	4.2	4.4	4.30	0.10
		7014	4.4	4.5	4.2	4.2	4.4	4.34	0.13
		7015	4.4	4.2	4.4	4.4	4.3	4.34	0.09
	7075-T73	7060	4.2	4.4	4.4	4.4	4.3	4.34	0.09
	2024-T3	7098	4.2	4.3	4.3	4.4	4.4	4.32	0.08
	5052-H32	7137	4.3	4.5	4.3	4.4	4.5	4.40	0.10

Figure 199 - Surface Resistance Data, Pre ASTM B 117 Testing

3.8 Contact Electrical Resistance

This test is used to determine coating electrical resistance.

3.8.1 Test Procedure

This test was conducted per MIL-DTL-81706B (Chemical Conversion Materials for Coating Aluminum and Aluminum Alloys). Ten (10) replicates per substrate / per coating were prepared for this test; 5 for pre ASTM B 117 salt spray exposure measurements and 5 for post ASTM B 117 salt spray exposure measurements.

Measurements were made using two copper electrodes (1” diameter and 1.5” diameter) with end surfaces polished to a mirror finish fixed in an Instron compression tester. Before taking readings on the panels, baseline electrical resistance readings of the copper electrodes were taken. These values were subtracted from the panel electrical resistance values. The copper electrical resistance values were monitored for any increase in baseline resistance, which indicated a need to re-polish the electrodes.

When testing, the larger diameter (1.5”) copper electrode was positioned on the lower Instron compression plate. The test panel was positioned on top of the larger diameter copper electrode and then the smaller diameter (1”) copper electrode was centered over the lower electrode while 200 lbs of force was applied using the Instron. Once 200 lbs of force was achieved, electrical resistance readings were taken using a Hewlett-Packard 4328A milliohm meter. Probes were integrated into the copper electrodes for taking the resistance readings. Ten electrical resistance readings were taken on each panel (see Figure 200). The electrical resistance readings were averaged and the baseline copper electrode electrical resistance readings subtracted from the average; this value was divided by two to give the coating electrical resistance value.

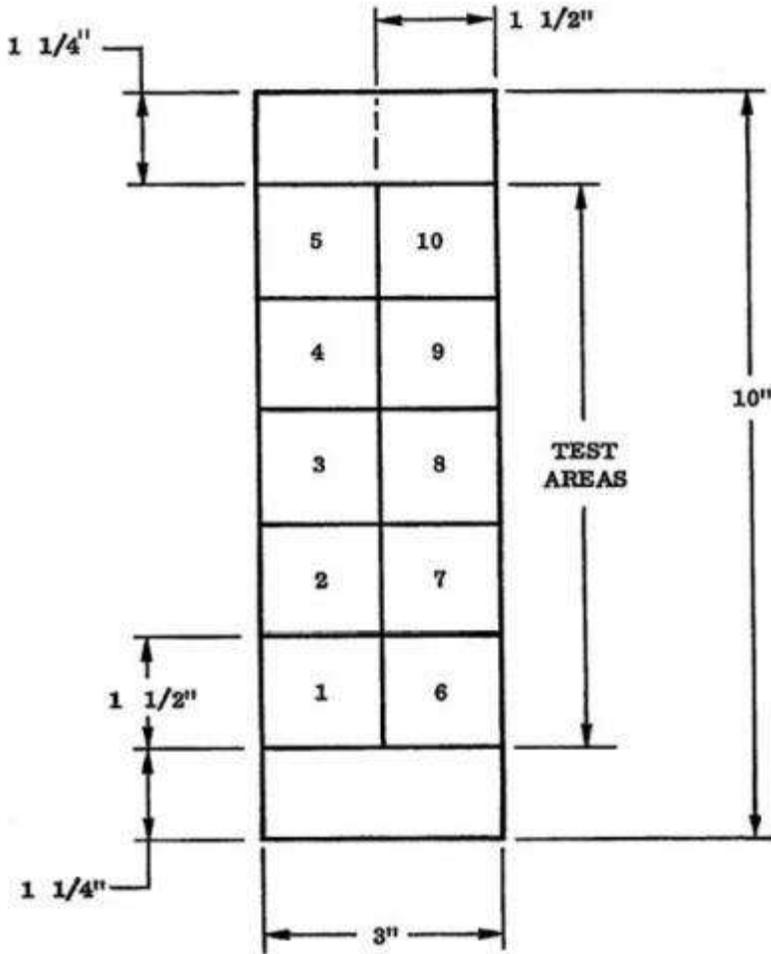


Figure 200 - Areas for measurements of electrical resistance on treated panels, MIL-DTL-81706B

3.8.2 Evaluation Procedure

Per MIL-DTL-81706B, the contact electrical resistance of aluminum alloy panels treated with class 3 materials under an applied electrode pressure of 200 pounds psi shall be not greater than 5,000 microhms psi as applied and 10,000 microhms psi after salt spray exposure. Individual readings not greater than 20 percent in excess of the specified maximums shall be acceptable, provided that the average of all readings does not exceed the specified maximum resistance.

3.8.3 Test Results - Contact Electrical Resistance

Coating electrical resistance values are provided in Figure 201. All of the pretreatments tested had coating electrical resistance values far below the specified maximum of 5,000 microhms.

microhms	2024-T3	5052-H32	6061-T6	7075-T73
Alodine 1600	449	422	433	349
Alodine T 5900 RTU	274	253	294	187
Iridite NCP	426	265	371	377
Metalast HF	177	41	73	278
Metalast HF-EPA	498	444	565	469
SurTec 650	600	759	647	451
SurTec 650C	572	745	702	650

Figure 201 – Contact Electrical Resistance Readings, Pre ASTM B 117

3.9 Screening Level Testing

Additional pretreatments were tested on a very limited basis in an effort to seek out new and emerging technologies. Candidates that perform well may be brought in for full testing in future projects. Since these coatings were only evaluated on a very limited basis, they are not being included in the overall Joint Test Report. Following is a list of pretreatments subjected to screening level testing:

- Alodine EC2
- Corrlink 30A
- Missouri S&T (aged samples)
- PPG X-Bond 4000
- Missouri S&T (newer samples)
- EonCoat
- Metalast TCPCC-600P
- NANOMYTE PT-10
- NANOMYTE TC-4001

4 Results Summary

The results from laboratory corrosion testing are contained in Figure 202. Alodine 1600, the control pretreatment, did not perform as expected. Following ASTM B 117 salt spray exposure, 168 hours, all of the test panels with Alodine 1600 were deemed failed. This unexpected result brings into question the compatibility of Alodine 1600 and the panel preparation procedure selected for this project. Following ASTM G 85, Annex 5 cyclic corrosion testing, test panels with Alodine 1600 revealed a clear trend with respect to pretreatment performance by alloy. Alodine 1600 on alloys known for their resistance to corrosion showed no evidence of corrosion when compared to unexposed control panels. Alodine 1600 on 2024-T3 and 7075-T73 alloys were determined failed after 168 hours of cyclic corrosion testing. These alloys are known to be more susceptible to corrosion due to their higher copper content but typically Alodine 1600 and other hexavalent chrome containing pretreatments are able to protect them adequately. Results from cyclic corrosion testing again bring into question the compatibility of Alodine 1600 and the panel preparation procedure selected for this project.

Following ASTM B 117 salt spray testing, 168 hours, hexavalent chrome free pretreatments revealed a clear trend with respect to pretreatment performance by alloy. Pretreatments on alloys known for their resistance to corrosion showed no evidence of corrosion when compared to unexposed control panels. Pretreatments on 2024-T3 and 7075-T73 alloys were determined failed after salt spray exposure. Such a strong delineation of the data across alloy type, regardless of hexavalent chrome free pretreatment, was not expected. This unexpected result brings into question the panel preparation procedure selected for this project. Following ASTM G85, Annex 5 cyclic corrosion testing, the hexavalent chrome free pretreatments revealed a clear trend with respect to pretreatment performance by alloy. As with ASTM B 117 test results, pretreatments on alloys known for their resistance to corrosion showed no evidence of corrosion when compared to unexposed control panels following cyclic corrosion testing. There was one exception to the trend; Metalast HF did show signs of corrosion on 6061-T6 and 5052-H32 alloys.

For ASTM B 117 salt spray testing, to failure, please review Section 3.1.5 for details on how the test panels were handled prior to testing.

Pretreatment	Alloy	B117 @ 168 Hours	G85 @ 168 Hours	B117 to Fail*
Alodine 1600	6061-T6	Fail	Pass	4 of 5 Pass @ 168
	7075-T73	Fail	Fail	Failed @ 168
	2024-T3	Fail	Fail	Failed @ 168
	5052-H32	Fail	Pass	1 of 5 Pass @ 168
Alodine 5900	6061-T6	Pass	Pass	3 of 5 Pass @ 168
	7075-T73	Fail	Fail	Failed @ 168
	2024-T3	Fail	Fail	Failed @ 168
	5052-H32	Pass	Pass	Pass @ 1008
Iridite NCP	6061-T6	Pass	Pass	4 of 5 Pass @ 168
	7075-T73	Fail	Fail	Failed @ 168
	2024-T3	Fail	Fail	Failed @ 168
	5052-H32	Pass	Pass	4 of 5 Pass @ 1008
Metalast HF	6061-T6	Pass	Fail	1 of 5 Pass @ 168
	7075-T73	Fail	Fail	Failed @ 168
	2024-T3	Fail	Fail	Failed @ 168
	5052-H32	Pass	Fail	2 of 5 Pass @ 1008
Metalast HF-EPA	6061-T6	Pass	Pass	4 of 5 Pass @ 168
	7075-T73	Fail	Fail	Failed @ 168
	2024-T3	Fail	Fail	Failed @ 168
	5052-H32	Pass	Pass	Pass @ 1008
Surtec 650	6061-T6	Pass	Pass	4 of 5 Pass @ 168
	7075-T73	Fail	Fail	Failed @ 168
	2024-T3	Fail	Fail	Failed @ 168
	5052-H32	Pass	Pass	Pass @ 1008
Surtec 650C	6061-T6	Pass	Pass	4 of 5 Pass @ 168
	7075-T73	Fail	Fail	Failed @ 168
	2024-T3	Fail	Fail	Failed @ 168
	5052-H32	Pass	Pass	4 of 5 Pass @ 1008

*Note - All five 6061-T6 test panels as well as 1 of 5 test panels for 7075-T73, 2024-T3, and 5052-H32 for all pretreatments were used for ASTM D 257 readings. Test panels were not tested at the same time as the others listed in the table. Testing with these test panels was stopped after 168 hours.

Figure 202 – Combined Corrosion Test Results

The results from tape adhesion testing are contained in Figure 203 and Figure 204. Overall, pretreatments with Deft 44-GN-07A had higher and more consistent ratings than pretreatments with PPG CA7233 primer. There are few exceptions, Iridite NCP with PPG CA7233 primer performed really well minus one off reading. Metalast HF with PPG CA7233 primer was rated perfect across all three adhesion tests. The discrepancy in results may be attributed to the fact that the PPG CA7233 coating was thicker than specified in the specifications for this test after it was applied. It is recommended that this test be re-run if funding permits for the most promising pretreatments in the next phase of testing.

Pretreatment	Alloy	Wet Tape Adhesion		Cross-Cut Tape
		24 hr. Immersion	4 Day Immersion @ 120°F	Rating
Alodine T 5900 RTU	6061-T6	3A	3A	1B
				1B
	5052-H32	5A	3A	1B
				1B
Iridite NCP	6061-T6	5A	5A	5B
				2B
	5052-H32	5A	5A	4B
				5B
Metalast HF	6061-T6	5A	5A	5B
				5B
	5052-H32	5A	5A	5B
				5B
Metalast HF-EPA	6061-T6	3A	3A	1B
				1B
	5052-H32	3A	3A	1B
				1B
SurTec 650	6061-T6	5A	5A	2B
				1B
	5052-H32	4A	3A	1B
				1B
SurTec 650C	6061-T6	4A	3A	2B
				2B
	5052-H32	4A	3A	2B
				2B

Figure 203 – Combined Adhesion Test Results; Pretreatments with PPG CA7233 primer

Pretreatment	Alloy	Wet Tape Adhesion		Cross-Cut Tape
		24 hr. Immersion	4 Day Immersion @ 120°F	Rating
Alodine T 5900 RTU	6061-T6	5A	5A	5B
				5B
	5052-H32	5A	5A	5B
				5B
Iridite NCP	6061-T6	5A	5A	5B
				5B
	5052-H32	5A	5A	5B
				5B
Metalast HF	6061-T6	5A	5A	5B
				5B
	5052-H32	5A	5A	5B
				5B
Metalast HF-EPA	6061-T6	5A	5A	5B
				5B
	5052-H32	5A	5A	5B
				5B
SurTec 650	6061-T6	5A	5A	5B
				5B
	5052-H32	5A	5A	4B
				5B
SurTec 650C	6061-T6	5A	5A	5B
				5B
	5052-H32	5A	5A	5B
				5B

Figure 204 - Combined Adhesion Test Results; Pretreatments with Deft 44-GN-07A primer

5 Recommendations

Inconsistent results across the hexavalent chrome control and hexavalent chrome free pretreatments have brought into question the panel preparation process used for this project. It is being suggested that a new panel process procedure should be developed and additional testing conducted. A new panel preparation process has been proposed. The single biggest change in the process is the replacement of Oakite LNC with Nitric acid at 50% concentration.

5.1 Proposed Panel Preparation Procedure

The following process has been developed with vendor and stakeholder input.

Solvent Hand Cleaning

The cleaner shall consist of Ethanol {200 proof}

Mild Alkaline Aqueous Degreaser (Non-Silicate)

Chemetall-Oakite NST – (5% by volume)

Bath temperature - 120oF (49oC)

Immersion time - 4 minutes

Bath needs to be stirred during test panel immersion

Panels will be rinsed with DI water to water break-free

DI water temperature 77oF (25oC)

Agitate test panels

Preceding degreasing steps will be repeated until water break-free is achieved

Deoxidize Bath (Nitric Acid)

Nitric acid at 50% concentration mixed with 5 megaohm or better DI water

Bath temperature - ambient temperature

Immersion time - 30 seconds

Rinse thoroughly using clean (5 megaohm or better) DI ambient temperature water.

DI water temperature 77oF (25oC)

Agitate test panels

Perform second rinse using clean (5 megaohm or better) DI ambient temperature water.

DI water temperature 77oF (25oC)

Take panels directly to pretreatment

5.2 Proposed Testing

The following testing procedures have been selected to retest the performance of hexavalent chrome free pretreatments in conjunction with the newly proposed panel preparation process.

- ASTM D 257
- MIL-DTL-81706B, Contact electrical resistance
- ASTM B 117 – to failure
- ASTM G85 {A5} – 168 hours
- Beach front
- Patti Jr. Pull-Off Adhesion
- Wet Tape Adhesion: 24 and 4 day (heated)
- Coating Weight